

## Doping dependence of the gap anisotropy in $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ studied by millimeter-wave spectroscopy

Artem V. Pronin, Andrei Pimenov, Alois Loidl, A. Tsukada, M. Naito

### Angaben zur Veröffentlichung / Publication details:

Pronin, Artem V., Andrei Pimenov, Alois Loidl, A. Tsukada, and M. Naito. 2003. "Doping dependence of the gap anisotropy in  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  studied by millimeter-wave spectroscopy." *Physical Review B* 68 (5): 054511. <https://doi.org/10.1103/PhysRevB.68.054511>.

### Nutzungsbedingungen / Terms of use:

licgercopyright

Dieses Dokument wird unter folgenden Bedingungen zur Verfügung gestellt: / This document is made available under these conditions:

#### Deutsches Urheberrecht

Weitere Informationen finden Sie unter: / For more information see:

<https://www.uni-augsburg.de/de/organisation/bibliothek/publizieren-zitieren-archivieren/publiz/>



## Doping dependence of the gap anisotropy in $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ studied by millimeter-wave spectroscopy

A. V. Pronin,<sup>1,2,\*</sup> A. Pimenov,<sup>1</sup> A. Loidl,<sup>1</sup> A. Tsukada,<sup>3</sup> and M. Naito<sup>3</sup>

<sup>1</sup>*Experimentalphysik V, Universität Augsburg, 86135 Augsburg, Germany*

<sup>2</sup>*Institute of General Physics, Russian Academy of Sciences, 119991 Moscow, Russia*

<sup>3</sup>*NTT Basic Research Laboratories, 3-1 Morinosato Wakamiya, Atsugi-shi, Kaganawa 243, Japan*

(Received 26 December 2002; published 7 August 2003)

We measure the penetration depth of optimally doped and underdoped  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  in the millimeter frequency domain ( $4\text{--}7\text{ cm}^{-1}$ ) and for temperatures  $2\text{ K} \leq T \leq 300\text{ K}$ . The penetration depth as a function of temperature reveals significant changes on electron doping. It shows quadratic temperature dependence in underdoped samples, but increases almost exponentially at optimal doping. Significant changes in the gap anisotropy (or even in the gap symmetry) may account for this transition.

DOI: 10.1103/PhysRevB.68.054511

PACS number(s): 74.25.Gz, 74.25.Nf, 74.72.Dn, 74.78.Bz

Being one of the keystones for theories of high-temperature superconductivity, the symmetry of the gap function in high  $T_c$ 's is one of the most attractive issues for experimental studies. At present  $d$ -wave pairing symmetry in hole-doped materials seems to be well established.<sup>1,2</sup> But so far there is no common consensus on electron-doped cuprates. It was initially suggested that these materials reveal an  $s$ -wave symmetry,<sup>3–6</sup> however, later measurements strongly supported a  $d$ -wave scenario.<sup>7–11</sup>

A number of recent reports indicate a possible transition in the gap symmetry with doping both in hole-<sup>12–14</sup> and electron-<sup>18,19</sup> doped cuprates. Tunneling data by Dagan and Deutscher<sup>12</sup> and by Sharoni *et al.*<sup>14</sup> suggest a possible transition from pure  $d_{x^2-y^2}$  to  $d_{x^2-y^2} + id_{xy}$  or  $d_{x^2-y^2} + is$  symmetry, while changing from the underdoped to the overdoped regime in  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  as well as in  $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$ . This transition could be due to surface effects, but possibly it reflects a bulk property, namely, the existence of a quantum critical point in these materials.<sup>15–17</sup> The paper by Yeh *et al.*<sup>13</sup> reports the changing of the pairing symmetry from predominately  $d_{x^2-y^2}$  in the underdoped and optimally doped  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  single crystals to  $d_{x^2-y^2} + s$  in the overdoped  $\text{Y}_{1-x}\text{Ca}_x\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$  thin films. That is, there is no apparent breaking of the time-reversal symmetry.

The point-contact spectroscopy data on electron-doped  $\text{Pr}_{2-x}\text{Ce}_x\text{CuO}_4$  by Biswas *et al.*<sup>19</sup> also indicate different pairing symmetries in samples with different doping:  $d$ -wave in the underdoped case and  $s$ -wave in the overdoped case. The radio-frequency inductance measurements by Skinta *et al.*<sup>18</sup> show a tiny, but measurable difference in the low-temperature ( $< 3\text{ K}$ ) behavior of the penetration depth among underdoped, optimally doped, and overdoped samples of  $\text{Pr}_{2-x}\text{Ce}_x\text{CuO}_4$  and  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ , indicating  $d$ -wave symmetry in the underdoped regime and  $s$ -wave symmetry in the optimally doped and overdoped regimes.

Overall the majority of these studies is quite consistent: the underdoped samples tend to demonstrate pure  $d$ -wave symmetry, while the overdoped samples rather reveal  $d + id_{xy}$ -,  $d + is$ -, or  $s$ -wave-like behavior. Optimal doping stays at the border of these two possibilities, falling more

into the pure  $d$ -wave limit in the hole-doped compounds,<sup>13</sup> and into the conventional  $s$ -wave-like behavior in the electron-doped ones.<sup>18</sup>

Here we present measurements of the superconducting penetration depth  $\lambda$  of optimally doped and underdoped electron superconductors  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  by a quasi-optical method at millimeter wavelengths.<sup>21</sup> We show that the temperature dependence of  $\lambda$  sensitively depends on the doping concentration.

High-quality  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  films with  $x = 0.106$  (optimally doped) and  $x = 0.081$  (underdoped) have been deposited by molecular-beam epitaxy<sup>22,23</sup> on transparent (001)-oriented  $\text{SrLaAlO}_4$  substrates. The substrates were plane-parallel plates, approximately  $10 \times 10\text{ mm}$  in size with thicknesses of  $0.335\text{ mm}$  for underdoped and  $0.472\text{ mm}$  for optimally doped films. The film thickness was  $140\text{ nm}$ . The films had sharp resistive and inductive transitions at  $T_c = 30\text{ K}$  (optimally doped sample) and  $25\text{ K}$  (underdoped sample) with  $\Delta T_c < 1\text{ K}$ .

The requirements to prepare high-quality  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  films are stringent cation stoichiometry adjustment and careful removal of the apical oxygen without phase decomposition. With regard to the latter issue, we kept films at  $600\text{ }^\circ\text{C}$  for  $10\text{ min}$  in oxygen pressure less than  $10^{-8}\text{ Torr}$  just after the film growth. By this reduction recipe, the superconducting properties were optimized. No phase decomposition was detected in the reflection high-energy electron-diffraction measurements. Although it is generally very difficult to evaluate the exact oxygen content in films, our *in situ*  $\text{Cu } 2p$  x-ray photoemission spectra on the film surfaces indicate that the Cu ions are mostly coordinated by four O ions in a square planar configuration (no apical oxygen). Similar studies are reported for  $\text{Nd}_{2-x}\text{Ce}_x\text{CuO}_4$  films in Ref. 20.

The temperature dependence of dc resistivity of both films, as measured by the standard four-probe method with evaporated Ag electrodes, is shown in Fig. 1. The overall shape of the  $\rho(T)$  curves is quadratic rather than linear. The underdoped sample reveals a slight upturn in  $\rho(T)$  at low temperatures ( $\leq 70\text{ K}$ ). This is an indication of localization effects, and is quite typical for this compound in the underdoped regime.<sup>23</sup>

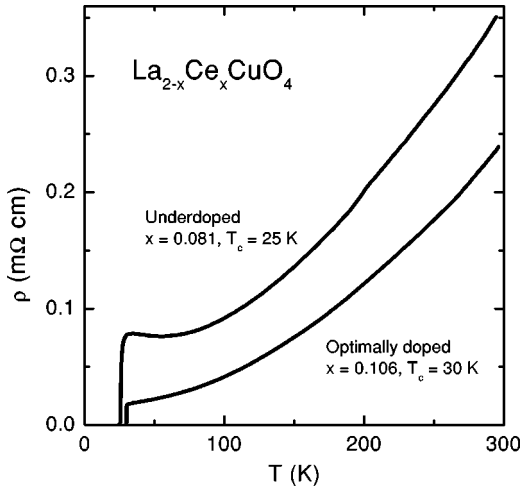


FIG. 1. Temperature dependence of dc resistivity for the optimally doped (bottom line) and the underdoped (upper line)  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  samples.

The measurements have been performed with a quasi-optical coherent source (backward-wave oscillator) spectrometer,<sup>21</sup> working in the millimeter-to-submillimeter wavelength domain. The Mach-Zehnder interferometer arrangement allows measuring both the intensity and the phase shift of the wave transmitted through the  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  films on the substrates. Using Fresnel optical formulas for the complex transmission coefficient of the substrate-film system, both components of the in-plane dynamic conductivity ( $\sigma_1 + i\sigma_2$ ) of the films have been directly calculated from these measurements. The penetration depth has been determined as  $\lambda = c/(4\pi\omega\sigma_2)^{1/2}$ , where  $c$  is the light velocity and  $\omega$  the angular frequency of the incident radiation. The optical parameters of the bare substrate have been measured in a separate experiment. At  $5\text{ cm}^{-1}$  the absorptive index of the substrate,  $k_{\text{sub}}$ , is below 0.01 at any temperature. The refractive index,  $n_{\text{sub}}$ , is equal to  $4.06 \pm 0.01$  at room temperature and  $4.03 \pm 0.01$  for  $T \rightarrow 0\text{ K}$ .

The as-measured transmission and phase-shift data are shown in Fig. 2. Since the  $\text{SrLaAlO}_4$  substrates have very low losses in the millimeter-to-submillimeter frequency range, the transmission level of the substrate-film “sandwich” is determined predominantly by the film properties. In the normally conducting state (above  $T_c$ ) the transmission is mainly controlled by the real part of the complex conductivity, while in the superconducting state both components of the complex conductivity contribute to the transmission, the imaginary part dominating at the lowest temperatures. The overall difference in the transmission levels between the two samples studied is due to difference of carrier concentrations in optimally doped and underdoped  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ .

The main contribution to the absolute values of the phase shift comes from the substrate. The major term of the phase shift is proportional to the substrate thickness multiplied by its refractive index  $n_{\text{sub}}$  and by the frequency of probing radiation. Since the thicknesses of the substrates were different, the phase level for the sample with the optimally doped film is higher than that for the sample with the underdoped film. The film contribution to the phase shift comes from

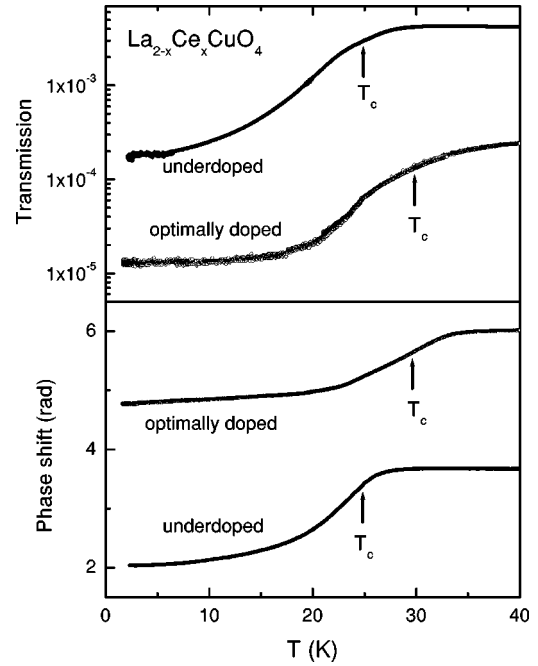


FIG. 2. Temperature dependence of the millimeter-wave ( $5\text{ cm}^{-1}$ ) intensity transmission (top panel) and of the corresponding phase shift (bottom panel) for optimally doped ( $x=0.106$ ,  $T_c=30\text{ K}$ ) and underdoped ( $x=0.081$ ,  $T_c=25\text{ K}$ )  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  films on  $\text{SrLaAlO}_4$  substrates.

both the real and the imaginary parts of the complex conductivity. Below  $T_c$  due to the Meissner effect,  $\sigma_2$  increases significantly and diverges at  $\omega \rightarrow 0$ , which leads to a negative contribution to the phase shift.

Let us recall that while processing the penetration depth data we used the complete Fresnel formulas, which automatically involve all contributions from the film complex conductivity to the transmission and phase shift, and take multiple reflections within the substrate into account.

Figure 3 shows the penetration depth of the optimally doped and the underdoped  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  samples measured at  $5\text{ cm}^{-1}$ . For better comparison with model calculations, the penetration depth data are plotted as  $\lambda^2(0)/\lambda^2(T)$  versus  $T/T_c$ , where  $\lambda(0)$  is the zero-temperature limit of the penetration depth. A substantially different behavior of  $\lambda(T)$  for samples with different doping is clearly seen at all temperatures below  $T_c$ . In the underdoped regime the experimental curve can be well fitted by a  $[1 - (T/T_c)^2]$  behavior, typical for high-temperature superconductors.<sup>24</sup> The results for the optimally doped sample look quite different; now a BCS-like<sup>25</sup>  $[1 - (T/T_c)^4]$  dependence (fully gapped superconductor) fits the experimental data. We note that the high-temperature ( $T > 0.9T_c$ ) tails in  $\lambda^2(0)/\lambda^2(T)$  are due to the influence of the normally conducting electrons:  $\sigma_2$  is not exactly zero above  $T_c$  at high frequencies.

The low-temperature variation of  $\lambda$  is shown in Fig. 4 as a function of  $T^2$ . Measurements at two additional frequencies (4 and  $6.7\text{ cm}^{-1}$ ) are also presented in this figure. In this representation the data of the underdoped sample follow rather well a straight line, while the data for the optimally doped sample demonstrate a much more gradual (although

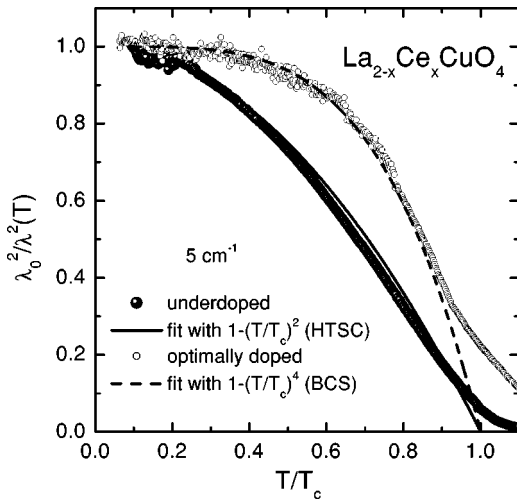


FIG. 3. Temperature dependence of the penetration depth in optimally doped ( $x=0.106$ ,  $T_c=30$  K) and underdoped ( $x=0.081$ ,  $T_c=25$  K)  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  at  $5\text{ cm}^{-1}$ . Points are experimental data, and lines indicate fits using  $1-(T/T_c)^2$  (solid line) and  $1-(T/T_c)^4$  (dashed line).

not really exponential) temperature dependence. No measurable frequency dependence of our findings is detected.

The absolute values of the penetration depth at the lowest temperatures are found to be equal to  $0.22 \pm 0.02\ \mu\text{m}$  in the optimally doped samples and  $0.38 \pm 0.03\ \mu\text{m}$  in the underdoped samples. Both values are in good agreement with data of Skinta *et al.*<sup>18</sup> Minor differences can be explained by slightly different doping levels of the samples marked as “underdoped” and “optimally doped” in Ref. 18 and in the present study.

The quadratic temperature dependence of the penetration depth in the underdoped sample provides strong experimental evidence of nodes in the gap function<sup>26</sup> and, likely, the  $d_{x^2-y^2}$ -wave pairing symmetry. The results in the optimally doped sample indicate a more isotropic gap function:  $d+is$ - or  $s$ -wave symmetry<sup>26</sup> seem to be good candidates for the gap symmetry in optimally doped  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ .

Since penetration depth measurements are not phase sensitive, it is impossible to decide from these measurements alone whether a transition of the gap symmetry exists. However, our results provide experimental evidence that the superconducting gap in the underdoped regime is significantly more anisotropic than in the optimally doped regime. As an alternative to a transition between two superconducting states characterized by different gap symmetries, one can imagine a gradual change in the gap anisotropy with  $d+is$ - or even with just anisotropic  $s$ -wave symmetry.

It is important to note that the influence of the quasiparticle scattering on the high-frequency (millimeter-wave) penetration depth data has to be clarified before making final conclusions on gap symmetry or the gap anisotropy transition. Strictly speaking, only the zero-frequency penetration

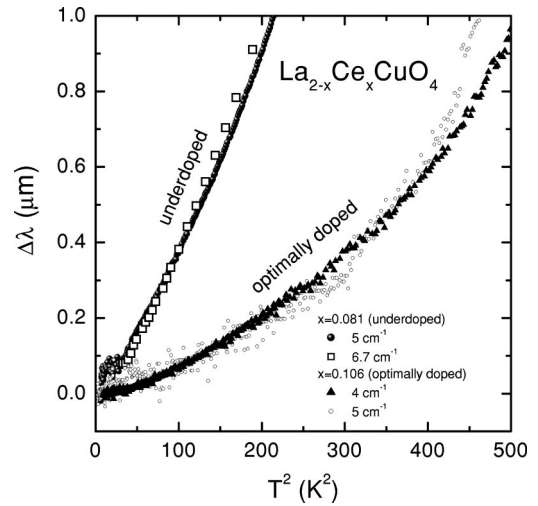


FIG. 4. Temperature variation of the penetration depth in  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  at low temperatures vs  $T^2$ . The experimental data for  $\nu=5\text{ cm}^{-1}$  are replotted from Fig. 3, and two additional data sets at 4 and  $6.7\text{ cm}^{-1}$  are added for the optimally doped and the underdoped samples, respectively.

depth is associated with the superconducting condensate, while the penetration depth at a finite frequency is partly influenced by the normal-conducting carriers.

A way to correctly and model-independently exclude the normal-conducting contribution to the high-frequency  $\lambda$  has been recently proposed by Dordevic *et al.*<sup>27</sup> It requires measurements of the complex conductivity over a wide frequency range. Such measurements have been undertaken by us at  $T=5$  K using the backward-wave-oscillator technique for frequencies from 4 to  $40\text{ cm}^{-1}$ , and standard infrared reflectivity measurements ( $40\text{--}4000\text{ cm}^{-1}$ ) with a Fourier-transform spectrometer.<sup>28</sup>

Applying the analysis given in Ref. 27, we have found the corrected zero-temperature values of the penetration depth:  $0.23\ \mu\text{m}$  for the optimally doped and  $0.4\ \mu\text{m}$  for the underdoped samples. The difference between the as-measured and the corrected penetration depth data is so minor because of very low residual losses in the investigated films. The details of the recalculation procedure together with the determination of the scattering rate in  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$  will be given elsewhere.<sup>29</sup>

In conclusion, we observed significant changes in the temperature dependence of the millimeter-wave penetration depth in optimally doped and underdoped  $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ .  $\lambda(T)$  behaves quadratically in the underdoped, but it is close to exponential in the optimally doped regime. A change in the gap anisotropy (or symmetry) is a plausible explanation for these dramatic differences.

We would like to thank L. Alff, J. F. Annett, D. N. Basov, G. Duetscher, R. Gross, R. Hackl, and D. van der Marel for useful discussions. The work was supported by BMBF via Contract No. 13N6917/0 - EKM.

- \*Electronic addresses: pronin@ran.gpi.ru;  
artem.pronin@physik.uni-augsburg.de
- <sup>1</sup>J.F. Annett, N. Goldenfeld, and A.J. Leggett, in *Physical Properties of High-Temperature Superconductors V*, edited by D.M. Ginsberg (World Scientific, Singapore, 1996), p. 375.
  - <sup>2</sup>C.C. Tsuei and J.R. Kirtley, *Rev. Mod. Phys.* **72**, 969 (2000), and references therein.
  - <sup>3</sup>D.H. Wu, J. Mao, S.N. Mao, J.L. Peng, X.X. Xi, T. Venkatesan, R.L. Greene, and S.M. Anlage, *Phys. Rev. Lett.* **70**, 85 (1993).
  - <sup>4</sup>S.M. Anlage, D.-H. Wu, J. Mao, S.N. Mao, X.X. Xi, T. Venkatesan, J.L. Peng, and R.L. Greene, *Phys. Rev. B* **50**, 523 (1994).
  - <sup>5</sup>L. Alff, S. Kleefisch, U. Schoop, M. Zittartz, T. Kemen, T. Bauch, A. Marx, and R. Gross, *Eur. Phys. J. B* **5**, 423 (1998).
  - <sup>6</sup>S. Kashiwaya, T. Ito, K. Oka, S. Ueno, H. Takashima, M. Koyanagi, Y. Tanaka, and K. Kajimura, *Phys. Rev. B* **57**, 8680 (1998).
  - <sup>7</sup>C.C. Tsuei and J.R. Kirtley, *Phys. Rev. Lett.* **85**, 182 (2000).
  - <sup>8</sup>J.D. Kokales, P. Fournier, L.V. Mercaldo, V.V. Talanov, R.L. Greene, and S.M. Anlage, *Phys. Rev. Lett.* **85**, 3696 (2000).
  - <sup>9</sup>R. Prozorov, R.W. Giannetta, P. Fournier, and R.L. Greene, *Phys. Rev. Lett.* **85**, 3700 (2000).
  - <sup>10</sup>N.P. Armitage, D.H. Lu, D.L. Feng, C. Kim, A. Damascelli, K.M. Shen, F. Ronning, Z.-X. Shen, Y. Onose, Y. Taguchi, and Y. Tokura, *Phys. Rev. Lett.* **86**, 1126 (2001).
  - <sup>11</sup>T. Sato, T. Kamiyama, T. Takahashi, K. Kurahashi, and K. Yamada, *Science* **291**, 1517 (2001).
  - <sup>12</sup>Y. Dagan and G. Deutscher, *Phys. Rev. Lett.* **87**, 177004 (2001).
  - <sup>13</sup>N.-C. Yeh, C.-T. Chen, G. Hammerl, J. Mannhart, A. Schmehl, C.W. Schneider, R.R. Schulz, S. Tajima, K. Yoshida, D. Garrius, and M. Strasik, *Phys. Rev. Lett.* **87**, 087003 (2001).
  - <sup>14</sup>A. Sharoni, O. Millo, A. Kohen, Y. Dagan, R. Beck, G. Deutscher, and G. Koren, *Phys. Rev. B* **65**, 134526 (2002).
  - <sup>15</sup>R.B. Laughlin, *Phys. Rev. Lett.* **80**, 5188 (1998).
  - <sup>16</sup>M. Vojta, Y. Zhang, and S. Sachdev, *Phys. Rev. Lett.* **85**, 4940 (2000).
  - <sup>17</sup>D.V. Khveshchenko and J. Paaske, *Phys. Rev. Lett.* **86**, 4672 (2001).
  - <sup>18</sup>J.A. Skinta, M.-S. Kim, T.R. Lemberger, T. Greibe, and M. Naito, *Phys. Rev. Lett.* **88**, 207005 (2002).
  - <sup>19</sup>A. Biswas, P. Fournier, M.M. Qazilbash, V.N. Smolyaninova, H. Balci, and R.L. Greene, *Phys. Rev. Lett.* **88**, 207004 (2002).
  - <sup>20</sup>H. Yamamoto, M. Naito, and H. Sato, *Phys. Rev. B* **56**, 2852 (1997).
  - <sup>21</sup>G.V. Kozlov and A.A. Volkov, in *Millimeter and Submillimeter Wave Spectroscopy of Solids*, edited by G. Grüner (Springer, Berlin, 1998), p. 51.
  - <sup>22</sup>M. Naito and M. Hepp, *Physica C* **357-360**, 333 (2001).
  - <sup>23</sup>M. Naito and M. Hepp, *Jpn. J. Appl. Phys., Part 2* **39**, L485 (2000).
  - <sup>24</sup>D.A. Bonn and W.N. Hardy, in *Physical Properties of High-Temperature Superconductors V* (Ref. 1), p. 7.
  - <sup>25</sup>M. Tinkham, *Introduction to Superconductivity* (McGraw-Hill, New York, 1975).
  - <sup>26</sup>J. F. Annett, N.D. Goldenfeld, and S.R. Renn, in *Physical Properties of High-Temperature Superconductors II*, edited by D.M. Ginsberg (World Scientific, Singapore, 1990), p. 571; J. Annett, N. Goldenfeld, and S.R. Renn, *Phys. Rev. B* **43**, 2778 (1991).
  - <sup>27</sup>S.V. Dordevic, E.J. Singley, D.N. Basov, S. Komiya, Y. Ando, E. Bucher, C.C. Homes, and M. Strongin, *Phys. Rev. B* **65**, 134511 (2002).
  - <sup>28</sup>For the underdoped composition these measurements have been reported in A. Pimenov, A.V. Pronin, A. Loidl, A. Tsukada, and M. Naito, cond-mat/0212400 (unpublished).
  - <sup>29</sup>A.V. Pronin, A. Pimenov, A. Loidl, A. Tsukada, and M. Naito (unpublished).