

Phonon anomalies in the infrared conductivity of the RuSr₂GdCu₂O₈ ferromagnetic superconductor

A. V. Boris, C. Bernhard, N. N. Kovaleva, Prabhat Mandal, Alois Loidl

Angaben zur Veröffentlichung / Publication details:

Boris, A. V., C. Bernhard, N. N. Kovaleva, Prabhat Mandal, and Alois Loidl. 2002. "Phonon anomalies in the infrared conductivity of the RuSr₂GdCu₂O₈ ferromagnetic superconductor." *Physica. B* 312-313: 797-99.
[https://doi.org/10.1016/S0921-4526\(01\)01228-5](https://doi.org/10.1016/S0921-4526(01)01228-5).

Phonon anomalies in the infrared conductivity of the $\text{RuSr}_2\text{GdCu}_2\text{O}_8$ ferromagnetic superconductor

A.V. Boris^{a,b,*}, C. Bernhard^a, N.N. Kovaleva^b, P. Mandal^{c,d}, A. Loidl^d

^aMax-Planck Institute FKF, Heisenbergstrasse, D-70569 Stuttgart, Germany

^bInstitute of Solid State Physics RAS, Chernogolovka 142432, Russia

^cSaha Institute of Nuclear Physics, 1/AF, Bidhannagar, Calcutta 700 064, India

^dEKM, Universität Augsburg, D-86135 Augsburg, Germany

Many aspects of the c -axis transport properties of superconducting (SC) bilayer compounds such as $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (Y-123) have been explained with a model invoking the onset of inter- and intrabilayer Josephson currents. In particular, this model explains a strong anomaly of the oxygen bond-bending phonon mode accompanied by the formation of an additional broad absorption peak in the c -axis optical conductivity of Y-123 [1]. The layered ruthenate-cuprate compound $\text{RuSr}_2\text{GdCu}_2\text{O}_8$ (Ru-1212) [2] presents a unique opportunity to develop the model of the bilayer Josephson plasmon for the case when a ferromagnetic moment is in the insulating plane. The present work aims to address this issue by studying the critical behavior in the infrared (IR) dielectric response of Ru-1212 near the superconducting $T_{\text{SC}} = 45$ K and magnetic $T_{\text{M}} = 133$ K transition temperatures.

Polycrystalline Ru-1212 samples were synthesized by solid-state reaction from high purity RuO_2 , SrCO_3 , Gd_2O_3 , and CuO powders. The ellipsometric measurements in the region from 50 to 3000cm^{-1} have been performed using a homebuilt setup attached to a “Bruker” IFS 133v spectrometer.

The measured real part of the IR conductivity $\sigma_1(\omega)$ and that of the dielectric function $\epsilon_1(\omega)$ of Ru-1212 for different temperatures are shown in Fig. 1. We applied a quantitative dispersion analysis in a Kramers–Kronig consistent way by fitting to the both $\sigma_1(\omega)$ and $\epsilon_1(\omega)$ a sum of Lorentzian functions. At room temperature the five distinct IR-active phonon modes at 128, 151, 190, 288, and 650cm^{-1} are superimposed on a featureless electronic background of $100\Omega^{-1}\text{cm}^{-1}$, consistent with the DC conductivity value. The IR-active phonons observed in the anisotropic ceramics are believed to correspond to the modes polarized along the c -axis and can be assigned similarly as reported for the c -axis optical phonons in Y-123 crystals. A comparison with the IR-spectra of Y-123 suggests that the phonon mode at 654cm^{-1} involves primarily the apical oxygen vibrations, whereas that at 288cm^{-1} is related to the

*Corresponding author. Tel.: +49-711-689-1735; fax: +49-711-689-1632.

E-mail address: boris@kmr.mpi-stuttgart.mpg.de (A.V. Boris).

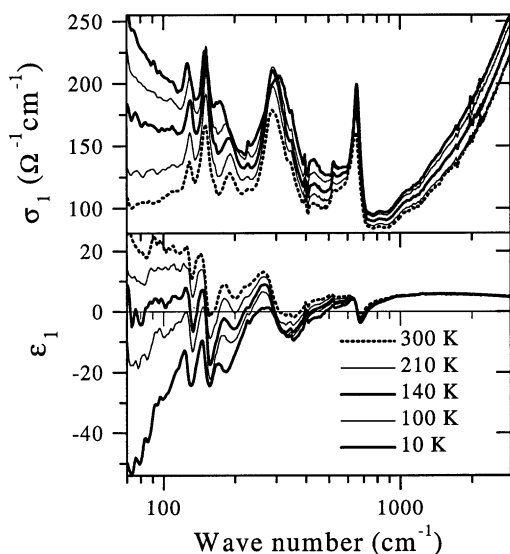


Fig. 1. Real part of the IR conductivity $\sigma_1(\omega)$ and the dielectric function $\epsilon_1(\omega)$ of Ru-1212 measured at different temperatures.

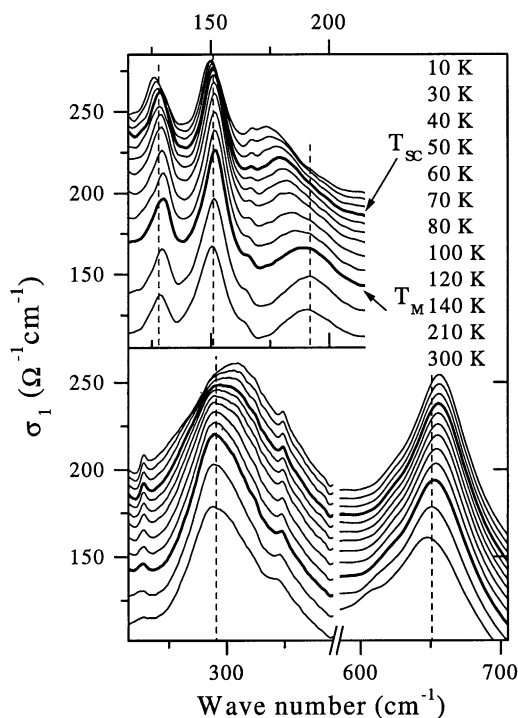


Fig. 2. Temperature dependence of $\sigma_1(\omega)$ at the phonon frequencies: successive curves are offset by $5 \Omega^{-1} \text{ cm}^{-1}$ for clarity.

Cu–O bending mode which involves vibrations of the oxygen ions of the CuO_2 planes. The three low-frequency modes at 128, 151, and 190 cm^{-1} are suggested to be assigned to the displacements of Cu, Gd, and Ru, respectively. Fig. 2 shows $\sigma_1(\omega)$ at the

phonon frequencies in detail for different temperatures. Among all phonon modes, only the apical oxygen mode exhibits the classical inharmonic increase of the eigenfrequency on decreasing temperature, revealing anomalies neither at T_{SC} nor at T_{M} . At the same time the low-frequency phonon modes show a characteristic softening at T_{SC} as observed in Y-123 related compounds.

The most apparent feature related to the onset of superconductivity is the transformation of the bending mode at 288 cm^{-1} to a broad band centered at 308 cm^{-1} . The transformation of the band profile starts at around 90 K being well below T_{M} , but also well above T_{SC} . The most pronounced changes are observed at T_{SC} . Comparing the temperature dependence of the asymmetric peak in Ru-1212 at 288 cm^{-1} with the data reported by Munzar et al. [1] for $\text{YBa}_2\text{Cu}_3\text{O}_{6.45}$ we find a striking similarity. The gradual onset of the anomalies above T_{SC} is explained within the model of the bilayer Josephson plasmon as due to the persistence of a coherent superconducting state within the individual copper–oxygen bilayers, whereas the steep and sudden changes at T_{SC} occur when the macroscopically coherent superconducting state forms. The present observation suggests a strongly underdoped character of the bulk superconductivity in Ru-1212 originated in weakly coupled cuprate biplanes.

The most remarkable feature associated with the onset of ferromagnetic order within the Ru–O layers at T_{M} is the anomalous softening of the mode at 190 cm^{-1} observed on decreasing temperature below T_{M} . This fact indicates that the Ru-related phonon mode is strongly affected by the interaction with the electronic system. The onset of this effect at the magnetic transition temperature can be explained by the renormalization of the electron–phonon coupling when the kinetic energy of the itinerant electrons increases due to the onset of the ferromagnetic correlations in the Ru–O layers. In favor

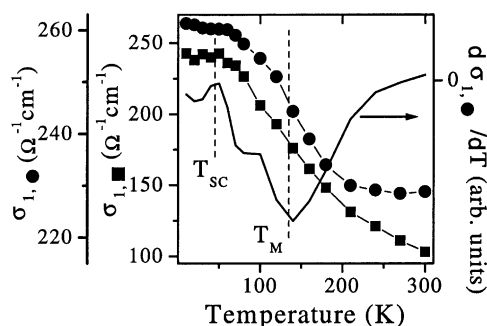


Fig. 3. Temperature dependences of σ_1 measured at $\omega = 75 \text{ cm}^{-1}$ (solid squares) and $\omega = 3000 \text{ cm}^{-1}$ (solid circles). The solid line shows the derived function of $\sigma_1(T)$ at $\omega = 3000 \text{ cm}^{-1}$.

of this scenario an increase of $\sigma_1(\omega)$ spectral weight in the mid-IR range at frequencies $\omega > 1000 \text{ cm}^{-1}$ is observed on lowering temperature below T_M . Fig. 3 shows indeed that the temperature dependence of σ_1 measured at $\omega = 3000 \text{ cm}^{-1}$ (solid circles) exhibits maximum negative derivative (solid line) right at T_M while the dependence of σ_1 at $\omega = 75 \text{ cm}^{-1}$ (solid squares) reproduces well that of the DCconductivity at $T > T_{SC}$. Finally, we note that the behavior of the optical conductivity of Ru-1212 observed in

the present study is in a good agreement with the previous report based on conventional reflection measurements [3].

References

- [1] D. Munzar, et al., Solid State Commun. 112 (1999) 365.
- [2] C. Bernhard, et al., Phys. Rev. B 61 (2000) R14960.
- [3] A.V. Boris, et al., Phys. Rev. B 63 (2001) 184505.