

Magnetic correlations in frustrated LiV_2O_4 and ZnV_2O_4

Norbert Büttgen, Alexander Krimmel, Alois Loidl, Matthias Klemm, Siegfried R. Horn, D. R. Noakes, E. Schreier, G. M. Kalvius

Angaben zur Veröffentlichung / Publication details:

Büttgen, Norbert, Alexander Krimmel, Alois Loidl, Matthias Klemm, Siegfried R. Horn, D. R. Noakes, E. Schreier, and G. M. Kalvius. 2002. "Magnetic correlations in frustrated LiV_2O_4 and ZnV_2O_4 ." *Physica B* 312-313: 703–5. [https://doi.org/10.1016/S0921-4526\(01\)01489-2](https://doi.org/10.1016/S0921-4526(01)01489-2).

Magnetic correlations in frustrated LiV_2O_4 and ZnV_2O_4 [☆]

N. Büttgen^{a,*}, A. Krimmel^a, A. Loidl^a, M. Klemm^a, S. Horn^a, D.R. Noakes^b,
E. Schreier^c, G.M. Kalvius^c

^a*Inst. für Physik, Elektronische Korrelationen und Magnetismus, Universität Augsburg, 86135 Augsburg, Germany*

^b*Physics Department, Virginia State University, Petersburg, VA 23806, USA*

^c*Physics Department, TU Munich, 85747 Garching, Germany*

In the AB_2O_4 normal spinel structure, the B ions form a sublattice of corner sharing tetrahedra while each B ion is octahedrally coordinated by six oxygens. For an ideal tetrahedral lattice of V spins on the B site in $(\text{Li:Zn})\text{V}_2\text{O}_4$ combined with simple antiferromagnetic (AFM) next-nearest neighbor interactions, a highly frustrated magnetic state results. The characteristic feature of this *geometric* frustration is the absence of long-range (Néel) order, in contrast to canonical spin glasses where frustration is caused by site disorder [1]. It has been pointed out [2] that in the cubic spinels canonical spin-glass behavior is unlikely. LiV_2O_4 gained additional interest after reports of heavy-fermion (HF) formation at low temperatures [3], making it a d-based HF system. The role of geometric frustration in

connection with Fermi-liquid behavior is discussed in Refs. [4,5]. Heavy-quasiparticle excitations originating from Heisenberg rings with $S = \frac{1}{2}$ and chains with $S = 1$ have been calculated in Ref. [6]. Quasielastic neutron scattering showed that at higher temperatures the relaxation rates increase linearly on momentum transfer typical of ferromagnetic spin-fluctuation systems [7]. Below 40 K, AFM fluctuations dominate and the relaxation depends only weakly on momentum transfer.

Fig. 1 presents the temperature dependence of the spin-lattice relaxation of LiV_2O_4 at different frequencies and external fields. At low frequencies a cusp-shaped maximum appears at ~ 0.6 K which becomes suppressed at higher frequencies and fields. Below 2 K the anomalous temperature dependence of $1/T_1$ is strongly dependent on frequency and the nuclear relaxation is markedly enhanced at low frequencies. These are similar characteristics as seen for the Li nuclear relaxation in Li doped CuO and NiO [8]. Those results have been compared to the spin dynamics in cuprate superconductors. Based on this interpretation the cusp-like anomalies in Fig. 1 are due to an exponentially decreasing magnetic relaxation rate $\Gamma = \Gamma_0 \exp(-\Delta/k_B T)$ indicating the slowing down of spin fluctuations on the NMR time scale. The corresponding

[☆]Work was supported by the Federal Ministry BMBF Germany under the contract number EKM 13N6917/0, the Sonderforschungsbereich 484 (Augsburg) of the Deutsche Forschungsgemeinschaft (DFG), and the US Air Force Office of Scientific Research.

*Corresponding author. Tel.: +49-821-598-3604; fax: +49-821-598-3649.

E-mail address: norbert.buettgen@physik.uni-augsburg.de (N. Büttgen).

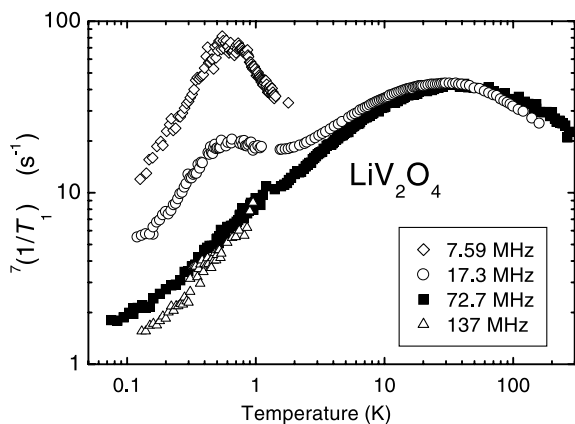


Fig. 1. ${}^7\text{Li}$ NMR spin-lattice relaxation rate $\log(1/T_1)$ vs. $\log T$ in LiV_2O_4 measured at different frequencies/applied fields.

slowing down of $1/T_1$ is driven by a characteristic energy Δ of the order of 1 K. This energy reflects probably an average barrier between neighboring configurations of a highly degenerate ground state. Alternatively, the effective interaction energy Δ could be caused by dynamic singlet pairing leading to an interpretation along the model of a ‘cooperative paramagnet’ proposed in Ref. [2]. The persistence of slow spin dynamics was also observed in a μSR study [9] down to 20 mK. The μSR rate of the LiV_2O_4 sample with the lowest impurity concentration showed on cooling only a slowing down of spin fluctuations, with no indication of static spin freezing. We point out that these μSR results combined with the absence of a static quadrupolar splitting in the ${}^7\text{Li}$ NMR spectra [10] give strong evidence that the spin-lattice relaxation process in our NMR data is not driven by the interaction of dynamic electric field gradients with the ${}^7\text{Li}$ quadrupole moment.

In ZnV_2O_4 a cubic to tetragonal phase transition occurs around 50 K [11] which is claimed to remove the geometric frustration. This was supported by an earlier neutron diffraction (ND) study reporting AFM order below 45 K [12]. A new experiment with the aim to verify the results of [12] showed no well defined magnetic Bragg peaks (see inset in Fig. 2) and the data were compatible with short-range magnetic order at best. This initiated the μSR study in order to clarify the situation. The measurements were carried out at the M20 surface muon facility of TRIUMF. From the shape of the zero field (ZF) spectra one can distinguish three magnetic regions, labeled III, II, I in order of descending temperature as it is shown in Fig. 2. In region III ($T > 40$ K), the muon spin relaxes exponentially with a very low and temperature independent rate λ_{para} which is

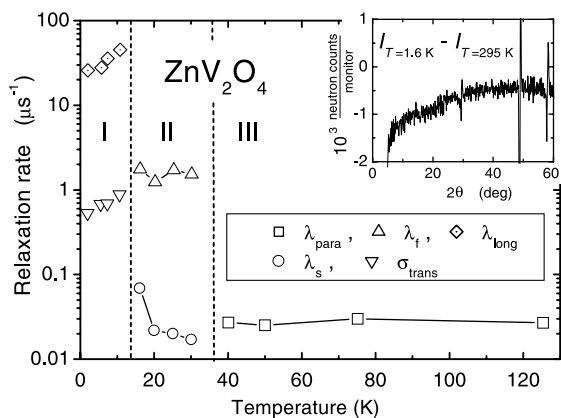


Fig. 2. μSR rates as a function of temperature in ZnV_2O_4 . The meaning of the labels are explained in text. Inset: difference spectrum from neutron diffraction.

typical of a well-established paramagnetic state where uncorrelated spins fluctuate rapidly. In region II ($10 \text{ K} < T < 40 \text{ K}$) two magnetic states coexists: The paramagnetic state with slow relaxation rates λ_s together with a dynamically correlated spin-glass-like state characterized by fast exponential relaxation rates λ_f . The fast rate is barely affected by a longitudinally (i.e. in muon spin direction) applied field of 3 kOe proving that the latter state is far away from spin freezing. The relative volume fraction of this state increases continuously on cooling. A similar magnetic regime was detected by μSR in other geometrically frustrated compounds, as YMn_2 and related intermetallics [13]. The rate λ_s increases on cooling toward 10 K, showing the typical critical slowing down of paramagnetic spin fluctuations on approach to a magnetic transition. No such effect is seen in region III, meaning that 40 K is not a magnetic phase transition point. In region I ($T \leq 10$ K), the observed μSR signal is of the form $A(t) = (a_0/3)\{2J_0(\omega_\mu t) \exp[-\sigma_{\text{trans}}^2 t^2] + \exp[-\lambda_{\text{long}} t]\}$ with J_0 being the zero-order Bessel function and ω_μ the muon spin precession frequency. The two terms are the transverse and the longitudinal signal of an ordered magnetic powder sample. The Bessel-type oscillations are the result of the special distribution of the field at the muon site in an incommensurate spin density wave (ISDW). The presence of the additional Gaussian damping term indicates an additional source of field distribution such as local random spin disorder in the ISDW structure. Fig. 2 shows the rate σ_{trans} to be very large. The local spin disorder must be substantial, preventing true long-range correlations in the ISDW state. This explains our ND result. The longitudinal rate λ_{long} is the response to slow spin fluctuations (i.e. within the μSR time window of MHz to GHz) in an ordered

state. Fig. 2 demonstrates that these spin fluctuations persists to low temperatures and that the system never reaches the quasi-static limit characteristic for typical ferro- or antiferromagnets. The persistent spin fluctuations, which tie in with the results for LiV_2O_4 , the substantial local spin disorder, which prevents the formation of a fully long-range correlated magnetic ground state, and the occurrence of a dynamic spin-glass-like magnetic precursor state are all indications for the presence of geometric frustration. The tetragonal lattice distortion in ZnV_2O_4 removes some, but not all, frustration. The partial removal of frustration allows the formation of a medium-range correlated magnetic ground state, in contrast to the situation in LiV_2O_4 .

References

- [1] K. Binder, A.P. Young, *Rev. Mod. Phys.* 58 (1986) 801.
- [2] J. Villain, *Z. Physik B* 33 (1979) 31.
- [3] S. Kondo, et al., *Phys. Rev. Lett.* 78 (1997) 3729.
- [4] C. Urano, et al., *Phys. Rev. Lett.* 85 (2000) 1052.
- [5] S.-H. Lee, et al., *Phys. Rev. Lett.* 86 (2001) 5554.
- [6] P. Fulde, et al., *Europhys. Lett.* 54(2001) 779.
- [7] A. Krimmel, et al., *Phys. Rev. Lett.* 82 (1999) 2919.
- [8] M. Corti, et al., *Phys. Rev. B* 56 (1997) 11 056.
- [9] J. Merrin, et al., *J. Magn. Magn. Mater.* 177–181 (1998) 799.
- [10] W. Trinkl, et al., *Phys. Rev. B* 62 (2000) 1793.
- [11] Y. Ueda, et al., *J. Phys. Soc. Jpn.* 66 (1997) 778.
- [12] S. Nizioł, *Phys. Stat. Sol. A* 18 (1973) K11.
- [13] G.M. Kalvius, *Hyperfine Interact.* 84 (1994) 249.