

Terahertz excitations in α -RuCl₃: Majorana fermions and rigid-plane shear and compression modes

Stephan Reschke, Vladimir Tsurkan, S.-H. Do, K.-Y. Choi, Peter Lunkenheimer, Zhe Wang, Alois Loidl

Angaben zur Veröffentlichung / Publication details:

Reschke, Stephan, Vladimir Tsurkan, S.-H. Do, K.-Y. Choi, Peter Lunkenheimer, Zhe Wang, and Alois Loidl. 2019. "Terahertz excitations in α -RuCl₃: Majorana fermions and rigid-plane shear and compression modes." *Physical Review B* 100 (10): 100403(R).
<https://doi.org/10.1103/physrevb.100.100403>.



Terahertz excitations in α -RuCl₃: Majorana fermions and rigid-plane shear and compression modes

S. Reschke,¹ V. Tsurkan,^{1,2} S.-H. Do,³ K.-Y. Choi,³ P. Lunkenheimer,¹ Zhe Wang,^{4,*} and A. Loidl^{1,†}

¹*Experimental Physics V, Center for Electronic Correlations and Magnetism, University of Augsburg, 86159 Augsburg, Germany*

²*Institute of Applied Physics, MD 2028 Chisinau, Republic of Moldova*

³*Department of Physics, Chung-Ang University, Seoul 06974, Republic of Korea*

⁴*Institute of Radiation Physics, Helmholtz-Zentrum Dresden-Rossendorf, 01328 Dresden, Germany*



(Received 27 February 2019; revised manuscript received 9 July 2019; published 6 September 2019)

Spin liquids may host emergent quasiparticles, collective excitations of the spin degrees of freedom with characteristic features of Majorana fermions, which experimentally are detectable by broad excitation continua due to spin fractionalization. The latter is predicted for the Kitaev spin liquid, an exactly solvable model with bond-dependent interactions on a two-dimensional honeycomb lattice. Here we report on detailed terahertz experiments in α -RuCl₃, identifying these characteristic fingerprints of Majorana fermions. The continuum intensity decreases and finally vanishes on increasing temperature. It partly overlaps with phonon modes, representing characteristic sliding and compression modes of the van der Waals bonded molecular layers.

DOI: [10.1103/PhysRevB.100.100403](https://doi.org/10.1103/PhysRevB.100.100403)

Majorana fermions are exotic particles being identical with their antiparticles, and it is an open question whether they exist in nature as elementary building blocks of matter. Recently, the realization of Majorana fermions as fundamental quasiparticles came into the focus of solid-state physics. Such quasiparticles can be realized in semiconductor-superconductor hybrid structures [1] via exchange-coupled ferromagnetic atoms [2] or in vortex cores of iron-based superconductors [3]. Besides their importance in correlated quantum matter, considerable interest stems from possible applications in quantum information [4]. Majorana quasiparticles also can be observed in spin liquids: α -RuCl₃, with effective spin- $\frac{1}{2}$ moments on a honeycomb lattice, is a prime candidate to host a Kitaev spin-liquid (KSL) ground state. The two-dimensional (2D) Kitaev model [5] with bond-dependent interactions is exactly solvable via the fractionalization of quantum spins into two types of Majorana fermions: Z_2 fluxes and itinerant fermions. Kitaev physics and appropriate materials are discussed in recent review articles [6,7].

In scattering experiments, these fractionalized excitations can be observed as characteristic continua up to temperatures comparable to the typical Kitaev exchange of order ~ 100 K. There are detailed theoretical proposals to observe spin fractionalization in the dynamic response via inelastic neutron scattering [8–12], Raman scattering [13,14], optical terahertz spectroscopy [12,15–17], as well as resonant inelastic x-ray-scattering experiments [18]. Indeed, broad continua in α -RuCl₃ were reported in neutron-scattering measurements [19–22], as well as in Raman [23,24] and terahertz experiments [25–28]. However, the interpretation of these broad

and featureless intensities in terms of fractional excitations of the spin liquid remains controversial [6,29,30]. Very recently, the observation of a half-integer thermal quantum Hall effect was interpreted as a hallmark of fractionalization of quantum spins [31].

In this work, we present detailed time-domain terahertz experiments in a broad frequency and temperature regime on high-quality single crystals of α -RuCl₃. Our results provide experimental evidence for the existence of a continuum with a characteristic temperature dependence, which we interpret in terms of fractionalized spin excitations. In addition, the continuum significantly decreases when passing the structural phase transition from the low-temperature rhombohedral to the high-temperature monoclinic phase. It signals the decreasing importance of Kitaev exchange in the honeycomb lattice with monoclinic distortions. This magnetic continuum partly overlaps with phononlike excitations, which can be described as characteristic rigid-plane shear and compression modes of molecular layers that are only weakly bonded by van der Waals (vdW) forces. These rigid-plane modes are characteristic features of 2D crystals and were observed in graphene multilayers and in dichalcogenides [32–35].

Terahertz experiments on α -RuCl₃ in a smaller energy range have been reported earlier, mainly focusing on the evolution of the low-temperature magnetic scattering [26]. To avoid the influence of phonon excitations and of the structural phase transition, all spectra were normalized to 60 K, and the evolution of a continuum was documented below this temperature only. Here we focus on the full spectral range up to 14 meV and up to room temperature. This takes into account that spin fractionalization will dominate the dynamic conductivity from the breakdown of magnetic order at least up to temperatures comparable to the Kitaev exchange of order ~ 100 K, while the pure phonon response is only weakly temperature dependent.

*Present address: Institute of Physics II, University of Cologne, 50937 Cologne, Germany.

†Corresponding author: alouis.loidl@physik.uni-augsburg.de

α -RuCl₃ is a layered compound, with each honeycomb lattice of ruthenium embedded within two hexagonal layers of chlorine. Ru³⁺(4d⁵) is octahedrally coordinated by Cl ions and exhibits an effective spin-1/2 ground state. The ruthenium ions, strongly bonded to adjacent chlorine layers, represent rigid molecular units which are only weakly connected by vdW forces to each other. Recent experiments converge towards a monoclinic (*C2/m*) room-temperature structure [36], which transforms via a strongly hysteretic first-order phase transition into a low-temperature rhombohedral phase [27,28,37]. In the rhombohedral phase with $R\bar{3}$ symmetry, the molecular stacks exhibit an ABC-type layering [37]. The phase transition into the monoclinic *C2/m* structure induces only little change in the geometry of the RuCl₃ slabs. There the molecular layers are displaced along the crystallographic *a* direction, yielding slight deviations from the low-temperature three-layer stacking periodicity. The main structural change is an increase in the interlayer spacing [28,37]. The monoclinic *C2/m* high-temperature phase exhibits a single-layer periodicity only. The effective spin-1/2 of the ruthenium ions on the honeycomb lattice undergo long-range antiferromagnetic order close to 7 K [28] and exhibit a characteristic zigzag spin pattern [36].

High-quality α -RuCl₃ single crystals were grown by vacuum sublimation. The sample characterization is described in detail in Refs. [21,37] and in the supplementary material of Ref. [28]. In the samples that have been investigated in the course of this work, the structural phase transition appeared close to 170 K (on heating) and antiferromagnetic order was established below 6.5 K. The samples for the optical terahertz experiments had a typical *ab* surface of 5 × 3 mm² and a thickness of ~1 mm. Time-domain terahertz transmission experiments were performed with the wave vector of the incident light perpendicular to the crystallographic *ab* plane using a TPS Spectra 3000 spectrometer. We measured time-domain signals for reference (empty aperture) and samples, from which power spectra were evaluated via Fourier transformation. The transmission spectra show characteristic modulation due to multiple scattering events within the sample. Whenever necessary, we tried to correct for these interference effects by calculating the interference pattern for a given thickness and refractive index of the sample.

Figure 1 documents the temperature dependence of the real part of the dielectric constant ϵ' and of the real part of the dynamic conductivity σ' , as determined by terahertz spectroscopy for energies between 1 and 14 meV and temperatures between 4.5 and 300 K. Both quantities document the weak dipolar strength of all excitations in this energy regime. The continuous decrease of the dielectric constant with decreasing energy results from contributions of high-energy phonons (not shown).

At the lowest temperatures, the conductivity spectra [Fig. 1(b)] are dominated by a narrow excitation close to 2.5 meV, a broad continuum around 8.5 meV, and a strong increase beyond 12 meV. The latter results from a weak phonon mode centered close to 15 meV [27,38]. An additional weak excitation close to 6 meV strongly overlaps with the continuum. The features at the lowest and highest frequencies are barely temperature dependent, while the continuum mode steadily decreases with increasing temperature and finally

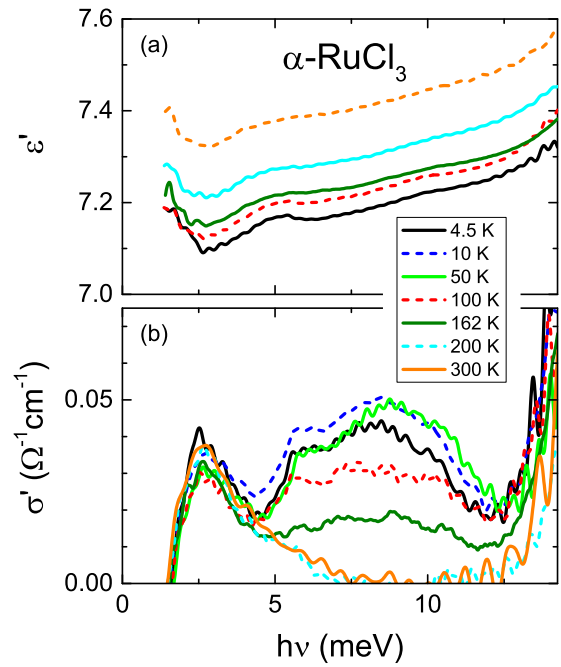


FIG. 1. Energy dependence of (a) the dielectric constant ϵ' and (b) the dynamic conductivity σ' in α -RuCl₃ in the terahertz regime for a series of temperatures between 4.5 and 300 K. These data have been taken in transmission in normal incidence upon heating. All the spectra shown were corrected for multiple scattering effects.

vanishes beyond 200 K. At room temperature, the continuum is completely absent.

Bolens *et al.* [16] calculated the low-frequency optical conductivity of Kitaev materials. They predict a gap, followed by a narrow low-frequency peak of magnetic dipolar character and a broad dominant peak of electric-dipolar nature. As mentioned earlier [28], these theoretical predictions are in qualitative agreement with the low-temperature conductivity shown in Fig. 1(b). However, it is obvious that the weak temperature dependence of the 2.5-meV excitation opposes this interpretation. Focusing on the temperature dependence and assuming that effects of spin fractionalization should vanish at temperatures far beyond the Kitaev exchange (>200 K), it seems natural to identify the low-energy (~2.5 meV) as well as the high-energy response (>12 meV) as being due to phonon excitations. The further weak excitation located close to 6 meV, mentioned above, likely is of phononic nature. Indeed, phonon modes were identified by neutron scattering close to 6 [19] and 7 meV [21]. In clear contrast, the broad continuum centered at around 8.5 meV, which vanishes at high temperatures, indeed could signal fractionalized excitations of the KSL.

A simple and straightforward experimental proof of the microscopic origin of the observed excitations can be realized by a plot of the normalized spectra, which will differentiate between phononic (weak temperature dependence) and magnetic scattering (strong temperature dependence when crossing the magnetic transition). Figure 2 shows the measured transmission at normal incidence at a series of temperatures between 4.5 and 20 K, with all spectra normalized to 7 K, a temperature close to the onset of magnetic order at

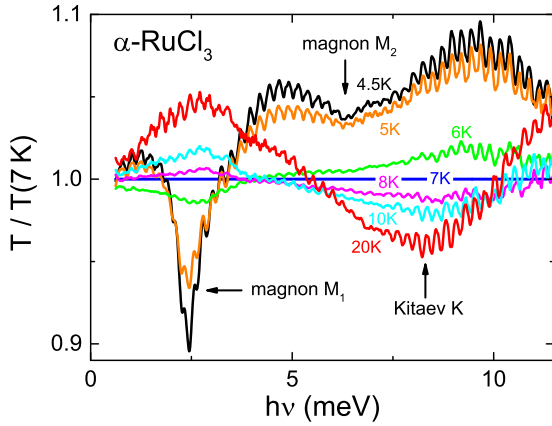


FIG. 2. Energy dependence of the transmission in α -RuCl₃ in the terahertz regime for energies between 1 and 12 meV and temperatures between 4.5 and 20 K. All transmission spectra were normalized to 7 K, a temperature close to the Néel temperature, $T_N \sim 6.5$ K. The arrows M_1 and M_2 indicate magnon excitations in the antiferromagnetic phase. The arrow K signals the evolution of a continuum due to fractionalized excitations of the Kitaev-type spin liquid in the paramagnetic phase.

$T_N = 6.5$ K. In this plot, phononic excitations will be simply ruled out by their weak variation in this narrow temperature regime, and the normalized transmission is dominated by excitations of magnetic origin with significant temperature dependence. A similar plot for a limited energy range and a single temperature was presented in [26].

The normalized transmission spectra of Fig. 2 document how the magnon modes M_1 and M_2 evolve below the onset of magnetic order at 6.5 K. Due to the strong phonon response arising at similar frequencies, these magnetic excitations can hardly be identified in the conductivity spectra of Fig. 1(b). They appear close to 2.5 and 6.5 meV and were identified by inelastic neutron scattering [20,39], but also by previous terahertz experiments [25,26,40,41]. These magnetic excitations accidentally appear at the same energies as the phonon modes discussed above, but they exist only below T_N . The low-frequency excitation M_1 is a one-magnon-response, while the weak and broader high-frequency excitation M_2 probably results from two-magnon scattering. For temperatures above the onset of magnetic order, both excitations become fully suppressed. However, a broad scattering continuum K centered around 8.5 meV evolves in the paramagnetic phase, which reduces the transmission in this energy range considerably. This is the first proof that the broad continuum documented in Fig. 1(b) is not connected to conventional magnetic excitations but results from fractionalized spin excitations of the KSL. The temperature evolution of the transmission certainly excludes an interpretation in terms of spin fluctuations. In the paramagnetic phase, e.g., at 8 K, just above T_N the magnetic modes have completely disappeared, and a continuum evolves at significantly higher energies, documented at 8, 10, and 20 K. The existence of long-lived fractionalized quasiparticles above the magnetic ordering temperature has recently been predicted theoretically [42].

To further discriminate between excitations of phononic and magnetic origin, we trace the temperature dependence of

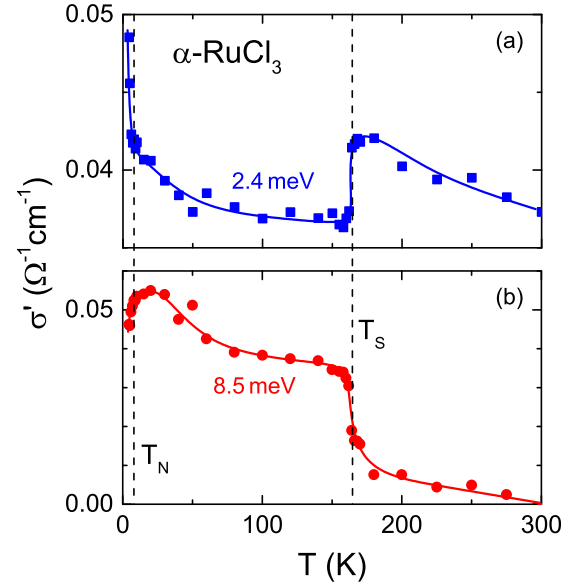


FIG. 3. Temperature dependence of dynamic conductivity σ' in α -RuCl₃ for energies at (a) 2.4 and (b) 8.5 meV, close to the maxima of the low- and high-energy excitations, respectively. The magnetic (T_N) and structural phase transition temperatures (T_S) are indicated by dashed vertical lines. The solid lines are drawn to guide the eye.

the dynamic conductivity σ' . The results as determined close to the peak values of $\sigma'(\omega)$ are documented in Fig. 3. The temperature dependence of the conductivity at these two energies behaves significantly different [please note the different scales in Figs. 3(a) and 3(b)]. On decreasing temperatures, $\sigma'(T)$ at 2.4 meV is only weakly temperature dependent and remains close to $0.04 \Omega^{-1} \text{ cm}^{-1}$. There is a small step-like decrease at the structural phase transition and a rather significant enhancement below the onset of magnetic order. This increase signals the appearance of the magnetic mode at 2.5 meV. Under cooling, the conductivity at 8.5 meV continuously increases from zero conductivity (within experimental uncertainty), exhibits a steplike increase at the structural phase transition, and then further increases down to the onset of magnetic order. In the magnetically ordered state, a decrease of the intensity signals a decrease of the dipolar strength of the continuum: Continuum intensity from fractionalized spin excitations is transferred to magnon modes with well-defined spin components.

In first respect, in the paramagnetic phase the low-frequency mode behaves phononlike while the high-frequency continuum indeed pertains to fractionalized excitations, which vanish at a temperature scale larger than the Kitaev interaction (>200 K). It is worth mentioning two further details: The high-frequency conductivity is significantly reduced in the high-temperature monoclinic phase [Fig. 3(b)]. This signals that Kitaev exchange is more dominant in the low-temperature rhombohedral phase. Indeed, the honeycomb lattice of the ruthenium ions is close to ideal in the low-temperature rhombohedral phase and slightly distorted in the high-temperature monoclinic phase [37]. In addition, a minor fraction of the conductivity is transferred from high to low frequencies at

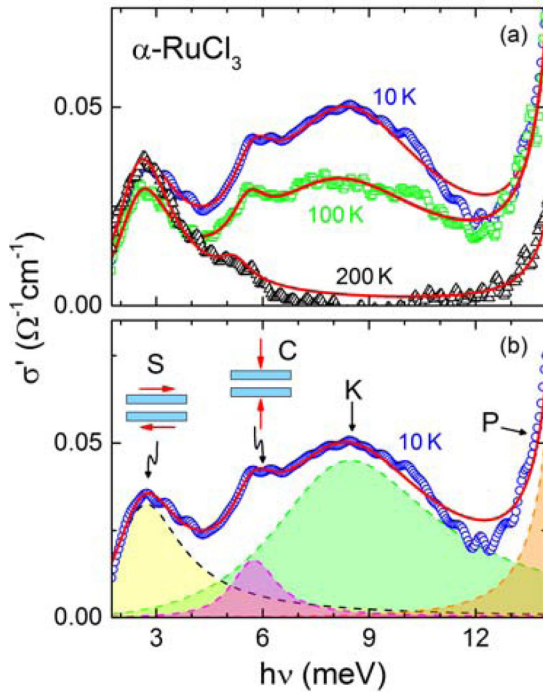


FIG. 4. Analysis of the energy-dependent dynamic conductivity in α - RuCl_3 . (a) Conductivity at a series of temperatures between 10 and 200 K. The solid lines show fits as described in the text. (b) Deconvolution of the conductivity spectrum at 10 K, using three phonon excitations S, C, and P located at 2.5, 6, and 15 meV and a broad continuum K close to 8.5 meV. The phonon modes close to 2.5 and 6 meV represent sliding (S) and compression (C) modes of rigid molecular RuCl_3 layers, as schematically indicated in (b).

the onset of magnetic order. This is compatible with neutron-scattering results [20], which show that in the antiferromagnetic phase the continuum is still finite but is significantly reduced with intensity transfer to magnon modes, indicating localized magnetic moments.

Returning to Fig. 1, we conclude that the low-frequency peak at 2.5 meV and the weak 6-meV excitation represent phononlike excitations, while the high-frequency continuum results from fractionalized spin excitations. The continuum observed in terahertz spectroscopy documents that these magnetic excitations gain electric-dipolar activity. What remains to be clarified is the nature of the phonon modes. In conventional phonon analysis of trihalides, these frequencies are much too low for modes within the molecular RuCl_3 layers. However, similar to a large variety of two-dimensional lattices, where the molecular stacks are bonded by weak vdW interactions, for the trihalides one expects low-frequency modes that characterize shear and layer-breathing motions of rigid molecular layers [34]. For a more quantitative analysis, we have fitted the energy-dependent conductivity of α - RuCl_3 .

Figure 4(a) shows fits of $\sigma'(\omega)$ between 1 and 14 meV for a series of characteristic temperatures. The fits were performed using three excitations in this energy regime and one phonon mode fixed at 15 meV, assuming a Lorentzian line. Figure 4(b) shows the deconvolution of the fit at 10 K into two narrow and

one rather broad component. The narrow modes, which exist up to room temperature, represent phonon modes, while the broad line, which vanishes for temperatures > 200 K, characterizes the response of the KSL due to spin fractionalization. In our interpretation, the broad continuum located at around 8.5 meV signifies the presence of Majorana fermions. The two phonon modes at 2.5 and 6 meV correspond to rigid-plane shear and breathing modes of molecular layers, respectively. Support for the latter notion comes from recent *ab initio* phonon calculations, which predict these excitations close to 3 and 7 meV [43].

In summary, we have detected an absorption continuum in α - RuCl_3 which extends from the lowest measured energies of ~ 2 up to ~ 15 meV. We identify it with fractionalized spin excitations of the KSL ground state, signifying the presence of Majorana-like quasiparticles. As a function of increasing temperature, it continuously decreases and vanishes within experimental uncertainty above 200 K. From the detailed temperature dependence of the continuum intensity [Fig. 3(b)], we conclude that the steplike decrease of its optical weight when entering the high-temperature monoclinic phase signals a significant lowering of the Kitaev exchange in this phase. Indeed, the rhombohedral phase exhibits an almost ideal honeycomb lattice [37]. That, indeed, Kitaev interactions in the monoclinic phase are reduced compared to competing Heisenberg and off-diagonal exchange follows from the fact that the magnetic ordering temperatures of monoclinic crystals are enhanced by a factor of 2 [36].

Our results compare well with those from neutron scattering. Banerjee *et al.* [20] identify a continuum with a maximum close to 5 meV extending up to 15 meV. In the magnetically ordered state, the continuum is reduced and its intensity is transferred to magnon excitations, similar to our findings. Do *et al.* [21] identify a continuum again extending up to 15 meV, which vanishes roughly at 150 K. In neutron scattering there are no detailed reports of scattering intensities when passing the structural phase transition. In Raman experiments the continuum extends to significantly higher frequencies (~ 30 meV) and survives almost up to room temperature [14,23,24]. Fractionalization of spin degrees of freedom in α - RuCl_3 was also derived from heat-capacity experiments [21,43]. Widmann *et al.*, utilizing a phonon correction based on *ab initio* calculations, identified a heat-capacity anomaly close to 70 K extending up to 150 K [43]. These temperatures are in good agreement with the energies derived from the scattering continuum reported in this terahertz study.

Finally, we reported on the observation of sliding and breathing modes of the molecular layers, a characteristic feature of 2D layered compounds. Similar modes have been identified in graphene and in di-chalcogenides. In α - RuCl_3 these modes are located close to 2.5 and 6 meV. Strictly speaking, these are acoustic modes, and according to *ab initio* phonon calculations [43], these values correspond to eigenfrequencies at the zone boundary along the crystallographic c direction. In terahertz spectroscopy, these modes probably can be observed via disorder of the stacking or via backfolding of zone-boundary intensities due to the ABC stacking sequences of the rhombohedral phase. It is worth mentioning that recent theories [44,45] stress the importance of the coupling of phonons and the quantum spin liquid to

observe a quantized thermal Hall effect [31]. It remains to be proven if the reported rigid-plane motions of our work play a specifically important role for the quantized thermal Hall effect.

Concluding, in this Rapid Communication we provide a detailed analysis of the temperature-dependent terahertz spectra in α -RuCl₃. We find convincing evidence for rigid-layer modes of the molecular units and for a continuum due to

Majorana fermions, characteristic excitations of the Kitaev-type spin-liquid state.

We thank H. M. Rønnow for bringing the physics of sliding modes in two-dimensional systems to our attention. This work has been partly supported by the Deutsche Forschungsgemeinschaft (DFG) via the Transregional Collaborative Research Center TRR 80.

-
- [1] R. M. Lutchyn, E. P. A. M. Bakkers, L. P. Kouwenhoven, P. Krogstrup, C. M. Marcus, and Y. Oreg, Majorana zero modes in superconductor–semiconductor heterostructures, *Nat. Rev. Mater.* **3**, 52 (2018).
- [2] S. Nadj-Perge, I. K. Drozdov, J. Li, H. Chen, S. Jeon, J. Seo, A. H. MacDonald, B. A. Bernevig, and A. Yazdani, Observation of Majorana fermions in ferromagnetic atomic chains on a superconductor, *Science* **346**, 602 (2014).
- [3] D. Wang, L. Kong, P. Fan, H. Chen, S. Zhu, W. Liu, L. Cao, Y. Sun, S. Du, J. Schneeloch, R. Zhong, G. Gu, L. Fu, H. Ding, and H.-J. Gao, Evidence for Majorana bound states in an iron-based superconductor, *Science* **362**, 333 (2018).
- [4] J. Alicea, New directions in the pursuit of Majorana fermions in solid state systems, *Rep. Prog. Phys.* **75**, 076501 (2012).
- [5] A. Kitaev, Anyons in an exactly solved model and beyond, *Ann. Phys.* **321**, 2 (2006).
- [6] S. M. Winter, A. A. Tsirlin, M. Daghofer, J. van den Brink, Y. Singh, P. Gegenwart, and R. Valenti, Models and materials for generalized Kitaev magnetism, *J. Phys.: Condens. Matter* **29**, 493002 (2017).
- [7] M. Hermanns, I. Kimchi, and J. Knolle, Physics of the Kitaev model: Fractionalization, dynamical correlations, and material connections, *Annu. Rev. Condens. Matter Phys.* **9**, 17 (2018).
- [8] J. Knolle, D. L. Kovrizhin, J. T. Chalker, and R. Moessner, Dynamics of a Two-Dimensional Quantum Spin Liquid: Signatures of Emergent Majorana Fermions and Fluxes, *Phys. Rev. Lett.* **112**, 207203 (2014).
- [9] J. Knolle, D. L. Kovrizhin, J. T. Chalker, and R. Moessner, Dynamics of fractionalization in quantum spin liquids, *Phys. Rev. B* **92**, 115127 (2015).
- [10] X.-Y. Song, Y.-Z. You, and L. Balents, Low Energy Spin Dynamics of the Honeycomb Spin Liquid Beyond the Kitaev Liquid, *Phys. Rev. Lett.* **117**, 037209 (2016).
- [11] A. M. Samarakoon, G. Wachtel, Y. Yamaji, D. A. Tennant, C. D. Batista, and Y.-B. Kim, Classical and quantum spin dynamics of the honeycomb model, *Phys. Rev. B* **98**, 045121 (2018).
- [12] T. Suzuki and S. Suga, Effective model with strong Kitaev interactions for α -RuCl₃, *Phys. Rev. B* **97**, 134424 (2018).
- [13] J. Knolle, G.-W. Chern, D. L. Kovrizhin, R. Moessner, and N. B. Perkins, Raman Scattering Signatures of Kitaev Spin Liquids in A₂IrO₃ Iridates with A = Na or Li, *Phys. Rev. Lett.* **113**, 187201 (2014).
- [14] J. Nasu, J. Knolle, D. L. Kovrizhin, Y. Motome, and R. Moessner, Fermionic response from fractionalization in an insulating two-dimensional magnet, *Nat. Phys.* **12**, 912 (2016).
- [15] J. Nasu, M. Udagawa, and Y. Motome, Thermal fractionalization of quantum spins in a Kitaev model: Temperature-linear specific heat and coherent transport of Majorana fermions, *Phys. Rev. B* **92**, 115122 (2015).
- [16] A. Bolens, H. Katsura, M. Ogata, and S. Miyashita, Mechanism for subgap optical conductivity in honeycomb Kitaev materials, *Phys. Rev. B* **97**, 161108(R) (2018).
- [17] T. Suzuki and S. Suga, Field dependence of THz spectra of effective models for α -RuCl₃, *AIP Adv.* **8**, 101414 (2018).
- [18] G. B. Halász, B. Perreault, and N. B. Perkins, Probing Spinon Nodal Structures in Three-Dimensional Kitaev Spin Liquids, *Phys. Rev. Lett.* **119**, 097202 (2017).
- [19] A. Banerjee, C. A. Bridges, J.-Q. Yan, A. A. Aczel, L. Li, M. B. Stone, G. E. Granroth, M. D. Lumsden, Y. Yiu, J. Knolle, S. Bhattacharjee, D. L. Kovrizhin, R. Moessner, D. A. Tennant, D. G. Mandrus, and S. E. Nagler, Proximate Kitaev quantum spin liquid behaviour in a honeycomb magnet, *Nat. Mater.* **15**, 733 (2016).
- [20] A. Banerjee, J. Yan, J. Knolle, C. A. Bridges, M. B. Stone, M. D. Lumsden, D. G. Mandrus, D. A. Tennant, R. Moessner, and S. E. Nagler, Neutron scattering in the proximate quantum spin liquid α -RuCl₃, *Science* **356**, 1055 (2017).
- [21] S.-H. Do, S.-Y. Park, J. Yoshitake, J. Nasu, Y. Motome, Y. S. Kwon, D. T. Adroja, D. J. Voneshen, K. Kim, T.-H. Jang, J.-H. Park, K.-Y. Choi, and S. Ji, Majorana fermions in the Kitaev quantum spin system α -RuCl₃, *Nat. Phys.* **13**, 1079 (2017).
- [22] A. Banerjee, P. Lampen-Kelley, J. Knolle, C. Balz, A. A. Aczel, B. Winn, Y. Liu, P. Pajeroski, J. Yan, C. A. Bridges, A. T. Savici, B. C. Chakoumakos, M. D. Lumsden, D. A. Tennant, R. Moessner, D. G. Mandrus, and S. E. Nagler, Excitations in the field-induced quantum spin liquid state of α -RuCl₃, *npj Quantum Mater.* **3**, 8 (2018).
- [23] L. J. Sandilands, Y. Tian, K. W. Plumb, Y.-J. Kim, and K. S. Burch, Scattering Continuum and Possible Fractionalized Excitations in α -RuCl₃, *Phys. Rev. Lett.* **114**, 147201 (2015).
- [24] A. Glamazda, P. Lemmens, S.-H. Do, Y. S. Kwon, and K.-Y. Choi, Relation between Kitaev magnetism and structure in α -RuCl₃, *Phys. Rev. B* **95**, 174429 (2017).
- [25] A. Little, L. Wu, P. Lampen-Kelly, A. Banerjee, S. Patankar, D. Rees, C. A. Bridges, J.-Q. Yan, D. Mandrus, S. E. Nagler, and J. Orenstein, Antiferromagnetic Resonance and Terahertz Continuum in α -RuCl₃, *Phys. Rev. Lett.* **119**, 227201 (2017).
- [26] Zhe Wang, S. Reschke, D. Hüvonen, S.-H. Do, K.-Y. Choi, M. Gensch, U. Nagel, T. Room, and A. Loidl, Magnetic Excitations and Continuum of a Possibly Field-Induced Quantum Spin Liquid in α -RuCl₃, *Phys. Rev. Lett.* **119**, 227202 (2017).
- [27] S. Reschke, F. Mayr, Zhe Wang, Seung-Hwan Do, K.-Y. Choi, and A. Loidl, Electronic and phonon excitations in α -RuCl₃, *Phys. Rev. B* **96**, 165120 (2017).

- [28] S. Reschke, F. Mayr, S. Widmann, H.-A. Krug von Nidda, V. Tsurkan, M. V. Eremin, S.-H. Do, K.-Y. Choi, Zhe Wang, and A. Loidl, Sub-gap optical response in the Kitaev spin-liquid candidate α -RuCl₃, *J. Phys.: Condens. Matter* **30**, 475604 (2018).
- [29] S. M. Winter, K. Riedl, P. A. Maksimov, A. L. Chernyshev, A. Honecker, and R. Valenti, Breakdown of magnons in a strongly spin-orbital coupled magnet, *Nat. Commun.* **8**, 1152 (2017).
- [30] S. M. Winter, K. Riedl, D. Kaib, R. Coldea, and R. Valenti, Probing α -RuCl₃ Beyond Magnetic Order: Effects of Temperature and Magnetic Field, *Phys. Rev. Lett.* **120**, 077203 (2018).
- [31] Y. Kasahara, T. Ohnishi, Y. Mizukami, O. Tanaka, S. Ma, K. Sugii, N. Kurita, H. Tanaka, J. Nasu, Y. Motome, T. Shibauchi, and Y. Matsuda, Majorana quantization and half-integer thermal quantum Hall effect in a Kitaev spin liquid, *Nature (London)* **559**, 227 (2018).
- [32] P. H. Tan, W. P. Han, W. J. Zhao, Z. H. Wu, K. Chang, H. Wang, Y. F. Wang, N. Bonini, N. Marzari, N. Pugno, G. Savini, A. Lombardo, and A. C. Ferrari, The shear mode of multilayer graphene, *Nat. Mater.* **11**, 294 (2012).
- [33] C. Cong and T. Yu, Enhanced ultra-low-frequency interlayer shear modes in folded graphene layers, *Nat. Commun.* **5**, 4709 (2014).
- [34] X. Zhang, W. P. Han, J. B. Wu, S. Milana, Y. Lu, Q. Q. Li, A. C. Ferrari, and P. H. Tan, Raman spectroscopy of shear and layer breathing modes in multilayer MoS₂, *Phys. Rev. B* **87**, 115413 (2013).
- [35] K. H. Michel and B. Verberck, Theory of rigid-plane phonon modes in layered crystals, *Phys. Rev. B* **85**, 094303 (2012).
- [36] R. D. Johnson, S. C. Williams, A. A. Haghighirad, J. Singleton, V. Zapf, P. Manuel, I. I. Mazin, Y. Li, H. O. Jeschke, R. Valentí, and R. Coldea, Monoclinic crystal structure of α -RuCl₃ and the zigzag antiferromagnetic ground state, *Phys. Rev. B* **92**, 235119 (2015).
- [37] S.-Y. Park, S.-H. Do, K.-Y. Choi, D. Jang, T.-H. Jang, J. Schefer, C.-M. Wu, J. S. Gardner, M. S. Park, J.-H. Park, and S. Ji, Emergence of the isotropic Kitaev honeycomb lattice with two-dimensional Ising universality in α -RuCl₃, [arXiv:1609.05690](https://arxiv.org/abs/1609.05690).
- [38] Y. Hasegawa, T. Aoyama, K. Sasaki, Y. Ikemoto, T. Moriwaki, T. Shirakura, R. Saito, Y. Imai, and K. Ohgushi, Two-phonon absorption spectra in the layered honeycomb compound α -RuCl₃, *J. Phys. Soc. Japan* **86**, 123709 (2017).
- [39] K. Ran, J. Wang, W. Wang, Z.-Y. Dong, X. Ren, S. Bao, S. Li, Z. Ma, Y. Gan, Y. Zhang, J. T. Park, G. Deng, S. Danilkin, S.-Li. Yu, J.-X. Li, and J. Wen, Spin-Wave Excitations Evidencing the Kitaev Interaction in Single Crystalline α -RuCl₃, *Phys. Rev. Lett.* **118**, 107203 (2017).
- [40] L. Y. Shi, Y. Q. Liu, T. Lin, M. Y. Zhang, S. J. Zhang, L. Wang, Y. G. Shi, T. Dong, and N. L. Wang, Field-induced magnon excitation and in-gap absorption in the Kitaev candidate RuCl₃, *Phys. Rev. B* **98**, 094414 (2018).
- [41] L. Wu, A. Little, E. E. Aldape, D. Rees, E. Thewalt, P. Lampen-Kelley, A. Banerjee, C. A. Bridges, J.-Q. Yan, D. Boone, S. Patankar, D. Goldhaber-Gordon, D. Mandrus, S. E. Nagler, E. Altman, and J. Orenstein, Field evolution of magnons in α -RuCl₃ by high-resolution polarized terahertz spectroscopy, *Phys. Rev. B* **98**, 094425 (2018).
- [42] I. Rousochatzakis, S. Kourtis, J. Knolle, R. Moessner, and N. B. Perkins, Quantum spin liquid at finite temperature: Proximate dynamics and persistent typicality, *Phys. Rev. B* **100**, 045117 (2019).
- [43] S. Widmann, V. Tsurkan, D. A. Prishchenko, V. G. Mazurenko, A. A. Tsirlin, and A. Loidl, Thermodynamic evidence of fractionalized excitations in α -RuCl₃, *Phys. Rev. B* **99**, 094415 (2019).
- [44] M. Ye, G. B. Halász, L. Savary, and L. Balents, Quantization of the Thermal Hall Conductivity at Small Angles, *Phys. Rev. Lett.* **121**, 147201 (2018).
- [45] Y. Vinkler-Aviv and A. Rosch, Approximately Quantized Thermal Hall Effect of Chiral Liquids Coupled to Phonons, *Phys. Rev. X* **8**, 031032 (2018).