

Optical phonons, spin correlations, and spin-phonon coupling in the frustrated pyrochlore magnets CdCr_2O_4 and ZnCr_2O_4

Christian Kant, Joachim Deisenhofer, T. Rudolf, Franz Mayr, Florian Schrettle, Alois Loidl, V. Gnezdilov, D. Wulferding, P. Lemmens, Vladimir Tsurkan

Angaben zur Veröffentlichung / Publication details:

Kant, Christian, Joachim Deisenhofer, T. Rudolf, Franz Mayr, Florian Schrettle, Alois Loidl, V. Gnezdilov, D. Wulferding, P. Lemmens, and Vladimir Tsurkan. 2009. "Optical phonons, spin correlations, and spin-phonon coupling in the frustrated pyrochlore magnets CdCr_2O_4 and ZnCr_2O_4 ." *Physical Review B* 80 (21): 214417. <https://doi.org/10.1103/physrevb.80.214417>.



Optical phonons, spin correlations, and spin-phonon coupling in the frustrated pyrochlore magnets CdCr_2O_4 and ZnCr_2O_4

Ch. Kant, J. Deisenhofer,* T. Rudolf, F. Mayr, F. Schrettle, and A. Loidl

Experimental Physics V, Center for Electronic Correlations and Magnetism, University of Augsburg, D-86135 Augsburg, Germany

V. Gnezdilov

B.I. Verkin Institute for Low Temperature Physics and Engineering, NASU, UA-61103 Kharkov, Ukraine

D. Wulferding and P. Lemmens

Institute for Condensed Matter Physics, Technical University of Braunschweig, D-38106 Braunschweig, Germany

V. Tsurkan

*Experimental Physics V, Center for Electronic Correlations and Magnetism, University of Augsburg, D-86135 Augsburg, Germany**and Institute of Applied Physics, Academy of Sciences of Moldova, MD-2028 Chişinău, Republic of Moldova*

(Received 9 June 2009; revised manuscript received 11 November 2009; published 17 December 2009)

We report on infrared, Raman, magnetic susceptibility, and specific-heat measurements on CdCr_2O_4 and ZnCr_2O_4 single crystals. We estimate the nearest-neighbor and next-nearest-neighbor exchange constants from the magnetic susceptibility and extract the spin-spin correlation functions obtained from the magnetic susceptibility and the magnetic contribution to the specific heat. By comparing with the frequency shift of the infrared optical phonons above T_N , we derive estimates for the spin-phonon coupling constants in these systems. The observation of phonon modes which are both Raman and infrared active suggest the loss of inversion symmetry below the Néel temperature in CdCr_2O_4 in agreement with theoretical predictions by Chern *et al.* [Phys. Rev. B **74**, 060405(R) (2006)]. In ZnCr_2O_4 several new modes appear below T_N but no phonon modes could be detected which are both Raman and infrared active.

DOI: [10.1103/PhysRevB.80.214417](https://doi.org/10.1103/PhysRevB.80.214417)

PACS number(s): 75.40.-s, 75.50.Ee, 78.30.-j

I. INTRODUCTION

The antiferromagnetic (AFM) oxide-spinel systems ACr_2O_4 ($A = \text{Cd}, \text{Mg}, \text{Zn}$) are prototypical examples for highly frustrated magnets,¹ where the magnetic Cr^{3+} ions with spin $S=3/2$ reside on the vertices of corner-sharing tetrahedra forming a pyrochlore lattice as shown in Fig. 1. An antiferromagnetic nearest-neighbor (nn) Heisenberg exchange on the pyrochlore lattice leads to inherent frustration and a multiply degenerate magnetic ground state. In real systems this degeneracy will be released at finite temperatures by coupling to other degrees of freedom and, indeed, the ACr_2O_4 systems ($A = \text{Cd}, \text{Mg}, \text{Zn}$) undergo a magnetostructural transition with antiferromagnetic order at 7.8, 12.7, and 12.5 K,^{2,3} although their Curie-Weiss temperatures (Θ_{CW}) are -71, -346, and -390 K, respectively.^{4,5} The theory of the magnetoelastic coupling and the magnetostructural transition for these systems was worked out by Tchernyshyov and co-workers^{6,7} in terms of a spin-driven Jahn-Teller effect.

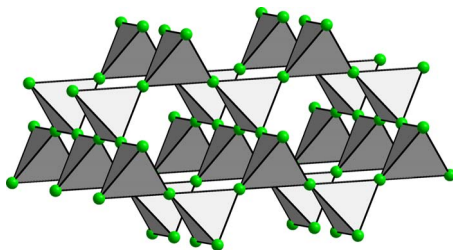


FIG. 1. (Color online) The pyrochlore structure formed by the magnetic Cr ions on the B site in ACr_2X_4 ($X = \text{S}, \text{O}$) spinels.

The structural and magnetic ground-state properties in the Cr spinels are strongly intertwined and, hence, the assignment of the correct symmetry groups is a complex task which has not been accomplished yet. The high-temperature cubic structure of spinels has space group $Fd\bar{3}m$, which is often reduced to tetragonal with space group $I4_1/amd$ (Refs. 8–11) when undergoing a structural or magnetostructural transition. Such a uniform tetragonal distortion was reported for CdCr_2O_4 .^{12,13} However, it was suggested from a theoretical analysis of the observed spiral spin structure that the lattice distortion should be chiral with space group $I4_122$, leading to the loss of inversion symmetry (IS).^{14,15} The corresponding distortion in ZnCr_2O_4 has been mostly described in terms of the tetragonal $I\bar{4}m2$ space group also lacking inversion symmetry^{3,13,16} but orthorhombic distortions have also been evoked leading to $F222$ symmetry¹⁷ (no IS) or $Fddd$ symmetry (conserving IS).¹⁸

The number of infrared (IR) and Raman-active optical phonons strongly depends on the exact symmetry and occupied Wyckoff positions of the lattice. If inversion symmetry is present IR and Raman modes are mutually exclusive. Hence, the appearance of resonances which are IR and Raman active is a secure indication for the loss of inversion symmetry.¹⁹ While we are not aware of any low-temperature Raman studies of these systems, the magnetoelastic coupling and the phase transitions clearly show up in the far-infrared optical spectra as shifts or splittings of the phonon modes.^{4,5,20,21} For ZnCr_2O_4 the spin-phonon coupling was estimated via two different approaches: The first one is a direct evaluation of the phonon splitting in the magnetically ordered phase using the spin-driven Jahn-Teller effect and

the second involves a comparison of the frequency shift of the phonons with the spin-spin correlation function derived from the magnetic contribution to the specific heat.⁵ The first approach also has been applied to CdCr₂O₄ already.²⁰

In this study we investigate the low-temperature Raman and IR optical response for both systems and analyze in detail the approach to derive the spin-phonon coupling by considering both, the spin-spin correlation function derived from the magnetic contribution to the specific heat, and the one obtained directly from the paramagnetic susceptibility. The outline of the paper is as follows: In Sec. III A we describe the susceptibilities of CdCr₂O₄ and ZnCr₂O₄ by a quantum tetrahedral mean-field model²² and obtain the nn and next-nearest-neighbor (nnn) exchange couplings in these systems. Then we extract the magnetic part of the specific heat in Sec. III B. After discussing the phonon excitations observed by IR and Raman measurements with regard to the proposed lattice symmetries in Sec. III C, we estimate in Sec. III D the spin-phonon coupling in both compounds by comparing the frequency shift of the IR-active phonons to the spin-spin correlations obtained from the susceptibility and the specific-heat data.

II. EXPERIMENTAL DETAILS

High-quality platelike single crystals of CdCr₂O₄ up to 7 mm in diameter were obtained by spontaneous crystallization from Bi₂O₃-V₂O₅ flux. ZnCr₂O₄ single crystals were grown by a chemical transport technique using Cl as a transport agent at temperatures between 950 and 900 °C. The length of the octahedra edges extends up to 6 mm. The optical measurements were performed on as-grown (111) mirrorlike surfaces. X-ray powder-diffraction patterns of crashed single crystals did not reveal any impurity phases and correspond to stoichiometric polycrystals. The magnetic-susceptibility measurements were carried out in a commercial superconducting quantum interference device magnetometer (Quantum Design MPMS-5). The heat capacity was measured in a Quantum Design physical properties measurement system for temperatures from 2 K < T < 300 K. The IR reflectivity was determined using a Bruker Fourier-transform IR spectrometer IFS 113v/S, which was equipped with a He-bath cryostat and a He-flow cryostat (5 K < T < 300 K). Raman-scattering experiments were carried out in a quasibackscattering geometry. An Ar/Kr ion laser was used for excitation at 514.5 nm (2.41 eV). The laser output power was kept below 3 mW on a focus of approximately 50 μ m of diameter to protect the sample from possible heating effects. The scattered light was collected and dispersed by a triple monochromator DILOR XY on a liquid-nitrogen-cooled charge coupled device detector in parallel and crossed polarization configurations. Temperature dependencies were obtained in a variable-temperature closed cycle cryostat (Oxford/Cryomech Optistat, RT-2.8 K).

The measured reflectivity spectra are analyzed by modeling the dielectric function and fitting it to the experimental data using the program RefFIT.²³ We utilize a three-parameter model for each phonon mode which is a sum over Lorentzian oscillators,

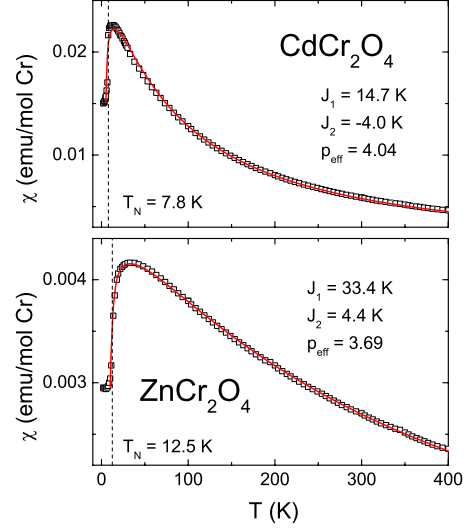


FIG. 2. (Color online) Temperature dependence of the magnetic susceptibility of CdCr₂O₄ and ZnCr₂O₄ in a field of $\mu_0 H = 1$ T and $\mu_0 H = 0.1$ T, respectively. The solid lines are fits to the experimental data according to Eq. (2).

$$\varepsilon(\omega) = \sum_j \frac{\Omega_j}{\omega_{0j}^2 - \omega^2 - i\gamma_j\omega} + \varepsilon_\infty. \quad (1)$$

Here, Ω_j denotes the plasma frequency, ω_{0j} the eigenfrequency, and γ_j the damping of mode j , respectively. ε_∞ is the dielectric constant beyond the phonons in the mid-infrared regime and accounts for high-frequency electronic polarizations. It is treated as a free parameter in the fitting procedure. The optical phonons in CdCr₂O₄ and ZnCr₂O₄ were measured from 5 to 300 K in the far-infrared and additional measurements were performed in the mid-infrared up to 8000 cm^{-1} for CdCr₂O₄ to determine the value of $\varepsilon_\infty = 4.6$ with high accuracy and to enable a Kramers-Kronig transformation. Therefore a constant extrapolation of the measured reflectivity was assumed at low frequencies and a smooth ω^{-h} behavior at the upper limit of the recorded spectrum.

III. EXPERIMENTAL RESULTS AND DISCUSSION

A. Magnetic susceptibility

Figure 2 shows the magnetic susceptibility of CdCr₂O₄ and ZnCr₂O₄ as a function of temperature. On cooling both curves exhibit a broad maximum before magnetic order sets in at the indicated Néel temperatures. Note that the susceptibility below T_N was shown to depend strongly on the applied magnetic field.²⁴ Our results are in good agreement with previous studies.^{2,25}

García-Adeva and Huber²² derived a quantum tetrahedral mean-field (TMF) model to calculate the magnetic susceptibility of pyrochlore lattices. We use this model in the form

$$\chi_{\text{TMF}}(T) = \frac{N_A g^2 \mu_B^2}{k_B} \frac{a \chi_{\text{tet}}(T)}{1 + (3J_1 + 12J_2) \chi_{\text{tet}}(T)}, \quad (2)$$

which describes the susceptibility per mole of magnetic ions. Here, N_A is the Avogadro constant, $g = 1.97$ the g factor,²⁵ μ_B

the Bohr magneton, and J_1 and J_2 are the nn and nnn exchange constants (in units of k_B), respectively. χ_{tet} can be calculated through

$$\chi_{tet}(T) = \frac{1}{12T} \frac{\sum_S g(S)S(S+1)(2S+1)e^{-J_1S(S+1)/2T}}{\sum_S g(S)(2S+1)e^{-J_1S(S+1)/2T}}. \quad (3)$$

The sum runs over the total spin values $S = (0, 1, 2, 3, 4, 5, 6)$ of the Cr tetrahedron and $g(S) = (4, 9, 11, 10, 6, 3, 1)$ are the corresponding degeneracies.²² The scaling factor a is related to the effective number of Bohr magnetons by $a = p_{eff}^2/[g^2s(s+1)]$.

The solid lines in Fig. 2 were obtained by fitting Eq. (2) to the experimental data. This procedure yielded $J_1 = 14.7$ K, $J_2 = -4.0$ K, and $p_{eff} = 4.04$ for CdCr_2O_4 and $J_1 = 33.4$ K, $J_2 = 4.4$ K, and $p_{eff} = 3.69$ for ZnCr_2O_4 . In literature values for p_{eff} range from 3.98 to $4.02\mu_B$ for the Cd spinel^{2,4} and between 3.85 and $3.94\mu_B$ for the Zn compound.^{4,26} The spin only value for a Cr^{3+} ion of $3.87\mu_B$ corresponds well to the reported data and to our findings. The exchange coupling constants were estimated from the Curie-Weiss temperatures to be $J_1 = 12$ K (Ref. 12) for the Cd and $J_1 = 35-45$ K (Ref. 25) for the Zn compound which is also in good agreement with our results. In Ref. 27 the TMF model was already applied to ZnCr_2O_4 and yielded $J_1 = 39.4$ K and $J_2 = 1.76$ K. Evidently, J_1 is about one order of magnitude stronger than J_2 in ZnCr_2O_4 while in CdCr_2O_4 the antiferromagnetic J_1 is already weakened and the nnn exchange J_2 is ferromagnetic. This is in agreement with the reduction in the direct exchange between nn Cr ions with an increase in the lattice parameter when substituting Zn by Cd.⁴ We also attempted to analyze our susceptibility data with an alternative model proposed by García-Adeva and Huber,²⁷⁻³⁰ which, however, did not allow to fit the data satisfactorily.³¹

B. Specific heat

In Fig. 3 we show the temperature dependencies of the specific heat divided by temperature C_p/T for CdCr_2O_4 , ZnCr_2O_4 , and the nonmagnetic compounds CdGa_2O_4 , ZnGa_2O_4 , and ZnAl_2O_4 . The magnetostructural transitions of CdCr_2O_4 at $T_N = 7.8$ K and ZnCr_2O_4 at $T_N = 12.5$ K are clearly visible as very sharp peaks, indicating first-order phase transformations. For ZnCr_2O_4 our data are comparable to the ones published in Ref. 25. However a close inspection of both data sets reveal a maximum value in C_p/T of 4.8 and 4.4 J/(mol K²), respectively, which probably can be attributed to different sample-preparation routes and slightly varied measurement conditions.

In order to extract the magnetic contribution to the specific heat we followed the procedure used in Ref. 25 for ZnCr_2O_4 . We prepared the nonmagnetic reference compounds CdGa_2O_4 and ZnGa_2O_4 to subtract the lattice contribution to the specific heat directly. The obtained specific-heat data are also displayed in Fig. 3. Obviously, the data for the reference compounds do not allow for a direct subtraction and it is not easy to explain the discrepancies for ZnGa_2O_4 in comparison to Ref. 25. Therefore, we chose an alternative approach to extract the magnetic contribution. As a nonmag-

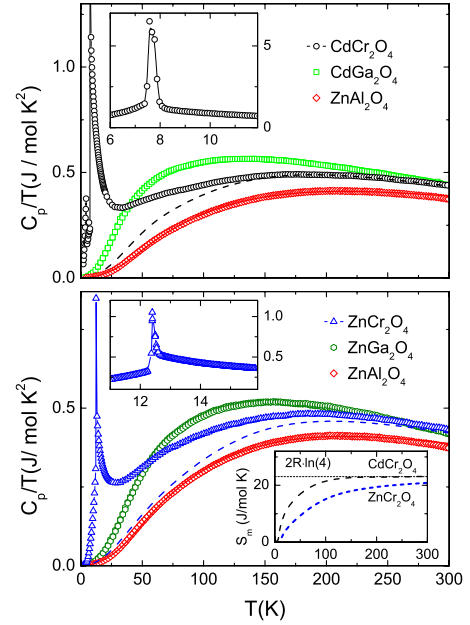


FIG. 3. (Color online) Upper frame: temperature dependence of C_p/T of CdCr_2O_4 (open circles), CdGa_2O_4 (open squares), and the reference compound ZnAl_2O_4 (open rhombi) together with the fitted lattice contributions C_{lat}^{fit}/T of the specific heat (lines) as described in the text. Lower frame: C_p/T of ZnCr_2O_4 vs temperature (open triangles) together with a fit of the phonon contribution (dashed line). Also shown are ZnGa_2O_4 (open hexagons) and the reference compound. Upper insets: C_p/T as a function of temperature around the AFM transition. Lower inset: entropy of the magnetic contribution $C_p - C_{lat}^{fit}$ of the specific heat for both Cr spinels.

netic reference we prepared ZnAl_2O_4 and fitted the specific-heat data by modeling the phonon density of state (PDOS). We were able to describe the experimentally obtained values with one isotropic Debye—(D) and three isotropic Einstein-type ($E_{1,2,3}$) contributions satisfactorily (compare rhombi and solid line in Fig. 3) with the corresponding Debye and the Einstein temperatures θ_D and $\theta_{E_{1,2,3}}$, respectively. To comply with the 21 degrees of freedoms per formula unit, we fixed the ratio between the Debye and Einstein terms to $D:E_1:E_2:E_3 = 1:1:3:2$. The parameters obtained by a best fit are $\theta_D = 330$ K, $\theta_{E_1} = 350$ K, $\theta_{E_2} = 640$ K, and $\theta_{E_3} = 1080$ K for ZnAl_2O_4 . The derived Einstein temperatures are in good agreement with maxima in the PDOS reported by neutron-diffraction studies.³²

Turning now to the frustrated systems ZnCr_2O_4 and CdCr_2O_4 we modeled the phonon contribution by scaling the Debye temperature of our reference with $\sqrt{m_{ZAO}/m_{ACO}}$ as it is expected for the phonon dispersion of acoustic modes close to the center of the first Brillouin zone. m_{ZAO} denotes the molar mass of the reference and m_{ACO} of the Cr spinel, respectively. The Einstein terms were adapted in such a way that the obtained magnetic contribution $C_m = C_p - C_{lat}^{fit}$ results in a magnetic entropy (see lower inset of Fig. 3)

$$S_m(T) = \int_0^T \frac{C_m}{\vartheta} d\vartheta, \quad (4)$$

which increases continuously with temperature and approaches the expected high-temperature limit value of

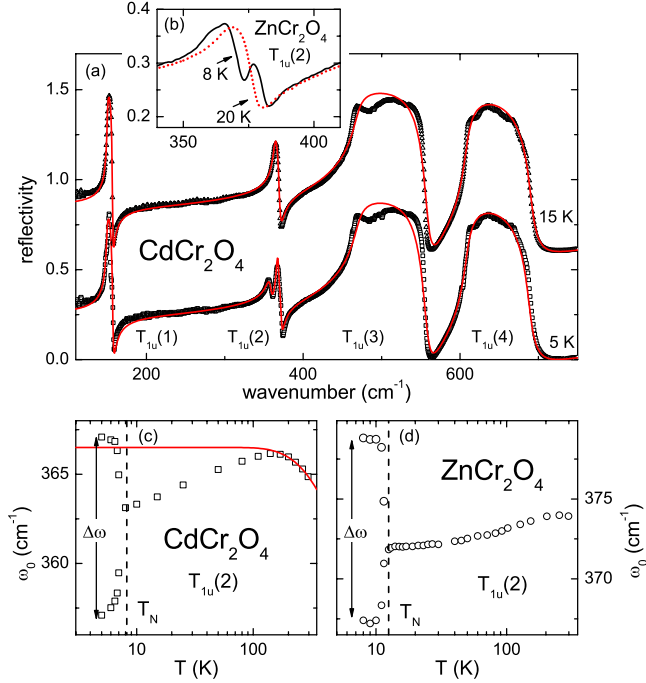


FIG. 4. (Color online) (a) Reflectivity spectra of CdCr₂O₄ in the paramagnetic state at 15 K (shifted for clarity) and at 5 K, below T_N . The $T_{1u}(2)$ mode is clearly split at 5 K (Ref. 4). (b) Splitting of the $T_{1u}(2)$ phonon in ZnCr₂O₄. [(c) and (d)] Temperature dependence of the phonon eigenfrequencies of the $T_{1u}(2)$ modes revealing the splitting at T_N in CdCr₂O₄ and ZnCr₂O₄, respectively.

$2R \ln(2S+1)$ for a spin system with $S=3/2$. For CdCr₂O₄ this procedure yielded $\theta_D=265$ K, $\theta_{E_1}=300$ K, $\theta_{E_2}=570$ K, and $\theta_{E_3}=820$ K. In ZnCr₂O₄ we obtained $\theta_D=290$ K, $\theta_{E_1}=360$ K, $\theta_{E_2}=600$ K, and $\theta_{E_3}=860$ K.

C. Infrared and Raman modes

1. Infrared spectroscopy

Figure 4(a) shows reflectivity spectra for CdCr₂O₄ at 5 and 15 K, below and above the magnetostructural transition at $T_N=7.8$ K. The fits using Eq. (1) are shown as solid lines in the same plot. The four IR-active phonon modes $T_{1u}(j)$ (with $j=1,2,3,4$) observed above T_N (150, 365, 465, and 605 cm⁻¹ at room temperature) were labeled according to the triply degenerate modes expected from the irreducible representations in the cubic $Fd\bar{3}m$ (227) symmetry,³³

$$\begin{aligned} \Gamma &= 4T_{1u} \quad (\text{IR active}) \\ &+ A_{1g} + E_{1g} + 3T_{2g} \quad (\text{Raman active}) \\ &+ 2A_{2u} + 2E_u + T_{1g} + 2T_{2u} \quad (\text{silent}). \end{aligned}$$

For ZnCr₂O₄ the reflectivity spectra exhibit a qualitatively similar shape and have been published earlier.⁵ The four reststrahlen bands are located at room temperature at 186, 373, 509, and 620 cm⁻¹, respectively. Therefore, we focus on the mode $T_{1u}(2)$ at 8 and 20 K, below and above the Néel temperature $T_N=12.5$ K in Fig. 4(b). As previously

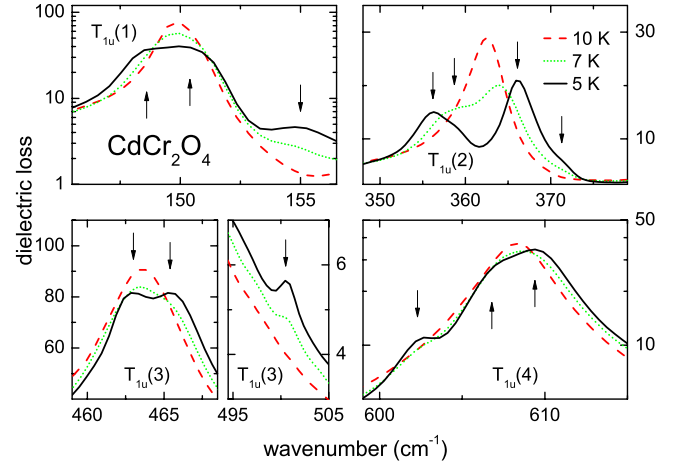


FIG. 5. (Color online) Dielectric loss of the phonons in CdCr₂O₄. Below T_N one can clearly see the splitting of the cubic modes and the appearance of new modes (indicated by arrows).

reported,^{4,5,20} this mode softens upon cooling and splits for both compounds when entering the magnetically ordered phase [see Figs. 4(c) and 4(d)]. The solid line in Fig. 4(c) is a fit of the increase in the phonon frequency with decreasing temperature using

$$\omega_j(T) = \omega_{0j} \left[1 - \frac{c_j}{\exp(\hbar\omega_{av}/k_B T) - 1} \right] \quad (5)$$

to include anharmonic effects.³⁴ Here, ω_{0j} indicates the eigenfrequency of the phonon in the absence of spin-phonon coupling at 0 K, c_j is a mode-dependent scaling factor of the anharmonic contributions, and $\omega_{av}=423$ cm⁻¹ is the arithmetic average of the phonon frequencies at room temperature.

In these AFM Cr spinels magnetic ordering is accompanied by a structural symmetry reduction. Accordingly, a splitting of the degenerate cubic $T_{1u}(j)$ modes and the appearance of new modes is expected. The most common structural distortion for spinels occurring below the Néel temperature is tetragonal with space group $I4_1/amd$ (141) (Refs. 8–11) with the following irreducible representations:³³

$$\begin{aligned} \Gamma &= 4A_{2u} + 6E_u \quad (\text{IR active}) \\ &+ 2A_{1g} + 3B_{1g} + B_{2g} + 4E_g \quad (\text{Raman active}) \\ &+ 2A_{1u} + A_{2g} + 2B_{1u} + 4B_{2u} \quad (\text{silent}). \end{aligned}$$

Such a symmetry reduction reportedly takes place in CdCr₂O₄, where the incommensurate spin structure is stabilized by a tetragonal distortion with an elongated c axis.^{12,13} Hence, one expects a splitting of each of the four cubic modes into a singlet and a doublet and the appearance of two more doublet modes. When zooming in on the dielectric loss spectra in the region of the four modes in CdCr₂O₄ in Fig. 5, splittings of all modes can be detected upon entering into the ordered state similar to the previously reported case of polycrystalline samples.⁴

Note that the effects are very subtle for the $T_{1u}(1)$ and $T_{1u}(4)$ modes and, therefore, we chose a semilogarithmic plot for these phonons. The $T_{1u}(1)$ mode develops into a broad flat feature indicative of a two-peak structure (at 148.6 and 150.4 cm^{-1}) and at about 155 cm^{-1} a new mode emerges. The splitting of the second phonon $T_{1u}(2)$ into two modes at 356.2 and 366.1 cm^{-1} , which has been described earlier in Ref. 4, is strong compared to the other phonons and amounts to approximately 10 cm^{-1} . Note that both split modes exhibit a shoulder on the high-frequency side which can be interpreted as two more new modes at 358.7 and 371.3 cm^{-1} . The phonon $T_{1u}(3)$ features a rather clear splitting into two modes at 463 and 465.4 cm^{-1} and a weak new mode appears at 500.5 cm^{-1} . On the low-energy side of the $T_{1u}(4)$ mode, at about 602.3 cm^{-1} an additional peak becomes visible below T_N and the main resonance at 609.4 cm^{-1} exhibits a shoulder at 606.8 cm^{-1} . Therefore, we identify 13 IR-active phonon modes below T_N for CdCr_2O_4 . Since from the factor-group analysis of space group $I4_1/amd$ only ten IR phonons should be observable, we conclude that the true space group should be of lower symmetry than $I4_1/amd$.^{12,13}

In ZnCr_2O_4 the reported commensurate spin structure is accompanied by a tetragonal distortion with a contracted c axis and the space group $I\bar{4}m2$ (119) has been assigned.^{3,13} The corresponding factor-group analysis for a $1\times 1\times 1$ chemical unit cell for ZnCr_2O_4 yields the following symmetry distribution of Γ -point vibrational modes:

$$\begin{aligned} \Gamma &= 8B_2 + 11E \quad (\text{IR and Raman active}) \\ &+ 6A_1 + 3B_1 \quad (\text{Raman active}) \\ &+ 3A_2 \quad (\text{silent}). \end{aligned}$$

Note that in this symmetry the $8B_2$ and $11E$ modes are both Raman and IR active because of the lack of inversion symmetry. Recently, ZnCr_2O_4 was studied using synchrotron x rays and neutron diffraction.¹⁶ To determine the tetragonal structure, x-ray integrated intensities of about 140 different superlattice reflections were measured and fitted within $I\bar{4}m2$ symmetry by Ji *et al.*¹⁶ The Cr ions were found to occupy six crystallographically distinct sites: four $8i$ sites and two $16j$ sites. Note that expanding the tetragonal unit cell by $\sqrt{2} \times \sqrt{2} \times 2$ compared to the cubic (or simply c -axis contracted tetragonal) unit cell should lead to the appearance of even more extra lines in the Raman and IR spectra.

A x-ray powder-diffraction study was also performed for ZnCr_2O_4 by Kagomiya *et al.*³⁵ and a Rietveld refinement below T_N was performed for the orthorhombic $Fddd$ symmetry (70). For this structure the factor-group analysis gives

$$\begin{aligned} \Gamma &= 7B_{1u} + 7B_{2u} + 7B_{3u} \quad (\text{IR active}) \\ &+ 3A_g + 4B_{1g} + 4B_{2g} + 4B_{3g} \quad (\text{Raman active}) \\ &+ 6A_u \quad (\text{silent}). \end{aligned}$$

Here one would expect 21 IR-active and 15 Raman-active phonons. In principle, the number of observed phonons in

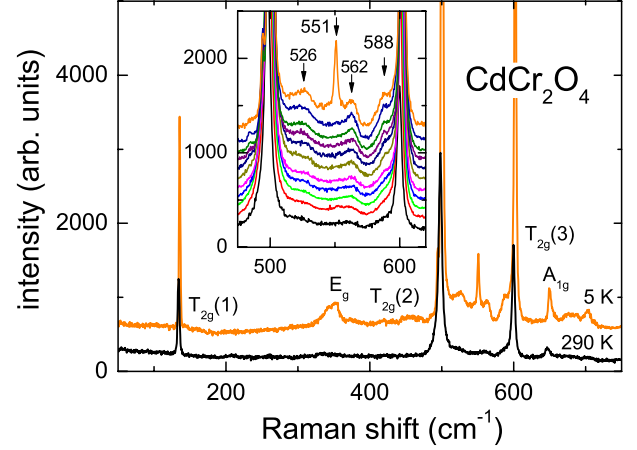


FIG. 6. (Color online) Raman spectra of CdCr_2O_4 for various temperatures. The spectrum at 5 K is shifted for clarity. In the magnetically ordered state a sharp resonance appears at 551 cm^{-1} . Inset: temperature evolution of Raman spectra in the region of the $T_{2g}(2)$ and $T_{2g}(3)$ modes ($T=5, 10, 50, 100, 150, 175, 200, 225, 250, 275,$ and 290 K from top to bottom). Additional features are indicated by arrows and their Raman shift is given in cm^{-1} . Spectra below 290 K are shifted for clarity.

the IR and Raman data could distinguish between the proposed space groups. In the IR experiment, however, only the splitting of $T_{1u}(2)$ and a new mode at 553 cm^{-1} has been observed,^{4,5} and no final conclusion can be drawn from IR data alone. Therefore, we will now turn to the Raman spectra of CdCr_2O_4 and ZnCr_2O_4 .

2. Raman scattering

The Raman spectra for CdCr_2O_4 at 290 and at 5 K, below $T_N=7.8$ K, are shown in Fig. 6. The five expected Raman modes for the cubic structure can be identified in the high-temperature data at 290 K. The spectrum consists of three phonon triplets of T_{2g} symmetry (134, 499, and 600 cm^{-1}), one weak doublet of E_g symmetry (343 cm^{-1}), and one singlet of A_{1g} symmetry (647 cm^{-1}).

The temperature dependence of the eigenfrequencies of the four intensive Raman-active modes of CdCr_2O_4 is shown in Fig. 7. With decreasing temperature, the phonon eigenfrequencies increase, as usually observed in anharmonic crystals. The data for $T > 150$ K were fitted using Eq. (5) with $\omega_{av}=423$ cm^{-1} (dashed lines in Fig. 7). The $T_{2g}(1)$ mode shows a purely anharmonic behavior while three phonon modes, $T_{2g}(2)$, $T_{2g}(3)$, and A_{1g} reveal negative deviations for $T < 150$ K. We observe no abrupt shifts of the cubic Raman modes at T_N .

Based on its energy and on the fact that it has the highest intensity among the other very weak lines in the Raman spectra, the mode at about 343 cm^{-1} is identified as the cubic E_g phonon mode. This mode is about four times as broad as the T_{2g} and A_g phonon lines. Besides, a shoulder is identified on its high energy side, which has the same frequency vs temperature behavior as the main line. However, it grows faster in intensity upon cooling. Higher order multiphonon scattering is observed in the Raman spectra, too. We identi-

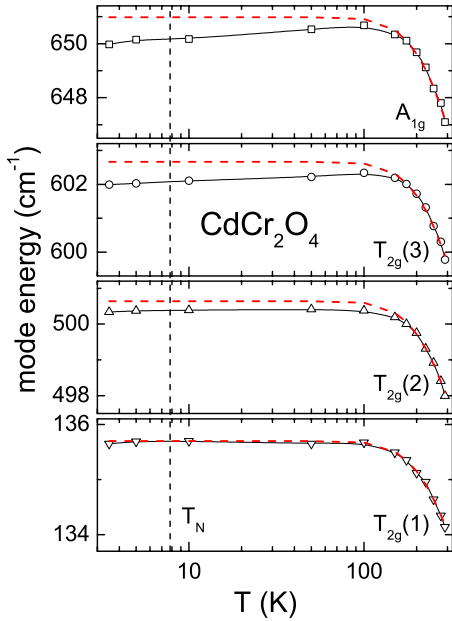


FIG. 7. (Color online) Temperature evolution of the four cubic Raman modes. The dashed lines are fits using Eq. (5). Solid lines are drawn to guide the eye.

fied lines with energies of approximately 670 and 700 cm^{-1} (not shown here) as overtones of the E_g mode and its satellite.

In the tetragonal $I4_1/amd$ phase at temperatures below T_N one expects a splitting of the triplet modes into a doublet and a singlet and the appearance of two more singlet modes, overall ten Raman-active modes. However, additional weak and broad features (indicated by arrows in the inset of Fig. 6) appear in the region of the $T_{2g}(2)$ and $T_{2g}(3)$ modes already at temperatures far above T_N . Only the feature at 551 cm^{-1} seems to be directly related to the low-temperature phase, because it is still absent at 10 K, just above the magnetostructural transition. When zooming in on the Raman spectra in the region of the $T_{2g}(2)$ mode in Fig. 8, a weak split-off resonance at 493 cm^{-1} on the low-frequency side is clearly seen upon cooling, similar to the feature at 588 cm^{-1} at the low-frequency side of $T_{2g}(3)$.

At present it is not clear where the additional modes observable above T_N stem from but such effects may be attributed to a modification of the selection rules similar to observations in resonance Raman scattering in semiconductors.³⁶ They can be separated into violations of long-wavelength selection rules as purely intrinsic bulk effects and additional extrinsic or defect contributions. Three main processes and their origin have been identified:^{37,38} (i) q -dependent, intraband Fröhlich interactions, (ii) q -independent, impurity-induced effects, and (iii) surface electric field effects at a depletion layer. All three of the given mechanisms might be relevant in the present case because comparably large intensities are observed and defects cannot be ruled out completely. Further studies including a test of polarization selection rules on samples with different defect contributions under resonant and nonresonant conditions would be needed to further clarify the origin of the additional modes.

Despite the unknown origin of these additional resonances, the Raman data provides valuable information on the

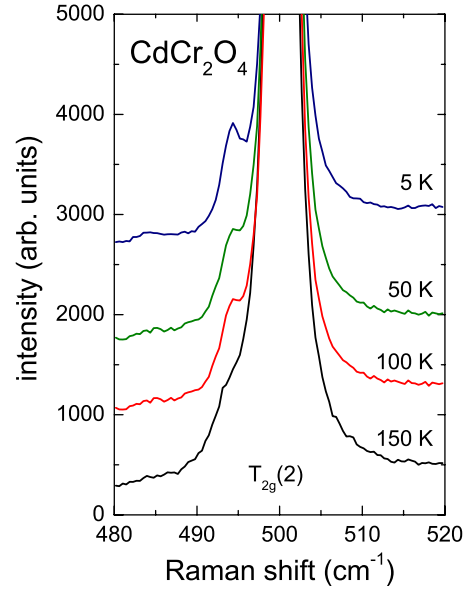


FIG. 8. (Color online) Temperature evolution of the $T_{2g}(2)$ mode and its split-off resonance at the low-frequency side (spectra are shifted for clarity).

low-temperature symmetry properties of CdCr_2O_4 because the low-temperature eigenfrequencies of the $T_{2g}(2)$ and $T_{2g}(3)$ modes are identical with two of the weak new modes appearing in the IR data below T_N . Explicit snapshots of the ion displacements for all phonon modes can be found in the work of Zwinscher and Lutz.³⁹ This strongly suggests that below T_N inversion symmetry is lost in agreement with the theoretical predictions by Chern and co-workers, who stated that the spiral magnetic ground state could be enabled by a chiral nature of the underlying lattice and proposed $I4_122$ for the space-group symmetry.^{14,15} From the infrared and Raman data we cannot identify a strong softening of an optical phonon mode in CdCr_2O_4 . However, in the case of ZnCr_2O_4 a softening of an elastic shearing mode has been observed on approaching the magnetostructural transition by Kino and

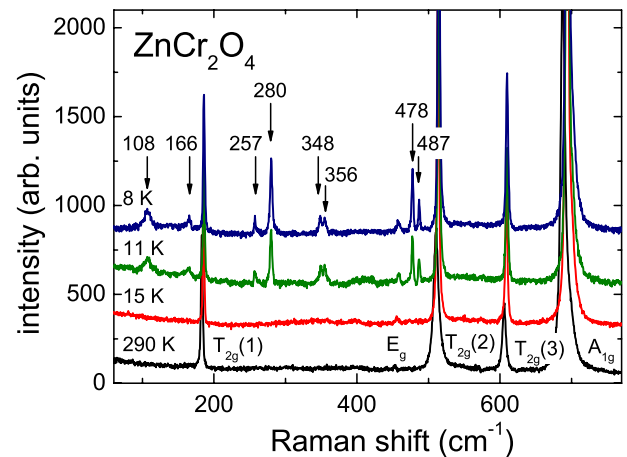


FIG. 9. (Color online) Raman spectra of ZnCr_2O_4 at selected temperatures measured at parallel polarization configuration. Spectra below room temperature are shifted for clarity by a constant offset. Arrows indicate new phonon lines at temperatures below T_N .

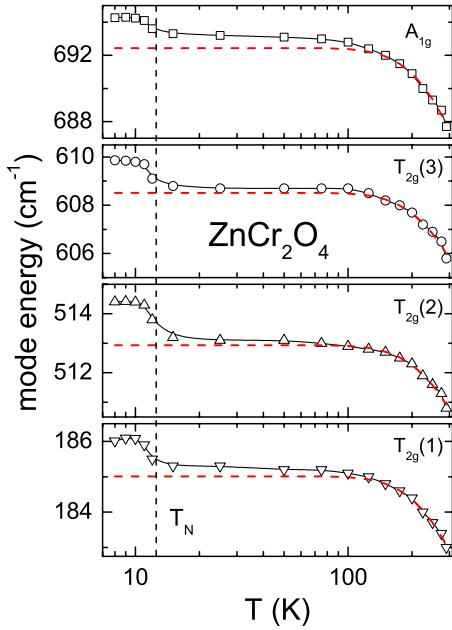


FIG. 10. (Color online) Mode energy of the phonons in ZnCr_2O_4 as a function of temperature. The dashed lines are fits to the high-temperature results using a simple anharmonic term, Eq. (5).

Lüthi,⁴⁰ calling for a similar study in this compound.

We now discuss the Raman spectra of ZnCr_2O_4 depicted in Fig. 9 for selected temperatures below and above the magnetostructural transition at $T_N=12.5$ K. Our measurements at room temperature agree with previously published data for single crystals of ZnCr_2O_4 .^{41,42} As in CdCr_2O_4 we observe the three triplets of T_{2g} symmetry (183, 511, and 606 cm^{-1}), the weak doublet of the E_g symmetry (457 cm^{-1}), and the singlet of A_{1g} symmetry (688 cm^{-1}).

The temperature dependence of the eigenfrequencies of the four intensive Raman-active modes of ZnCr_2O_4 is shown in Fig. 10. The dashed lines are fits using Eq. (5). Evidently, all modes reveal deviations from this purely anharmonic behavior for $T < 150$ K. The discrepancies are on the order of 10^{-3} and positive for all Raman-active modes. The anomalous temperature dependence smoothly evolves below 150 K, but significantly becomes enhanced just below T_N , where a jump of the eigenfrequencies occurs. We observed also an anomalous increasing of the phonon line intensities below T_N and an abrupt breakdown of their width at T_N . Figures 11(a) and 11(b) show the T dependence of the integrated intensity and linewidth of the $T_{2g}(2)$ triplet mode, respectively.

Similar anomalies in the intensity were observed in related spinels early on and, subsequently, it has been shown that this resonant effect is connected with a change in the electronic zone structure caused by magnetic ordering.⁴³ For example, in CdCr_2S_4 , resonant Raman scattering is related to a redshift in the absorption spectrum caused by the magnetic ordering.⁴⁴

The solid line in Fig. 11(b) is a fit of the temperature dependence of the phonon linewidth using

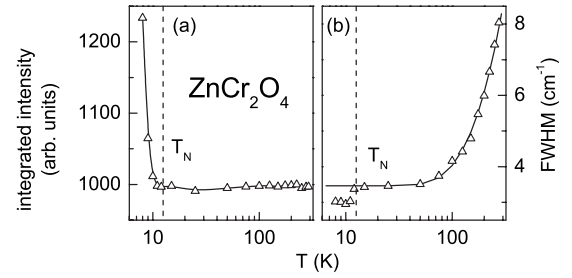


FIG. 11. (a) Temperature dependence of the integrated intensity and (b) the linewidth (full width at half maximum) of the $T_{2g}(510 \text{ cm}^{-1})$ triplet mode. The solid line in (a) is drawn in to guide the eye and reflects in (b) the expected behavior for ZnCr_2O_4 according to Eq. (6).

$$\Gamma(T) = \Gamma_0 \left[1 + \frac{d_j}{\exp(\hbar\omega_0/k_B T) - 1} \right] \quad (6)$$

with $\Gamma_0=3.46 \text{ cm}^{-1}$, the eigenfrequency $\omega_0=516 \text{ cm}^{-1}$, and d_j being a mode dependent fit parameter. The data can be described very well down to the Néel temperature by this expression, which incorporates cubic anharmonicity effects.^{45,46}

Experimentally, besides the shifts of the five cubic phonon modes, we observe an appearance of eight new phonon modes with frequencies 106.7, 164.8, 257.3, 280, 348.4, 355, 477.6, and 487.0 cm^{-1} in the Raman spectra of ZnCr_2O_4 below T_N (indicated by arrows in Fig. 9). Unfortunately, the identification of a total of 13 Raman and six IR-active modes does not allow to conclusively discard any of the proposed low-temperature symmetries. However, we would like to point out that, in contrast to CdCr_2O_4 , we could not identify any phonon mode that appears in both Raman and IR spectra below T_N as implied by the assignment of the $\bar{I}4m2$ symmetry^{3,13,16} or the additional orthorhombic lattice distortions within space group $F222$ (22) evoked to describe the antiferromagnetic resonance properties of ZnCr_2O_4 .¹⁷

D. Spin-phonon coupling

In the Cr spinels spin-phonon coupling is considered to be the driving force to relieve magnetic frustration by the magnetostructural phase transition. Already above the transition, in the correlated paramagnetic state, the spin-phonon coupling shows up in the temperature dependence of the phonon frequencies. In the following we will concentrate on the IR-active $T_{1u}(2)$ modes of CdCr_2O_4 and ZnCr_2O_4 because this mode exhibits a clear splitting upon entering into the magnetically ordered state [Figs. 4(c) and 4(d)]. With respect to the behavior expected for the frequency shift due to anharmonicity [solid line in Fig. 4(c)], there is a clear deviation which becomes stronger on approaching magnetic ordering. Therefore, it has been attributed to the coupling of the lattice to spin fluctuations. Considering a nn Heisenberg spin system, Baltensberger and Helman related the frequency shift of lattice vibrations in magnetic crystals to the magnetic energy of the system,

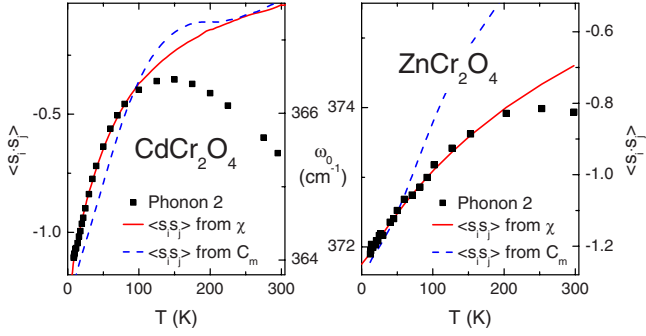


FIG. 12. (Color online) Temperature dependence of the spin correlations $\langle S_i S_j \rangle$ derived according to Eqs. (9) and (10) and the eigenfrequency ω_0 of phonon $T_{1u}(2)$ in a scaling that reveals a linear behavior of the two quantities at low temperatures.

$$\Delta\omega \approx \lambda \langle S_i S_j \rangle, \quad (7)$$

by introducing the spin-phonon coupling parameter λ , which depends on the derivatives of the exchange constants with respect to the coordinates of the magnetic ions.^{47,48} The coupling parameter λ in the paramagnetic state can be determined if both the frequency shift of the lattice vibrations and the spin-spin correlation function are known. To obtain the spin-spin correlation function we follow two independent approaches.

According to the fluctuation-dissipation theorem the magnetic molar susceptibility per spin in the disordered state can be written as

$$\chi(T) = \frac{N_A g^2 \mu_B^2}{k_B T} \sum_{m,n} \langle S_m S_n \rangle_\chi, \quad (8)$$

where $\langle S_m S_n \rangle$ represents the spin-spin correlation function between the spin S_m and S_n . Restricting the sum to nn, the spin-spin correlation function is given by

$$\langle S_i S_j \rangle_\chi = \frac{k_B T \chi(T)}{N_A g^2 \mu_B^2} - \frac{s(s+1)}{3}, \quad (9)$$

i.e., we can directly utilize the experimental susceptibility data shown in Fig. 2.

An alternative derivation of the nn spin-spin correlation function can be obtained from specific-heat data.⁵ Assuming that the dominant part of the magnetic energy is given by the nn Heisenberg interaction, one can extract the temperature dependence of the spin-spin correlations from the magnetic contribution of the specific heat via

$$\langle S_i S_j \rangle_{C_m}(T) = \text{const} + \frac{1}{6N_A J_1} \int_{T_N}^T C_m(\vartheta) d\vartheta, \quad (10)$$

where $6N_A$ is the number of bonds between adjacent magnetic ions per mole. For the analysis of the specific heat, we used the nn exchange coupling J_1 obtained from the magnetic susceptibility data derived in Sec. III A.

In Fig. 12 we plot $\langle S_i S_j \rangle(T)$ calculated from the magnetic susceptibility (solid line) and from the magnetic contribution of the specific heat (dashed line). In addition, the eigenfrequencies ω_0 of the $T_{1u}(2)$ mode are shown as a function of

temperature (solid squares). The offsets and scalings of the ordinates were chosen to make ω_0 coincide with the susceptibility data. Comparing the curves for the correlation functions of CdCr_2O_4 , one can see that they show a similar evolution and a good agreement of their absolute values. At low temperatures both exhibit a quasilinear behavior. With increasing temperatures they increase monotonically and reach zero at about room temperature. Up to 125 K the phonon frequency scales very well with the evolution of $\langle S_i S_j \rangle$. The similarity between the correlation curves can be regarded as a justification of the procedure to describe and extract the lattice contribution to the specific heat in Sec. III B. Since, however, $\langle S_i S_j \rangle_{C_m}$ suffers from the uncertainty of modeling the PDOS and depends on the exact determination of the nn exchange coupling J_1 , we think that the use of $\langle S_i S_j \rangle_\chi$ leads to a more precise determination of λ . In case of ZnCr_2O_4 , the correlation functions obtained by both approaches show a similar evolution up to ≈ 50 K. However, above this temperature they seem to diverge increasingly. This behavior most probably is owed to the difficulty of modeling the lattice contribution in this compound over a broad temperature range accurately. Due to the high absolute value of Θ_{CW} , even at room-temperature magnetic fluctuations can be expected generating a significant contribution to the heat capacity. Nevertheless, for the further analysis the low-temperature correlations are of decisive importance, which should be determined by the scaled Debye contribution of the lattice accurately.

Assuming that Eq. (7) holds, we directly plot the frequency shift $\Delta\omega$ vs the spin-spin correlation $\langle S_i S_j \rangle_\chi$ and $\langle S_i S_j \rangle_{C_m}$ for the measured temperatures above T_N in Fig. 13. Figure 13(a) clearly documents a linear behavior for CdCr_2O_4 up to about 100 K. The solid line is a linear fit to the data [Eq. (7)] and yields a value for the spin-phonon coupling constant in the paramagnetic state of $\lambda_\chi = 3.3 \text{ cm}^{-1}$. At 125 K the eigenfrequencies begin to deviate from the regression curve. The inset [Fig. 13(b)] shows ω_0 against $\langle S_i S_j \rangle_{C_m}$, the spin-spin correlation function calculated from the magnetic specific heat. Below 50 K the data can be fitted linearly giving a slope of $\lambda_{C_m} = 3.9 \text{ cm}^{-1}$. Above 50 K it starts to deviate until an abrupt breakdown above 150 K occurs. In the lower panels of Fig. 13 we present our results for the ZnCr_2O_4 spinel. The plot of ω_0 versus $\langle S_i S_j \rangle_\chi$ [Fig. 13(c)] shows a linear increase up to about 150 K. The slope gives a coupling constant of $\lambda_\chi = 5.0 \text{ cm}^{-1}$. When the frequency shift is plotted against $\langle S_i S_j \rangle_{C_m}$ we attain a value of 4.0 cm^{-1} . This drawing reveals a convincing linear relation up to about 60 K and then starts to segregate from the regression curve [see Fig. 13(d)].

A comparable value $\lambda = 6.2 \text{ cm}^{-1}$ has been reported for ZnCr_2O_4 by Sushkov *et al.*⁵ using $\langle S_i S_j \rangle$ derived by subtracting the specific heat of nonmagnetic ZnGa_2O_4 from ZnCr_2O_4 . Although we could not follow their approach as described above, the agreement with our results $\lambda_\chi = 5.0 \text{ cm}^{-1}$ and $\lambda_{C_m} = 4.0$ is fairly good.

Keeping in mind that the spin-phonon coupling leads to the magnetostructural phase transition the splitting of the $T_{1u}(2)$ modes allows to obtain further estimates for λ . The magnetostructural transition can be described by the spin-

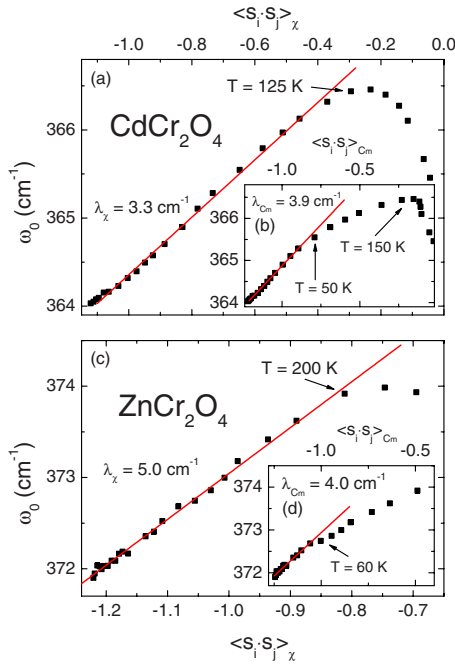


FIG. 13. (Color online) Eigenfrequency ω_0 as a function of the spin-spin correlation functions for CdCr_2O_4 and ZnCr_2O_4 . [(a) and (c)] ω_0 vs $\langle S_i S_j \rangle_\chi$ obtained from the magnetic-susceptibility data. [(b) and (d)] ω_0 vs $\langle S_i S_j \rangle_{c_m}$ derived from specific-heat measurement.

Peierls order parameter $n_{sp} = \langle S_1 S_2 - S_1 S_4 \rangle$. It accounts for the difference in tetrahedral bonds with ferromagnetic or antiferromagnetic coupling and vanishes accordingly in the undistorted paramagnetic state. The splitting between the two modes can then be expressed in terms of n_{sp} (Ref. 49),

$$\Delta\omega \approx \lambda \langle S_1 S_2 - S_1 S_4 \rangle. \quad (11)$$

In the case of CdCr_2O_4 , where the dominant distortion is a uniform elongation along the c axis, the singlet mode is lower in energy and the order parameter becomes $n_{sp} = -9/4$ if one assumes a collinear ground state of the spins. For the proposed tetragonal distortion of ZnCr_2O_4 with space group $\bar{1}4m2$,¹³ n_{sp} equals $9/2$ when assuming an oversimplified model of a collinear ground state.

Via this approach $\lambda = 4.4 \text{ cm}^{-1}$ and $\lambda = 2.6 \text{ cm}^{-1}$ have been extracted previously for CdCr_2O_4 and ZnCr_2O_4 , respectively.⁵ We find that the value for CdCr_2O_4 compares nicely to our results derived in the paramagnetic phase. This indicates that the proposed order parameter based on a collinear spin state describes the magnetostructural transition correctly. Assuming that our value for λ for ZnCr_2O_4 is valid to describe also the splitting below T_N , one can estimate $n_{sp} \approx 2$, confirming that the assumption of a collinear spin configuration does not hold for this compound.

IV. SUMMARY

Using a quantum tetrahedral mean-field model we fitted the susceptibilities of CdCr_2O_4 and ZnCr_2O_4 and obtained the nn and nnn exchange coupling constants $J_1 = 14.7 \text{ K}$, $J_2 = -4.0 \text{ K}$, and $J_1 = 33.4 \text{ K}$, $J_2 = 4.4 \text{ K}$, respectively. Moreover, we analyzed the specific heat for these systems in comparison to nonmagnetic reference compounds. From both the susceptibility and the specific heat, we extracted the spin-spin correlation function in order to relate it to the shift of the IR phonon $T_{1u}(2)$ which shows the strongest splitting at the Néel temperature. We argue that the results derived by using directly the magnetic susceptibility appear more reliable, giving spin-phonon coupling parameters $\lambda = 3.3 \text{ cm}^{-1}$ and $\lambda = 5.0 \text{ cm}^{-1}$ for the Cd and Zn spinel, respectively. Additionally, we show that the observed IR and Raman spectra of CdCr_2O_4 provide evidence for the loss of inversion symmetry, thus ruling out the proposed $I4_1/amd$ symmetry in the magnetically ordered phase. For the low-temperature phase of ZnCr_2O_4 we observed the appearance of several new modes in the Raman and IR spectrum without any signatures of a loss of inversion symmetry.

ACKNOWLEDGMENTS

We thank A. Krimmel, D. L. Huber, A. J. García-Adeva, Yu. G. Pashkevich, and O. Tchernyshyov for fruitful discussions. This work was partly supported by the Deutsche Forschungsgemeinschaft (DFG) through the Collaborative Research Center SFB 484 (University of Augsburg) and the Project No. LE967/6-1 (TU-BS) by ESF-HFM and B-IGSM V.G. acknowledges Ukrainian-Belorussiania under Grant No. F29.1/014 for a partial support.

*joachim.deisenhofer@physik.uni-augsburg.de

¹S.-H. Lee, C. Broholm, W. Ratcliff, G. Gasparovic, Q. Huang, T. H. Kim, and S.-W. Cheong, *Nature (London)* **418**, 856 (2002).

²M. T. Rovers, P. P. Kyriakou, H. A. Dabkowska, G. M. Luke, M. I. Larkin, and A. T. Savici, *Phys. Rev. B* **66**, 174434 (2002).

³S.-H. Lee, C. Broholm, T. H. Kim, W. Ratcliff II, and S.-W. Cheong, *Phys. Rev. Lett.* **84**, 3718 (2000).

⁴T. Rudolf, Ch. Kant, F. Mayr, J. Hemberger, V. Tsurkan, and A. Loidl, *New J. Phys.* **9**, 76 (2007).

⁵A. B. Sushkov, O. Tchernyshyov, W. Ratcliff II, S. W. Cheong, and H. D. Drew, *Phys. Rev. Lett.* **94**, 137202 (2005).

⁶O. Tchernyshyov, R. Moessner, and S. L. Sondhi, *Phys. Rev. B* **66**, 064403 (2002).

⁷Y. Yamashita and K. Ueda, *Phys. Rev. Lett.* **85**, 4960 (2000).

⁸J. Akimitsu, K. Siratori, G. Shirane, M. Iiyumi, and T. Watanabe, *J. Phys. Soc. Jpn.* **44**, 172 (1978).

⁹M. Hidaka, M. Yoshimura, N. Tokiwa, J. Akimitsu, Y. J. Park, J. H. Park, S. D. Ji, and K. B. Lee, *Phys. Status Solidi B* **236**, 570 (2003).

¹⁰P. G. Radaelli, *New J. Phys.* **7**, 53 (2005).

¹¹M. Reehuis, A. Krimmel, N. Büttgen, A. Loidl, and A. Prokofiev, *Eur. Phys. J. B* **35**, 311 (2003).

- ¹²J.-H. Chung, M. Matsuda, S.-H. Lee, K. Kakurai, H. Ueda, T. J. Sato, H. Takagi, K.-P. Hong, and S. Park, *Phys. Rev. Lett.* **95**, 247204 (2005).
- ¹³S.-H. Lee, G. Gasparovic, C. Broholm, M. Matsuda, J.-H. Chung, Y. J. Kim, H. Ueda, G. Xu, P. Zschack, K. Kakurai, H. Takagi, W. Ratcliff, T. H. Kim, and S.-W. Cheong, *J. Phys.: Condens. Matter* **19**, 145259 (2007).
- ¹⁴G.-W. Chern, C. J. Fennie, and O. Tchernyshyov, *Phys. Rev. B* **74**, 060405(R) (2006).
- ¹⁵O. Tchernyshyov and G.-W. Chern, arXiv:0907.1693 (unpublished).
- ¹⁶S. Ji, S.-H. Lee, C. Broholm, T. Y. Koo, W. Ratcliff, S.-W. Cheong, and P. Zschack, *Phys. Rev. Lett.* **103**, 037201 (2009).
- ¹⁷V. N. Glazkov, A. M. Farutin, V. Tsurkan, H.-A. Krug von Nidda, and A. Loidl, *Phys. Rev. B* **79**, 024431 (2009).
- ¹⁸I. Kagomiya, K. Kohn, M. Toki, Y. Hata, and E. Kita, *J. Phys. Soc. Jpn.* **71**, 916 (2002).
- ¹⁹H. Poulet and J. P. Mathieu, *Vibration Spectra and Symmetry of Crystals* (Gordon and Breach, New York, 1976).
- ²⁰R. Valdés Aguilar, A. B. Sushkov, Y. J. Choi, S.-W. Cheong, and H. D. Drew, *Phys. Rev. B* **77**, 092412 (2008).
- ²¹T. Rudolf, C. Kant, F. Mayr, M. Schmidt, V. Tsurkan, J. Deisenhofer, and A. Loidl, *Eur. Phys. J. B* **68**, 153 (2009).
- ²²A. J. García-Adeva and D. L. Huber, *Phys. Rev. Lett.* **85**, 4598 (2000).
- ²³A. B. Kuzmenko, *Rev. Sci. Instrum.* **76**, 083108 (2005).
- ²⁴H. Martinho, N. Moreno, J. Sanjurjo, C. Rettori, A. Garcia-Adeva, D. Huber, S. Oseroff, W. Ratcliff II, S. Cheong, P. Pagliuso, J. L. Sarrao, and G. B. Martins, *J. Appl. Phys.* **89**, 7050 (2001).
- ²⁵H. Martinho, N. O. Moreno, J. A. Sanjurjo, C. Rettori, A. J. Garcia-Adeva, D. L. Huber, S. B. Oseroff, W. Ratcliff II, S.-W. Cheong, P. G. Pagliuso, J. L. Sarrao, and G. B. Martins, *Phys. Rev. B* **64**, 024408 (2001).
- ²⁶F. Leccabue, B. E. Watts, D. Fiorani, A. M. Testa, J. Alvarez, V. Sagredo, and G. Bocelli, *J. Mater. Sci.* **28**, 3945 (1993).
- ²⁷A. J. García-Adeva and D. L. Huber, *Physica B* **320**, 18 (2002).
- ²⁸A. J. García-Adeva and D. L. Huber, *Phys. Rev. B* **63**, 174433 (2001).
- ²⁹A. J. García-Adeva and D. L. Huber, *Phys. Rev. B* **63**, 140404(R) (2001).
- ³⁰A. J. Garcia-Adeva and D. L. Huber, *Phys. Rev. B* **65**, 184418 (2002).
- ³¹Ch. Kant, J. Deisenhofer, V. Tsurkan, and A. Loidl, arXiv:0905.4903 (unpublished).
- ³²C. M. Fang, C.-K. Loong, G. A. de Wijs, and G. de With, *Phys. Rev. B* **66**, 144301 (2002).
- ³³D. L. Rousseau, R. P. Bauman, and S. P. S. Porto, *J. Raman Spectrosc.* **10**, 253 (1981).
- ³⁴K. Wakamura and T. Arai, *J. Appl. Phys.* **63**, 5824 (1988).
- ³⁵I. Kagomiya, H. Sawa, K. Siratori, K. Kohn, M. Toki, Y. Hata, and E. Kita, *Ferroelectrics* **268**, 327 (2002).
- ³⁶W. Kauschke, N. Mestres, and M. Cardona, *Phys. Rev. B* **36**, 7469 (1987).
- ³⁷R. M. Martin and T. C. Damen, *Phys. Rev. Lett.* **26**, 86 (1971).
- ³⁸R. M. Martin and L. M. Falicov, in *Light Scattering in Solids*, Topics in Applied Physics Vol. 8, edited by M. Cardona (Springer, Berlin, 1975), pp. 79–145.
- ³⁹J. Zwinscher and H. D. Lutz, *J. Solid State Chem.* **118**, 43 (1995).
- ⁴⁰Y. Kino and B. Lüthi, *Solid State Commun.* **9**, 805 (1971).
- ⁴¹H. D. Lutz, B. Müller, and H. J. Steiner, *J. Solid State Chem.* **90**, 54 (1991).
- ⁴²J. Himmrich and H. D. Lutz, *Solid State Commun.* **79**, 447 (1991).
- ⁴³G. Güntherodt and R. Zeyher, in *Light Scattering in Solids IV (Electronic Scattering, Spin Effects, SERS, and Morphic Effects)*, Topics in Applied Physics Vol. 54, edited by M. Cardona and G. Güntherodt (Springer-Verlag, Berlin, 1989).
- ⁴⁴N. Koshizuka, Y. Yokoyama, and T. Tsushima, *Solid State Commun.* **18**, 1333 (1976).
- ⁴⁵P. G. Klemens, *Phys. Rev.* **148**, 845 (1966).
- ⁴⁶M. Balkanski, R. F. Wallis, and E. Haro, *Phys. Rev. B* **28**, 1928 (1983).
- ⁴⁷W. Baltensperger and J. S. Helman, *Helv. Phys. Acta* **41**, 668 (1968).
- ⁴⁸W. Baltensperger, *J. Appl. Phys.* **41**, 1052 (1970).
- ⁴⁹C. J. Fennie and K. M. Rabe, *Phys. Rev. Lett.* **96**, 205505 (2006).