

Low-temperature electrical resistivity of slightly Ge-doped YbRh₂Si₂

M. Schubert, H. S. Jeevan, Philipp Gegenwart

Angaben zur Veröffentlichung / Publication details:

Schubert, M., H. S. Jeevan, and Philipp Gegenwart. 2011. "Low-temperature electrical resistivity of slightly Ge-doped YbRh₂Si₂." *Journal of the Physical Society of Japan* 80 (Suppl. A): SA004. <https://doi.org/10.1143/jpsjs.80sa.sa004>.

Nutzungsbedingungen / Terms of use:

licgercopyright

Dieses Dokument wird unter folgenden Bedingungen zur Verfügung gestellt: / This document is made available under these conditions:

Deutsches Urheberrecht

Weitere Informationen finden Sie unter: / For more information see:

<https://www.uni-augsburg.de/de/organisation/bibliothek/publizieren-zitieren-archivieren/publiz/>



Low-temperature electrical resistivity of slightly Ge-doped YbRh_2Si_2

M. Schubert, H.S. Jeevan and P. Gegenwart*

I. Physik. Institut, Georg-August-Universität Göttingen, D-37077 Göttingen

Quantum criticality in single crystalline $\text{YbRh}_2(\text{Si}_{1-x}\text{Ge}_x)_2$ with $x \approx 0.01$ is investigated by electrical resistivity measurements down to 15 mK at various magnetic fields applied parallel and perpendicular to the c -axis. Compared to undoped YbRh_2Si_2 with $T_N = 75$ mK (from the onset of the resistive signature), the slightly Ge-doped sample exhibits a reduced Néel temperature of 53 mK. In contrast to the recent report on nominally $\text{YbRh}_2(\text{Si}_{0.95}\text{Ge}_{0.05})_2$, we do not observe evidence for a non-Fermi liquid regime at $T \rightarrow 0$ over an extended magnetic field range. The obtained phase diagrams rather resemble the case of undoped YbRh_2Si_2 .

The tetragonal YbRh_2Si_2 is one of the prototype heavy fermion (HF) systems, which displays pronounced non-Fermi liquid (NFL) behavior related to a magnetic quantum critical point (QCP).¹⁾ The latter is realized by suppression of a very weak antiferromagnetic (AF) state below $T_N = 70$ mK at a critical magnetic field B_c of 0.06 T (0.7 T) perpendicular (parallel) to the tetragonal c -axis.²⁾ The observed thermodynamic, transport and magnetic properties are in contradiction with the predictions for an itinerant AF QCP.^{3–5)} Different alternative theoretical scenarios have been proposed for YbRh_2Si_2 , i.e. a breakdown of Kondo screening,^{6–9)} the vicinity to a quantum tricritical point,¹⁰⁾ a critical valence transition¹¹⁾ or a fermion condensation quantum phase transition.¹²⁾

One crucial question concerns the evolution of the Fermi surface across the QCP, since a destruction of Kondo screening would lead to a decomposition of the heavy quasiparticles into conduction electrons and local magnetic moments. In such case, an additional energy scale, often labeled T^* , related to the formation of a Kondo screened HF state, is expected to vanish at the QCP. Indeed, measurements of the Hall coefficient and various other transport and thermodynamic properties have proven the existence of such an energy scale $T^*(B)$ in the $T - B$ phase diagram of YbRh_2Si_2 , which terminates at the field-induced QCP.^{13,14)} The extrapolation of the broadened crossover in the Hall-effect towards $T \rightarrow 0$ suggests a step-like change of the Hall coefficient. This is interpreted as a collapse of the heavy quasiparticle Fermi surface at the QCP.¹⁵⁾

It has been found, that $T^*(B)$ and $T_N(B)$ could be separated from each other under hydrostatic¹⁶⁾ or chemical pressure.¹⁷⁾ Negative chemical pressure, achieved by either partially replacing Rh with larger Ir¹⁷⁾ or Si with larger Ge,¹⁸⁾ results in a finite field range, in which the system neither orders magnetically, nor forms a Fermi liquid ground state. Such a NFL phase could indicate a novel fractionalized Fermi liquid state.¹⁹⁾

Below, we focus on Ge-doped YbRh_2Si_2 . The isoelectronic substitution of Si with Ge weakens the Kondo interaction and leads to a reduction of the Néel temperature to 20 mK in nominally $\text{YbRh}_2(\text{Si}_{0.95}\text{Ge}_{0.05})_2$ which in fact has a Ge-content of 2% only.³⁾ This large discrepancy between the nominal and

actual Ge concentration results from a reduced solubility of Ge compared to Si in the In flux. We have performed a new growth of $\text{YbRh}_2(\text{Si}_{1-x}\text{Ge}_x)_2$ with a nominal Ge-content of $x = 0.1$ using a flux of 75% In and 25% Sn. Different single crystalline pieces have been obtained and characterized by X-ray diffraction (XRD), electron microprobe energy dispersive x-ray (EDX) and electrical resistivity measurements between 4 and 300 K. Unfortunately, XRD, due to the very small effect on the lattice parameters, and EDX, because the Yb-L and Ge-K lines overlap, could not be used to determine the exact Ge concentration. The effect of Ge-doping can be observed as a slight shift of the electrical resistivity maximum temperature T_{max} which equals 125 K for undoped YbRh_2Si_2 towards higher temperatures.²⁰⁾ To roughly estimate the Ge content of the different new single crystals we have measured their $\rho(T)$ behavior. The crystal with the largest shift of T_{max} has been studied by tomographic atom probe, revealing a Ge concentration of only $x = 0.015$. Thus, the problem with the solubility of Ge has not been solved using the different flux. The single crystalline piece studied in this paper has a lower shift of T_{max} and displays a smaller residual resistivity (ρ_0). Accordingly, its Ge-concentration is considerably lower and will not exceed 1%. In the following, we label the single crystal as $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$. The low-temperature electrical resistivity has been measured in a dilution refrigerator using the four-terminal ac technique on a thin plate-like single crystal with the current flowing in the plane perpendicular to the c -axis.

Figure 1 displays the electrical resistivity $\rho(T)$ of the investigated $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$ single crystal at various magnetic fields $B \perp c$ (a) and $B \parallel c$ (b). Upon cooling from 1 K, an almost linear temperature dependence is found for all different curves, whereas significant changes in slope occur only below 0.2 K. At zero magnetic field, we observe a sharp decrease at the onset of the Néel ordering, similar as has been found for undoped YbRh_2Si_2 .²⁾ Taking the maximum in the temperature derivative $d\rho(T)/dT$, we estimate $T_N = (0.055 \pm 0.003)$ K for $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$, which is about 0.02 K lower as in undoped YbRh_2Si_2 . With increasing B we find a continuous suppression of $T_N \rightarrow 0$ towards critical magnetic fields B_c of (0.06 ± 0.005) T and (0.6 ± 0.1) T for $B \perp c$ and $B \parallel c$, respectively. At $B > B_c$, the low-T resistivity tends towards a T^2 dependence below T_{LFL} .

*pgegenw@gwdg.de

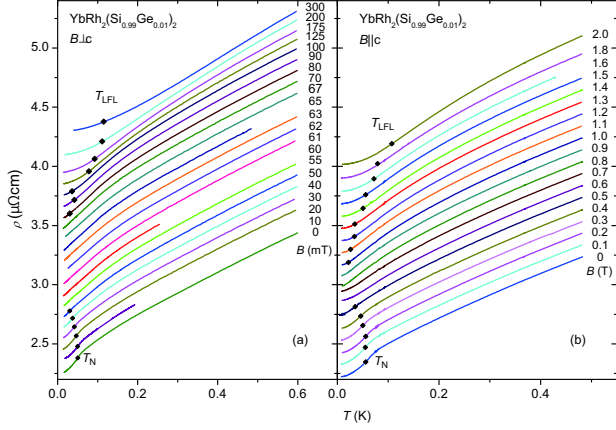


Fig. 1. Temperature dependence of the electrical resistivity of $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$ at various magnetic fields applied perpendicular (a) and along the c-axis (b). For clarity, the curves at $B > 0$ are shifted by $0.1 \mu\Omega\text{cm}$ with respect to each other. T_N indicates AF transition temperature as determined from maxima in $d\rho/dT$, T_{LFL} marks upper boundary of $\rho(T) = \rho_0 + AT^2$ behavior.

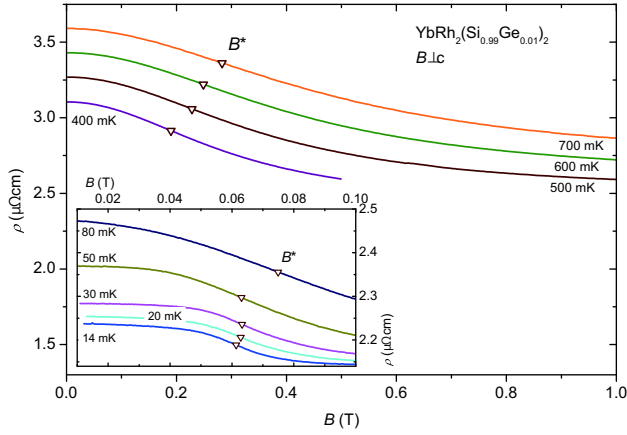


Fig. 2. Magnetoresistance of $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$ at selected temperatures. The triangles indicate the positions of inflection points related to the energy scale $T^*(B)$.

Complementary measurements of the magnetoresistance (MR) have been performed in the easy magnetic plane ($B \perp c$) only. As shown in Figure 2, an overall negative MR is found at low fields. Clear inflection points are found, whose positions shift towards higher fields with increasing temperature. A very similar signature has been found for undoped YbRh_2Si_2 at the low-energy scale $T^*(B)$ determined from the Hall effect¹³⁾ and various thermodynamic measurements.^{5,14)} Compared to undoped YbRh_2Si_2 , we do not observe any shift of $T^*(B)$ like reported for low Ir- or Co-doped systems.¹⁷⁾

Next, we turn to the analysis of the temperature dependence of the electrical resistivity. At those magnetic fields where the resistivity follows $\rho(T) = \rho_0 + A(B)T^2$, i.e. within the AF phase, as well as below T_{LFL} at $B > B_c$, the coefficient $A(B)$ has been determined (cf. Figure 3). Upon reducing the field

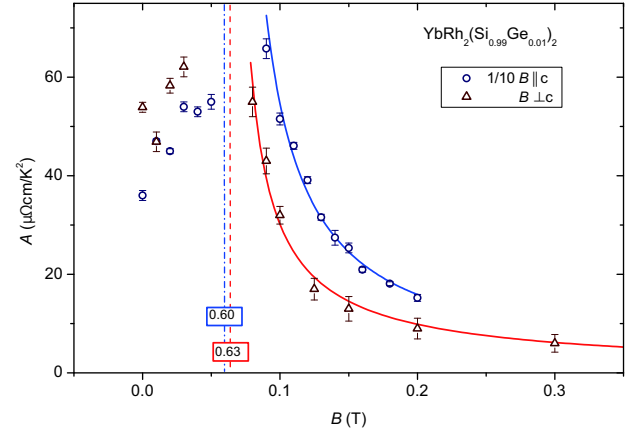


Fig. 3. Magnetic field dependence of the coefficient A derived from $\rho(T) = \rho_0 + AT^2$ for $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$. The data for $B \parallel c$ have been divided by an anisotropy factor of 10.

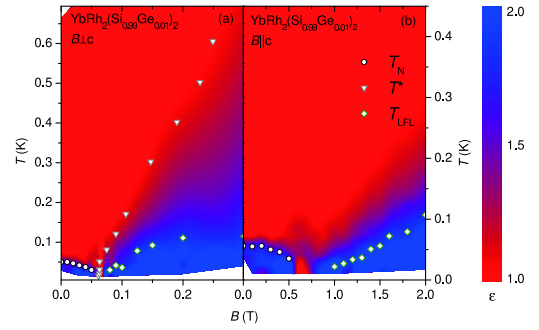


Fig. 4. Temperature versus magnetic field phase diagram for $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$ for $B \perp c$ (a) and $B \parallel c$ (b). The circles, triangles and diamonds indicate T_N , T^* and T_{LFL} (see text). The color code reflects the exponent of the temperature dependence of the resistivity calculated as $\epsilon = d\log(\rho - \rho_0)/d\log T$.

from $B > B_c$ towards B_c , diverging behavior is found which could approximately be described by $A(B) \propto (B - B_c)^{-1}$ with $B_c = 0.6$ for $B \parallel c$ and $A(B) \propto (B - B_c)^{-0.85}$ with $B_c = 0.063$ for $B \perp c$, respectively. Similar behavior has been found for undoped YbRh_2Si_2 .²⁾ Despite the 25% reduction of T_N in $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$, the critical fields are not reduced compared to the pure system.

To get further information on a possible NFL phase in $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$, we analyze the temperature dependence of the resistivity exponent ϵ as $\epsilon = d\log(\rho - \rho_0)/d\log T$, like it has been done for nominally $\text{YbRh}_2(\text{Si}_{0.95}\text{Ge}_{0.05})_2$.³⁾ As shown in Figure 4, for both field orientations no indication for an extended NFL phase at $T = 0$ could be found. Previously, Knebel et al. have claimed a T^2 dependence of the electrical resistivity in undoped YbRh_2Si_2 even directly at the field-induced QCP.²¹⁾ However, pure single crystals of YbRh_2Si_2 with $\rho_0 = 0.5 \mu\Omega\text{cm}$ have clearly shown a linear T -dependence at B_c down to 20 mK.²²⁾ For the slightly Ge-doped single crystal studied in this paper, no indication for a

crossover to T^2 behavior is found for $B \perp c$ (cf. Fig. 1a) for fields between 0.055 and 0.065 T. For $B \parallel c$ only at 0.8 T a linear temperature dependence is found towards lowest temperatures, whereas at slightly smaller fields a significant curvature in $\rho(T)$ is found. We may speculate that a smearing of the AF transition due to the disorder introduced by the slight Ge-doping causes this behavior at fields applied along the hard direction. On the other hand, the *stronger* Ge-doped $\text{YbRh}_2(\text{Si}_{0.95}\text{Ge}_{0.05})_2$ (with actual composition of $x \approx 0.02$) studied previously, has displayed an extended $T \rightarrow 0$ NFL regime at $0 \leq 0.7$ T for this field orientation with no indication of curvature in $\rho(T)$ in the same temperature range.¹⁸⁾ Additional thermodynamic experiments in this field orientation are needed to prove the existence of an extended NFL phase.

To summarize, we have performed low-temperature electrical resistivity measurements on a $\text{YbRh}_2(\text{Si}_{0.99}\text{Ge}_{0.01})_2$ single crystal at magnetic fields applied parallel and perpendicular to the c -axis. Compared to the pure compound, a 25% reduction of the Néel temperature is found, whereas the critical fields and the field dependence of the A coefficient are almost unchanged. We do not find indications for a NFL regime at $T \rightarrow 0$ over an extended range in magnetic field, as reported for $\text{YbRh}_2(\text{Si}_{0.95}\text{Ge}_{0.05})_2$ (with actual composition of $x \approx 0.02$) at $B \parallel c$.³⁾ We conclude, that more than 1% Ge substitution is required for obtaining a NFL phase.

We would like to thank C. Geibel, F. Steglich, Y. Tokiwa and K. Winzer for useful discussions. This work was supported by the DFG research unit 960 "Quantum phase transitions".

- 1) O. Trovarelli, C. Geibel, S. Mederle, C. Langhammer, F. M. Grosche, P. Gegenwart, M. Lang, G. Sparn, and F. Steglich: Phys. Rev. Lett. **85** (2000) 626
- 2) P. Gegenwart, Custers J., C. Geibel, K. Neumaier, T. Tayama, K. Tenya,

- O. Trovarelli, and F. Steglich: Phys. Rev. Lett. **89** (2002) 056402
- 3) J. Custers, P. Gegenwart, H. Wilhelm, K. Neumaier, Y. Tokiwa, O. Trovarelli, C. Geibel, F. Steglich, C. Pepin, and P. Coleman: Nature **424** (2003) 524.
- 4) R. K  chler, N. Oeschler, P. Gegenwart, T. Cichorek, K. Neumaier, O. Tegus, C. Geibel, J.A. Mydosh, F. Steglich, L. Zhu, and Q. Si: Phys. Rev. Lett. **91** (2003) 066405.
- 5) Y. Tokiwa, T. Radu, C. Geibel, F. Steglich, and P. Gegenwart: Phys. Rev. Lett. **102** (2009) 066401
- 6) P. Coleman, C. P  pin, Q. Si, and R. Ramazashvili: J. Phys. Condens. Matter **13** (2001) R723.
- 7) Q. Si, M.S. Rabello, K. Ingersent, and J.L. Smith: Nature **413** (2001) 804.
- 8) T. Senthil, M. Vojta, and S. Sachdev: Phys. Rev. B **69** (2004) 035111.
- 9) I. Paul, C. P  pin, and M.R. Norman: Phys. Rev. Lett. **98**, 026402 (2007), C. P  pin, Phys. Rev. Lett. **98**, 206401 (2007)
- 10) T. Misawa, Y. Yamaji, and M. Imada: J. Phys. Soc. Jpn. **77** (2008) 093712.
- 11) S. Watanabe, A. Tsuruta, K. Miyake, and J. Flouquet: J. Phys. Soc. Jpn. **78** (2009) 104706.
- 12) V.R. Shaginyan, JETP Lett. **79** (2004) 286.
- 13) S. Paschen, T. L  hmann, S. Wirth, P. Gegenwart, O. Trovarelli, C. Geibel, F. Steglich, P. Coleman, and Q. Si: Nature **432** (2004) 881.
- 14) P. Gegenwart, T. Westerkamp, C. Krellner, Y. Tokiwa, S. Paschen, C. Geibel, F. Steglich, E. Abrahams, and Q. Si: Science **315** (2007) 969.
- 15) S. Friedemann, N. Oeschler, S. Wirth, C. Krellner, C. Geibel, F. Steglich, S. Paschen, S. Kirchner, Q. Si, PNAS **107** (2010) 14547.
- 16) Y. Tokiwa, P. Gegenwart, C. Geibel, F. Steglich, J. Phys. Soc. Jpn. **78** (2009) 123708.
- 17) S. Friedemann, T. Westerkamp, M. Brando, N. Oeschler, S. Wirth, P. Gegenwart, C. Krellner, C. Geibel, and F. Steglich: Nature Phys. **5** (2009) 465.
- 18) J. Custers, P. Gegenwart, C. Geibel, F. Steglich, P. Coleman, S. Paschen, Phys. Rev. Lett. **104** (2010) 186402.
- 19) M. Vojta, Phys. Rev. B **78** (2008) 125109.
- 20) O. Trovarelli, J. Custers, P. Gegenwart, C. Geibel, P. Hinze, S. Mederle, G. Sparn, F. Steglich, Physica B **312-313** (2002) 401.
- 21) G. Knebel, R. Boursier, E. Hassinger, G. Lapertot, P.G. Niklowitz, A. Pourret, B. Salce, J.P. Sanchez, I. Sheikin, P. Bonville, H. Harima, J. Flouquet, J. Phys. Soc. Jpn. **75** (2006) 114709.
- 22) P. Gegenwart, T. Westerkamp, C. Krellner, M. Brando, Y. Tokiwa, C. Geibel, F. Steglich, Physica B **403** (2008) 1184.