




Exploring strong electronic correlations in the breathing kagome metal Fe₃Sn

Shivalika Sharma, Liviu Chioncel, Igor Di Marco

Angaben zur Veröffentlichung / Publication details:

Sharma, Shivalika, Liviu Chioncel, and Igor Di Marco. 2025. "Exploring strong electronic correlations in the breathing kagome metal Fe₃Sn." *Physical Review B* 111 (23): 235127. <https://doi.org/10.1103/xmmr-mfv4>.

Exploring strong electronic correlations in the breathing kagome metal Fe₃SnShivalika Sharma ^{1,*}, Liviu Chioncel ^{2,3} and Igor Di Marco ^{1,4,†}¹*Institute of Physics, Nicolaus Copernicus University, 87-100 Toruń, Poland*²*Theoretical Physics III, Center for Electronic Correlations and Magnetism, Institute of Physics, University of Augsburg, 86135 Augsburg, Germany*³*Augsburg Center for Innovative Technologies, University of Augsburg, 86135 Augsburg, Germany*⁴*Department of Physics and Astronomy, Uppsala University, Uppsala 751 20, Sweden*

(Received 5 January 2025; revised 3 April 2025; accepted 15 May 2025; published 16 June 2025)

Kagome metals have emerged as pivotal materials in condensed matter physics due to their unique geometric arrangement and intriguing electronic properties. Understanding the origin of magnetism in these materials, particularly in iron-rich Fe-Sn binary compounds such as Fe₃Sn, holds a significant importance, as they represent potential candidates for permanent magnets with a high Curie temperature and a strong magnetic anisotropy. In the present study, we employ density functional theory and dynamical mean-field theory to analyze the electronic structure and magnetic properties of Fe₃Sn. Our investigation reveals the presence of several nearly flat bands and Weyl nodes at low excitation energies. The inclusion of local correlation effects is shown to push these features even closer to the Fermi energy, which may be important for their manipulation via external stimuli. Regarding magnetism, the Hubbard-like interaction leads to an increase of orbital polarization at the expenses of a minor reduction of the spin moment. The magnetic anisotropy energy exhibits a strong dependence on the particular choice of the Coulomb interaction parameters. Additionally, our detailed analysis of the interatomic exchange interactions indicates a significant contribution from the antisymmetric exchange, i.e., the Dzyaloshinskii-Moriya interaction, which showcases the existence of magnetic chirality in the system. Overall, our investigation highlights a strong interplay between the flat bands near the Fermi level, the local Coulomb interaction, and the triangular geometry of the lattice, which plays a crucial role in driving the magnetic properties of this material.

DOI: [10.1103/xmmr-mfv4](https://doi.org/10.1103/xmmr-mfv4)

I. INTRODUCTION

The exploration of kagome lattices has garnered significant interest in condensed matter physics due to their unique geometric configuration that leads to exotic physical phenomena [1,2]. These lattices are characterized by a pattern of interlaced triangles that create a complex network of hexagons and have emerged as a playground for studying the interplay of electronic topology, strong correlations, and magnetism [1–3]. Kagome materials such as AV₃Sb₅ ($A = \text{K, Cs, Rb}$) [4–7] and Co₃Sn₂S₂ [8–10] were found to host flat bands and Weyl nodes near the Fermi level. Similar features were also reported for the binary metals T_xSn_y ($T = \text{Fe, Mn, Co}$; $x:y = 1:1, 3:2, 3:1$) [11–15]. These characteristics make kagome materials an intriguing platform to witness many exotic phenomena such as topological Hall and Nernst effects, unconventional superconductivity, ferromagnetism, magnetic spin chirality, magnetic skyrmions, and more [1,2].

The physics of the kagome lattice is further enriched by the possibility of departing from the ideal geometry, allowing for a trimerization that breaks the inversion symmetry. This unique geometry of unequal corner-sharing triangles, known as the breathing-kagome lattice, is fascinating due to its potential to host higher-order topological insulators and to exhibit unique magnetic properties [16,17]. Fe₃Sn₂ provides a material realization of the breathing-kagome lattice, with stanene layers sandwiched between Fe₃Sn bilayers, thus creating a quasi-two-dimensional system. Following reports of a large anomalous Hall effect, a giant magnetic tunability and the presence of skyrmions bubbles, further research on Fe₃Sn₂ suggested the presence of flat bands, massive Dirac fermions, and a very large Berry curvature in the kagome plane [12]. More detailed experiments via angle-resolved photoemission spectroscopy (ARPES) demonstrated that these Dirac fermions have a dominant contribution from the surface states and Fe₃Sn₂ behaves instead as a magnetic Weyl semimetal [18]. Ferromagnetism, reported up to a critical temperature of 670 K, was connected to the presence of flat bands that extend over large sections of the Brillouin zone [13]. The flat bands owe their existence to destructive wave interference—a direct consequence of the unique kagome lattice structure. This interference leads to a quenching of the kinetic energy, making the effect of the electron-electron interaction particularly significant [19]. For Fe₃Sn₂, the exchange mechanisms arising from flat bands have been inter-

*Contact author: shivalika.sharma@umk.pl

†Contact author: igor.dimarco@physics.uu.se;
igor.dimarco@umk.pl

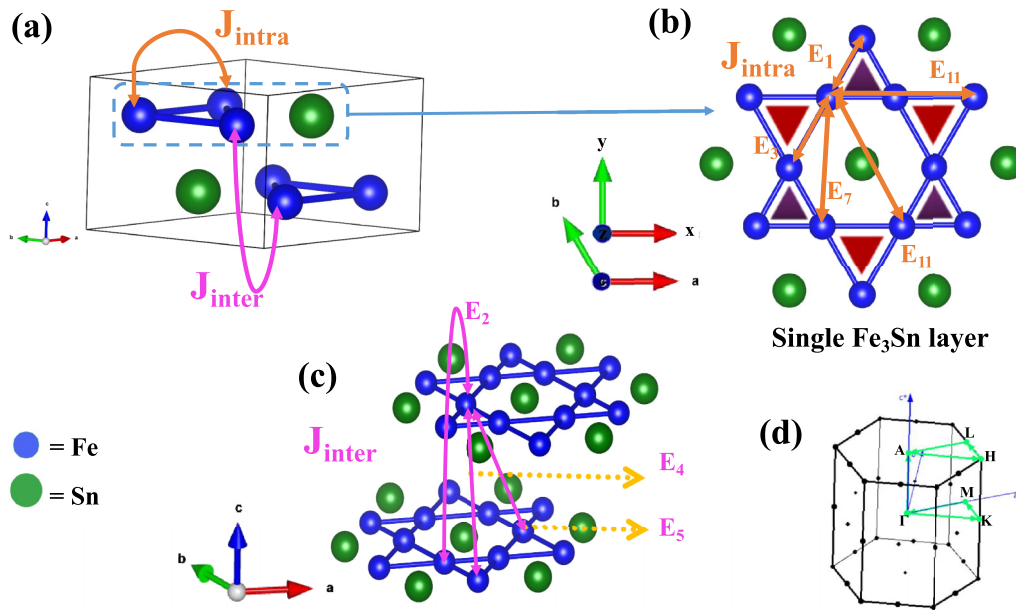


FIG. 1. (a) Illustration of the Fe_3Sn unit cell, highlighting interatomic exchange paths between two Fe atoms. (b) A single kagome layer (Fe_3Sn), consisting of two differently sized equilateral triangles (indicated in dark red and violet), with selected intralayer exchange paths. (c) Stacking of two kagome layers in the $P6_3/mmc$ structure, with selected interlayer exchange paths. (d) The Brillouin zone of the hexagonal kagome lattice showing paths connecting high-symmetry points.

preted [13] as a coexistence of Mielke’s ferromagnetism [20] and Nakaoka-type ferromagnetism [21].

Flat bands also arise in other Fe-Sn binary systems. FeSn is a metastable material with a simpler stacking, composed of isolated (ideal) kagome planes [14]. Termination-dependent ARPES measurements detected two-dimensional Dirac cones and flat bands that extend over the full Brillouin zone [14]. Conversely, three-dimensional features emerge in the breathing-kagome material Fe_3Sn . This compound was the first extensively studied system among Fe-Sn binaries, due to a stable ferromagnetic order with a Curie temperature of 705 K and a large magnetic anisotropy energy (MAE) [22–24]. Although these characteristics would make Fe_3Sn an ideal candidate as a component for rare-earth free permanent magnets, the easy axis does not lay along the c crystallographic axis, but inside the kagome plane [25]. This *de facto* easy plane is not suitable for magnetic applications. Alloying with Sb, As, and Te and nanostructuring have been explored as possible pathways to rotate the easy axis to be perpendicular to the kagome plane, but this approach has had limited success due to the high sensitivity of the MAE to compositional parameters and electron or hole doping [25]. More recent works have pointed out that Fe_3Sn hosts a large anomalous Hall effect [3,26,27] and a large anomalous Nernst effect [28]. These topological features can be connected to the presence of a nodal plane composed of two nearly flat bands closely facing each other in the two-dimensional plane [15,28]. Since the stacking of Fe_3Sn forms a genuine three-dimensional network rather than isolated planes, a comprehensive understanding of its electronic structure from first principles becomes crucial. This also includes the analysis of strong electronic correlations, whose importance for kagome-based materials has been recently emphasized by a theoretical study on $\text{Sc}_3\text{Mn}_3\text{Al}_7\text{Si}_5$

[29], as well as by high-resolution laser-based microfocused ARPES measurements on Fe_3Sn_2 [30].

In the present study, we have performed an extensive analysis of the electronic and magnetic properties of bulk Fe_3Sn , based on a combination of density functional theory (DFT) [31] and dynamical mean-field theory (DMFT) [32]. This DFT + DMFT approach [33,34] is employed to understand how strong electronic correlations affect the behavior of the flat bands in different parts of the Brillouin zone. The calculation of the interatomic exchange parameters between local moments at the Fe sites makes it possible to connect these effects to the strength of the magnetic coupling. The paper is organized as follows. After this introduction, the methodology of our work is presented in Sec. II. The results of our research are then illustrated in Sec. III and Sec. IV, respectively, for the magnetic properties and the details of the electronic structure. Finally, the conclusions of our work are presented in Sec. V.

II. METHODOLOGY

We have considered the bulk crystal structure of Fe_3Sn , consisting of layers of Fe and Sn in the A-B stacking, as shown in Fig. 1(a). It has a space group of $P6_3/mmc$, with Fe atoms forming the kagome lattice and Sn atoms residing in the center of the hexagon, on a different plane along the c crystallographic axis. The structural data used for the calculations were taken from experiments on single-crystal samples [24]. The corresponding lattice parameters are $a = b = 5.4604 \text{ \AA}$ and $c = 4.3458 \text{ \AA}$, while the breathing distortion gives a ratio of approximately 0.86 between the sides of the smaller and larger triangles. These triangles of different sizes, emphasized by red and violet shades in Fig. 1(b), are the fundamental components of the breathing-kagome lattice, corresponding to a single Fe_3Sn layer. DFT and DFT +

DMFT calculations were performed by using the full potential linear muffin-tin orbital method (FP-LMTO) as implemented in the Relativistic Spin-Polarized Toolkit (RSPT) code [35,36]. The generalized gradient approximation (GGA) was used for the exchange-correlation functional, based on the Perdew and Wang functional with Perdew-Burke-Ernzerhof (PBE) corrections [37–39]. For the DFT + DMFT calculations, the effective impurity problem has been solved through the spin-polarized T -matrix fluctuation-exchange (SPTF) solver [40], in its spin- and orbital-rotationally invariant formulation [41,42]. SPTF is a perturbative solver that works well for magnetic systems with moderate correlations, but is not adequate for strong many-body effects such as those associated to the formation of fluctuating local moments in the paramagnetic phase [43], the emergence of Kondo physics [44], or the Mott metal-to-insulator transition [45]. SPTF has proved to be very successful in describing electronic and magnetic properties of transition-metal elements and compounds, including itinerant ferromagnets [42,46,47], half-metallic ferromagnets [48], two-dimensional magnets [49], high-entropy alloys [50], as well as kagome systems with complex magnetic textures [6,7]. Thus, we expect SPTF to be perfectly adequate to describe Fe_3Sn as well. Like in our previous studies, the dynamical self-energy is obtained as a function of the renormalized Hartree-Fock Green's function [6,7]. Moreover, when the effective impurity problem is solved in the Hartree-Fock approximation, we recover the DFT + U approach [33,51]. The double-counting term for DFT + U is chosen as the around-mean-field (AMF) correction [33,51]. For DFT + DMFT, the orbital average of the static part of the self-energy is used [47], which reduces to the AMF correction if only Hartree-Fock terms are included. The basis of the local orbitals is constructed by considering only the muffin-tin heads, as described in Ref. [42]. The Coulomb interaction term, to be solved in DFT + U and DFT + DMFT, is applied to the Fe-3d states only, using the aforementioned basis. Regarding the Coulomb interaction parameters, no estimates can be found in the literature specifically for Fe_3Sn . Since bandwidth and band filling are not too different from those of bulk bcc Fe, we decided to employ the Coulomb interaction parameters used in the past studies for this system [41,52,53]. Hence, the Hubbard U and the Hund exchange J to be used in DFT + DMFT have been set to 2.3 and 0.9 eV. These values are also compatible with recent calculations made for FeSn by means of the constrained random phase approximation (cRPA) [54]. While the Hubbard U predicted there is slightly higher (3 eV), one should keep in mind that the hybridization in Fe_3Sn is larger due to the presence of a stronger out-of-plane coupling. For DFT + U calculations, the aforementioned values have been decreased to 1.5 and 0.8 eV, to account for the fact that in the Hartree-Fock solution, there is no dynamical screening [55]. This reduction is somehow arbitrary, but it is necessary to have a meaningful comparison with DFT + DMFT. Nevertheless, this arbitrariness implies that the comparison between DFT + U and DFT + DMFT can only be made at a qualitative level. Other choices for U and J have been explored, as commented throughout the text. The spectral functions are calculated via Green's function theory at a distance of 13 meV from the real energy axis [41], unless stated otherwise. The analytical continuation was performed directly on the self-

energy function by means of the revised Padé approximant method [56].

Converged electronic structure calculations from DFT, DFT + U , and DFT + DMFT are then utilized to extract interatomic exchange parameters J_{ij} by mapping the magnetic excitations onto to an effective Heisenberg Hamiltonian [57],

$$H = - \sum_{i \neq j} J_{ij} \vec{e}_i \cdot \vec{e}_j. \quad (1)$$

Here, (i, j) are the indices for atomic sites hosting the magnetic moments, while \vec{e}_i and \vec{e}_j are unit vectors along the spin direction at sites i and j , respectively. The J_{ij} are calculated as the response to an infinitesimal rotation of two spins at sites i and j , by means of a generalized magnetic force theorem [57,58]. In the presence of spin-orbit coupling (SOC), the interatomic exchange becomes anisotropic and Eq. (1) can be rewritten in a tensorial form, which can be recast as [59]

$$H = - \sum_{i \neq j} J_{ij} \vec{e}_i \cdot \vec{e}_j - \sum_{i \neq j} \mathbf{e}_i^T \mathbb{J}_{ij}^S \mathbf{e}_j - \sum_{i \neq j} \vec{D}_{ij} \cdot (\vec{e}_i \times \vec{e}_j). \quad (2)$$

Here, the first term is the isotropic exchange interaction corresponding to Eq. (1), the second term is the symmetric anisotropic exchange, and \mathbb{J}_{ij}^S is the symmetric anisotropic exchange tensor. The third term is the antisymmetric anisotropic exchange, also known as the Dzyaloshinskii-Moriya (DM) interaction [60,61]. The scalar triple product is written in terms of the DM vector \vec{D}_{ij} , whose explicit expression can be found in Ref. [62]. Usually the strength of the DM interaction is discussed with respect to the magnitude of the DM vector,

$$|\vec{D}_{ij}| = \sqrt{(D_{ij}^x)^2 + (D_{ij}^y)^2 + (D_{ij}^z)^2}, \quad (3)$$

where \vec{D}^x , \vec{D}^y , and \vec{D}^z are the directional components of \vec{D}_{ij} along the Cartesian axes. In our reference frame, the crystallographic directions are arranged to have x and z parallel to a and c , respectively, as also shown in Fig. 1(b). Finally, the sampling of the Brillouin zone was performed by a dense Monkhorst-Pack grid of $24 \times 24 \times 24$ \mathbf{k} points, in order to ensure the convergence of the interatomic magnetic exchange coupling. All calculations were performed for a temperature of 200 K.

III. MAGNETIC PROPERTIES

Previous computational works have demonstrated that the ground state of Fe_3Sn is ferromagnetic with an easy plane [22,25]. Our DFT calculations confirm these results and predict a MAE of 0.64 meV per formula unit between the easy axis (100) and the hard axis (001). In the easy plane, the calculated energy differences amount to less than 2 μeV . Such small differences are expected due to the hexagonal symmetry, which makes spin orientations within the a - b plane energetically degenerate. The MAE resulting from our calculations, which in different units amounts to 1.8 MJ/m³, is in perfect agreement with the value reported in the recent work by Belbase *et al.*, based on the full-potential

TABLE I. Total magnetic moments per formula unit and site-projected spin and orbital moments for bulk Fe₃Sn, as computed in DFT, DFT+*U*, and DFT+DMFT, using the default (def.) Coulomb interaction parameters, as well as reduced (red.) values $U = 2.0$ eV and $J = 0.65$ eV. The values are given in μ_B .

	μ_{tot}	μ_{Fe}^s	μ_{Fe}^o	μ_{Sn}^s	μ_{Sn}^o
DFT	7.14	2.45	0.07	-0.11	0.00
DFT+ <i>U</i>	6.93	2.34	0.12	-0.13	0.00
DFT+DMFT (def.)	6.82	2.31	0.10	-0.12	0.00
DFT+DMFT (red.)	6.93	2.35	0.09	-0.12	0.00

local-orbital (FPLO) method [3]. Other theoretical studies [3,22–24] predicted values that range from 1.3 to 1.6 MJ/m³, which is slightly larger than the discrepancy that one may expect nowadays from electronic structure calculations [63]. This discrepancy has already been pointed out as a consequence of the high sensitivity of the MAE to the c/a ratio, which may greatly amplify minor structural differences, as, e.g., due to structural optimization or experimental input [3,25]. The most recent experimental results on single crystals [24,26] estimate the MAE to be around 1.0 MJ/m³ at room temperature and then to increase up to 1.3 MJ/m³ at 2 K. These values are from 30% to 40% smaller than the number we obtained from electronic structure calculations. A similar discrepancy characterizes the saturation magnetization, whose measurements give values in the range of 6.6–6.8 μ_B per formula unit [23,24,26]. Our DFT calculations give a slightly larger value amounting to 7.1 μ_B per formula unit, which is in perfect agreement with previous theoretical studies [3,22–26]. Site-projected magnetic moments are reported in Table I, including also spin and orbital decompositions. These data show that the Fe and Sn spin moments are antiparallel to each other and that the contribution of the orbital magnetism is rather small, in agreement with the itinerant metallic character of this material. These values are in excellent agreement with those obtained in FPLO calculations, especially if we take into account the usage of different sets of local orbitals for the site projections [23].

Next, we focus on how the magnetic properties are affected by the inclusion of an explicit Hubbard interaction term, via DFT + *U* and DFT + DMFT. Regarding the MAE, the value obtained from the DFT + *U* calculations amounts to 2.4 MJ/m³. This increase with respect to the DFT result is mainly driven by the increase in the orbital polarization of the Fe-3*d* states, as evident from Table I. These results are consistent with the even larger MAE that was recently obtained [3] through the inclusion of the orbital-polarization correction [64]. The rise of the orbital moment observed in Table I is accompanied by a small decrease of the spin moment, which is a consequence of the very definition of the AMF double counting for DFT + *U* [65]. The balance between spin and orbital magnetism is supposed to be better described when magnetic fluctuations that go beyond the static mean-field approximation are included [33,42]. The DFT + DMFT results reported in Table I show that dynamical correlation effects drive a further decrease of the spin moment, but also reduce the orbital moment with respect to the DFT + *U* values. The

MAE calculated with these (default) settings is, however, extremely large, amounting to 5.9 MJ/m³. Additional calculations reveal that the MAE estimated from DFT + DMFT is very sensitive to small variations of the Coulomb interaction parameters, in particular the Hund’s exchange J . If the chosen parameters, namely, $U = 2.3$ eV and $J = 0.9$ eV, are decreased to $U = 2.0$ eV and $J = 0.65$ eV, then the MAE reduces to 1.3 MJ/m³, in agreement with the experiment, while the spin and orbital moments become closer to the original DFT values; see Table I. More comprehensive data on the dependence of the MAE on the Coulomb interaction parameters are presented in the Supplemental Material (SM) [66]. Overall, the large variations of the MAE may have a methodological origin, reflecting, e.g., the deficiencies of approaches where the Hubbard correction is applied on top of a spin-polarized DFT description [49,67,68]. Alternatively, they may have a physical origin, connecting to the high sensitivity of the MAE to small structural differences, as emphasized above. The latter interpretation would be in line with the expectation of a strong interplay between electronic correlations, magnetism, and topology on the unique kagome geometry [6,29,30,69,70]. Recent findings on FeSn, approaching the limit of a two-dimensional kagome lattice, have also emphasized orbital-selective physics driven by the Hund’s exchange, in analogy to iron-based superconductors [71]. Finally, the reduction of the total magnetic moment observed in both DFT + *U* and DFT + DMFT with respect to DFT is also more consistent with the measured saturation magnetization of 6.6–6.8 μ_B per formula unit [23,24,26].

Having established the basic properties of the magnetic ground state, we proceed to the analysis of the interatomic exchange coupling, according to Eq. (2). In the Fe₃Sn unit cell shown in Fig. 1(a), we highlight the difference between the two fundamental groups of exchange interactions, namely, the intralayer terms J_{intra} and the interlayer terms J_{inter} . The most important exchange paths E_n between two Fe atoms are illustrated in Fig. 1(b) and Fig. 1(c), for J_{intra} and J_{inter} , respectively. The index n labels the shell of nearest neighbors (NNs), ordered with respect to their interatomic distance. With this in mind, we can inspect the plots of the isotropic averages and the DM interaction as a function of the interatomic distance, reported in Fig. 2. In standard DFT, the isotropic exchange interaction for the first four shells of NNs is markedly ferromagnetic, in agreement with what we have discussed above. The exchange coupling for the first NN shell is the largest and corresponds to the intralayer path E_1 , connecting two Fe atoms in the smaller triangle of the breathing kagome. The coupling between Fe atoms in the larger triangle, along the path E_3 , is about 30% smaller than the first NN value. The second and fourth NNs are located along the interlayer paths E_2 and E_4 , and yet they also exhibit a substantial ferromagnetic coupling, in agreement with the fact that the distance between the kagome planes (2.61 Å) is comparable to the side of the triangles in the breathing kagome (2.52 and 2.93 Å). The exchange interaction of the first four shells of NNs quantitatively demonstrates that magnetism in Fe₃Sn arises from a full three-dimensional network, in agreement with the experimental trends of the Fe stannides [14,23,28]. The first antiferromagnetic coupling emerges for the fifth shell of NNs, along the interlayer path E_5 , shown in Fig. 1(c). For larger interatomic

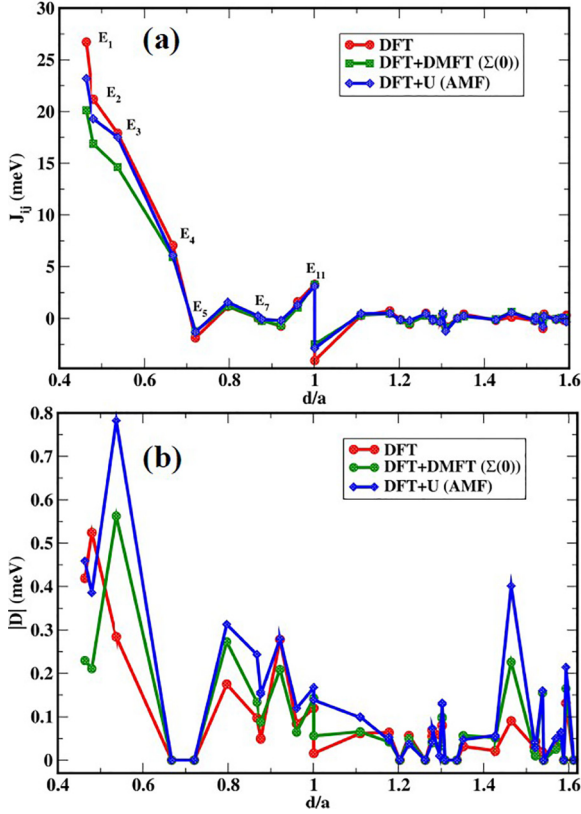


FIG. 2. (a) Isotropic averages of the exchange tensor as a function of the distance between Fe atoms. (b) The magnitude of the DM vector as a function of the distance between Fe atoms. Calculations are done with RSPT in DFT, DFT + DMFT, and DFT + U with the inclusion of SOC.

distances, the system exhibits a long-range oscillatory behavior that is reminiscent of the Ruderman-Kasuya-Kittel-Yosida (RKKY) interaction [72]. In Fig. S2 of the SM [66], we show that in standard DFT, the interatomic exchange interaction approximately scales as the cube of the interatomic distance d . This scaling is precisely what is expected from RKKY coupling in a three-dimensional system [72] and offers a definitive support to the three-dimensional nature of the ferromagnetism in Fe_3Sn . A more quantitative theory of the RKKY oscillations would require an analysis of the caliper vectors defined in the Fermi surface, as in Ref. [73], but this is beyond the scope of the present article. Interestingly, the role of the RKKY coupling in layered topological semimetals has been recently pointed out, albeit for noncoplanar magnetism involving different sublattices [74]. Going back to the analysis of Fig. 2(a), competing ferromagnetic and antiferromagnetic interactions are visible for the 11th shell of NNs, indicating the presence of frustration in the system due to its structural geometry, which leads to two different paths E_{11} , as depicted in Fig. 1(b).

The amplitude of the DM vector as a function of the interatomic distance is shown in Fig. 2(b), while the components D^x , D^y , and D^z for selected exchange paths are given in Table II. The largest coupling is interlayer, connecting Fe atoms along the path E_2 , and amounts to 0.52 meV, mostly arising from its D^z component. Inside the kagome plane, the first and

TABLE II. Components of the DM vector along the Cartesian axes as depicted in Fig. 1, as calculated in DFT, DFT+DMFT, and DFT+ U by RSPT. All values are given in meV.

Exchange path	DM vector	DFT	DFT+DMFT	DFT+ U
E_1	D^x	0	0	0
	D^y	0	0	0
	D^z	0.41	0.22	0.50
E_2	D^x	-0.08	-0.05	-0.05
	D^y	0.04	0.02	0.02
	D^z	0.51	0.19	0.36
E_3	D^x	0	0	0
	D^y	0	0	0
	D^z	0.28	0.56	0.78
E_6	D^x	-0.16	-0.27	-0.31
	D^y	0	0	0
	D^z	0	0	0
E_9	D^x	0.09	0.09	0.13
	D^y	0.16	0.17	0.23
	D^z	0.19	0.05	0.07

second shells of NNs are characterized by slightly smaller DM vectors, whose major contributions still come from the D^z component. These finite values of the DM interaction indicate the tendency for chirality between two Fe sites with the preferred direction for the DM vector along the z axis (out of plane). The magnitude of the DM interaction is relatively small ($\sim 3\text{--}4\%$) compared to the isotropic Heisenberg exchange tensor, making the likelihood of spin canting quite low [75]. Definitive confirmation of collinear order would require the solution of the effective Heisenberg Hamiltonian defined by Eq. (2), which would be an interesting task for future works involving multiscale modeling [76]. Furthermore, we see that $|D|$ for the fourth- and fifth-NN shells is zero because of the presence of inversion symmetry, as evidenced by the interlayer exchange paths E_4 and E_5 depicted in Fig. 1(c).

The inclusion of an explicit Hubbard term via DFT + U and DFT + DMFT leads to a small reduction of the isotropic exchange, as shown in Fig. 2(a). This reduction reflects the smaller values of the Fe spin moments reported in Table I through the definition used in Eq. (2). By inspecting the projected density of states (PDOS) for the Fe-3d states, depicted in Fig. 3, we observe that the exchange splitting is largest in DFT and smallest in DFT + DMFT, in agreement with the trends of the magnetic moments and interatomic interactions. The overall reduction of the strength of the magnetic coupling in DFT + DMFT is similar to the one previously observed for bcc Fe [57,77]. Nevertheless, it is surprising that the DFT + U does not cause a stronger localization of the Fe-3d electrons, making the J_{ij} 's shorter ranged. Although a possible reason for the observed behavior may be the usage of smaller Coulomb interaction parameters in DFT + U , additional calculations demonstrate that this is not the leading factor (data not shown). In fact, the long-range nature is found to be a consequence of the AMF double counting, which is usually used for correlated metals [78]. To evaluate the impact of the double counting, we performed additional electronic structure calculations in DFT + U in the fully localized limit (FLL), while keeping the other settings unchanged. As expected, a

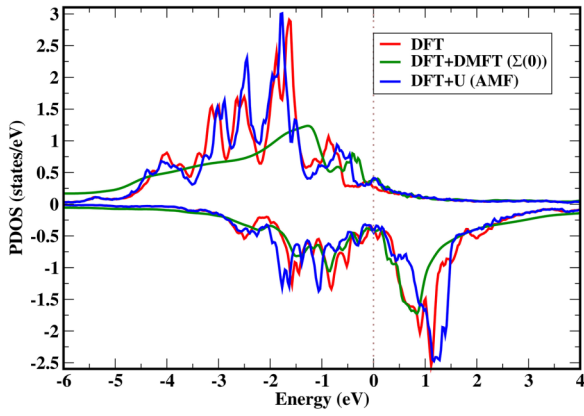


FIG. 3. PDOS of Fe-3d states as obtained in DFT, DFT + DMFT, and DFT + U via RSPT. The Fermi level is located at zero energy.

much stronger electronic localization is observed, resulting in an increase of the exchange splitting (data not shown), a higher local magnetic moment of $2.54 \mu_B$, and an increase of the first-NN coupling up to 31 meV. This magnetic moment deviates significantly from the experimentally reported values, which demonstrates that the FLL double counting is not suitable for describing this system, as usual for itinerant ferromagnets [78].

The inclusion of the on-site Coulomb interaction via DFT + DMFT and DFT + U leads to significant qualitative and quantitative changes in the DM interaction. For both methods, Fig. 2(b) shows a marked increase in the value of $|D|$ for the third shell of NNs, corresponding to the intralayer exchange path E_3 . The first shell of NNs, along the intralayer exchange path E_1 , exhibits a more complex trend, as the DM interaction increases in DFT + U but decreases in DFT + DMFT. The dominant character of the intralayer terms remains D^z , compatibly with the symmetry of the kagome lattice. The DM interaction with the second shell of NNs, along the exchange path E_2 , decreases for both DFT + U and DFT + DMFT, an effect driven mainly by a change in D^z . Notably, there is also a significant increase in the magnitude of the DM interaction with farther NNs, as, e.g., in the sixth and ninth shells, which we attribute to a stronger orbital polarization driven by the inclusion of the on-site Coulomb interaction. These data, and in particular the decomposition shown in Table II, suggest deeper changes in the electronic structure than those observed from the PDOS of Fig. 3. We will investigate these changes in the next section.

For completeness, we also calculated the values of the interatomic exchange interactions for the nonrelativistic case, corresponding to Eq. (1). As illustrated in Fig. S1 of the SM [66], the isotropic exchange is only marginally affected by the presence of SOC, and the primary consequence of the latter is to induce anisotropic terms as the DM interaction, favoring spin canting and complex magnetic textures [7].

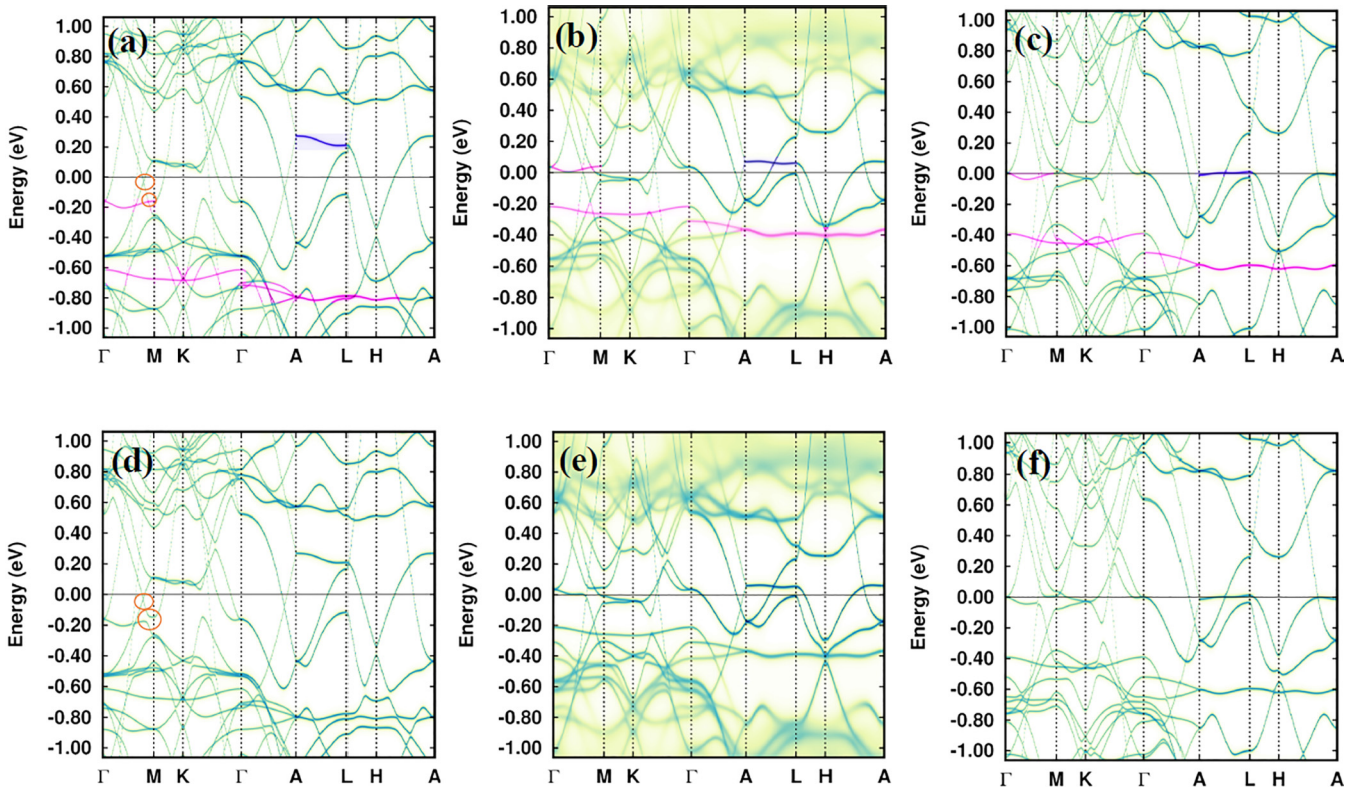


FIG. 4. Spectral function of Fe_3Sn as obtained in (a),(d) DFT, (b),(e) DFT + DMFT, and (c),(f) DFT + U . (a)–(c) Calculations without SOC and (d)–(f) calculations with SOC, for the magnetization along the easy axis (100). The magenta and blue colors are used to highlight the nondispersive bands with majority and minority spin character, respectively. The orange circles show the possible Weyl nodes for this specific magnetization direction.

IV. DETAILS OF THE ELECTRONIC STRUCTURE

The spectral functions along high-symmetry directions in the Brillouin zone are reported in Fig. 4 for DFT, DFT + DMFT, and DFT + U , with and without the inclusion of SOC. As in the previous section, the data for SOC are shown for a magnetization along the easy axis (100). Focusing on the DFT results, shown in Figs. 4(a) and 4(d), we see the presence of several bands with a relatively flat dispersion near the Fermi level. For convenience, we highlighted those bands in magenta and blue, reflecting their spin character. In agreement with the study by Belbase *et al.* [3], we observe two bands spanning a larger portion of the Brillouin zone, i.e., the band at -0.6 eV along Γ - M - K - Γ and the band at -0.8 eV along A - L - H - A . The orbital-projected spectral functions, reported in the SM [66], allow us to identify the dominant character of these bands. The local projectors are constructed by real spherical harmonics defined on a rotated reference frame $\tilde{x} \tilde{y} \tilde{z}$, where \tilde{z} lays in the kagome plane and points toward the neighboring Sn atom, as illustrated in Fig. S3 of the SM [66]. This choice is analogous to the one used for $\text{Sc}_3\text{Mn}_3\text{Al}_7\text{Si}_5$ in a very recent DFT + DMFT study [29]. With the help of these data, we can establish that the flat band at -0.6 eV has mostly $d_{\tilde{x}\tilde{z}}|d_{\tilde{y}\tilde{z}}$ majority-spin character, which is consistent with recent results on the related breathing-kagome material Ni_3In [79]. This can be easily verified through a further rotation of the local orbitals to match the two reference frames. The other flat band, at -0.8 eV, exhibits a similar character, but also has a substantial contribution from $d_{\tilde{x}^2-\tilde{y}^2}|d_{\tilde{x}\tilde{y}}$ majority-spin states, in particular between L and H . Along the same high-symmetry directions, one can also observe the corresponding minority-spin bands at higher energies, namely, 1.6 and 1.4 eV; see Fig. S10 of the SM [66]. Another notable flat band can be observed at -1.2 eV, mainly of $d_{\tilde{x}\tilde{z}}|d_{\tilde{y}\tilde{z}}$ minority-spin character. Due to the strong interlayer coupling between the two kagome layers [13,80], these flat bands do not extend over the entire Brillouin zone, but acquire a strong dispersion along the Γ - A direction. In Fig. 4(a), we also observe another set of nondispersive bands extending along smaller segments of the Brillouin zone, mainly at smaller excitation energies. The two bands, highlighted in blue at about 50 and 200 meV, come from the states determining the nodal plane between the U^* points, which was suggested to drive a large anomalous Nernst effect, 10 times larger than for pure Fe [15]. For these bands, the hybridization between the Fe- $3d$ states and Sn- $5p$ states becomes more important, as it can be inferred from comparing the corresponding orbital-projected spectral functions in Figs. S4 and S7 of the SM [66]. In general, the presence of flat bands has been linked to the formation of ferromagnetic order in Fe stannites, especially for the analysis of Fe_3Sn_2 , whose kagome features are enhanced by its quasi-two-dimensional nature [13,19,81]. In Fe_3Sn , the role played by the flat bands and other nondispersive states in the long-range order is expected to be less crucial due to the three-dimensional magnetism emphasized above. Moreover, the analysis of Fig. 4(a) as well as the orbital projections reported in the SM [66] has shown that the carriers mediating the exchange coupling belong to hybridized $3d$ - $5p$ states having a marked itinerant character, at least in DFT.

The inclusion of SOC does not significantly alter the shape and position of the nondispersive bands, but results in gap opening at the band-crossing points, which we highlighted in orange in Fig. 4(d). This means that the Weyl nodes move away from the high-symmetry directions, as recently demonstrated by Belbase *et al.* [3]. These points were suggested to be the cause of the large anomalous Hall conductivity observed in experiment [69], but electronic structure calculations indicate more structured contributions across the entire Brillouin zone [3]. By changing the magnetization axis to the hard axis (001), we observe a notable band splitting close to the Fermi level, as shown in Figs. S8 and S9 of the SM [66]. This splitting stems from the dependence of the electron scattering on the spin orientation and differs from the Zeeman splitting. This phenomenon is recognized as the giant magneto band structure effect, as discussed in the literature for two-dimensional CrI_3 [82]. Furthermore, we observe that the distribution of the gap openings significantly depends on the magnetization direction. This difference is connected to a different shift of the Weyl nodes under SOC, regarding both energy and location in the Brillouin zone [3,83].

Next, we focus on the band structure (spectral function) obtained in DFT + DMFT, shown in Figs. 4(b) and 4(e). Due to the imaginary part of the self-energy, the quasiparticles acquire a finite lifetime which makes the energy bands well defined only for energies close to the Fermi level, consistently with the Fermi liquid theory [41]. This is also evident from the PDOS shown in Fig. 3, where no structure can be resolved below -2 eV and above 2 eV. The real part of the self-energy renormalizes the DFT eigenvalues, which is particularly evident in Fig. 4(b) for the nondispersive bands highlighted in blue, which move much closer to the Fermi level. A similar renormalization has been reported recently for other kagome metals, such as Mn_3Sn [84] and AV_3Sb_5 ($A = \text{K}, \text{Cs}, \text{Rb}$) [6]. The proper flat bands, highlighted in red, also move closer to the Fermi level. All these shifts are due to the combination of Fermi liquid renormalization, which induces a band narrowing [85], and a rigid shift of the Fe- $3d$ orbitals, driven by a larger orbital polarization and a decreased spin splitting, as emphasized in Sec. III. To compare these two effects, we can inspect the results obtained in DFT + U , shown in Figs. 4(c) and 4(f). Since these plots do not contain the effect of Fermi liquid renormalization, we can conclude that the latter is quite substantial in the correlated electronic structure obtained from DFT + DMFT, at least in reference to the energy scale we are focusing on. By extracting the quasiparticle weight from the self-energy, we obtain a mass renormalization m^*/m_e of 1.31 for majority spin and 1.25 for minority spin. These values are in line with those obtained for ferromagnetic kagome metals such as AV_3Sb_5 ($A = \text{K}, \text{Cs}, \text{Rb}$) [6,86,87] and ScV_6Sn_6 [88], but are slightly smaller than those expected for Mn_3Sn [29,84]. This is consistent with previous findings that the magnetic fluctuations in Mn tend to be larger than in Fe, as the former is closer to having a half-filled $3d$ shell [43,47]. For completeness, the orbital-decomposed renormalization is reported in Table III.

Interestingly, for both DFT + DMFT and DFT + U , the band segments along Γ - M and M - K are predicted to cross

TABLE III. Mass renormalization m^*/m_e as calculated in DFT+DMFT using the default Coulomb interaction parameters, as well as reduced values $U = 2.0$ eV and $J = 0.65$ eV, which were shown to provide a good quantitative agreement for the MAE.

Setup	Spin	d_{z^2}	$d_{x^2-y^2} d_{xy}$	$d_{xz} d_{yz}$
Default	minority	1.29	1.27	1.21
Default	majority	1.25	1.32	1.34
Reduced	minority	1.20	1.18	1.15
Reduced	majority	1.16	1.19	1.20

the Fermi level, while those along A - L move at very small excitation energies. However, we should stress that this effect is very sensitive to the precise choice of the Coulomb interaction parameters. For example, the DFT + DMFT results for values of U and J that provide the optimal MAE, discussed in Sec. III, do not exhibit these changes (data not shown). This uncertainty, as well as having neglected defects of any sort, makes it impossible to provide a quantitative analysis of how far these nondispersive bands are going to be located from the Fermi level. Nevertheless, our results highlight the following fundamental aspects: (1) a series of nondispersive bands is located in the very vicinity of the Fermi level, and (2) these nondispersive bands are strongly affected by the local Coulomb repulsion. This suggests that one could induce a variety of Lifshitz transitions by a small modulation of external parameters, which could take the form of a small strain (to change the $3d$ bandwidth) or doping charge carriers (to change the position of the Fermi level). We believe that these aspects are behind the large sensitivity to doping and growth conditions exhibited by the magnetic properties, which have prevented the stabilization of the MAE along the out-of-plane direction [23]. Interestingly, the formation of unexpected hole pockets and band crossing analogous to the one observed here has recently been reported by laser-based microfocused ARPES measurements of Fe_3Sn_2 [30].

Finally, we focus on the spectral functions obtained in DFT + DMFT and DFT + U when SOC is included, as observed in Fig. 4(e) and Fig. 4(f), respectively. We can see that the band crossing closest to the M point, corresponding to a Weyl point in the analysis by Belbase *et al.* [3], moves off the high-symmetry direction, leading to the opening of a gap precisely at the Fermi level. Conversely, the band crossing close to it just moves to lower energies (-0.2 eV for both DFT + DMFT and DFT + U). This new configuration may alter the contributions of these points to the Berry curvature, thus bringing a quantitative change to the topological properties. This may provide another route to explain the remaining discrepancy reported between calculated and theoretical values for the anomalous Hall conductivity in both single crystals [3,26] and polycrystalline samples [15,83]. The changes induced in the interlayer coupling, visible through an additional crossing point along the Γ - A direction with respect to DFT, are likely behind the drastic increase of the Dzyaloshinskii-Moriya interaction, reported in Fig. 2(b).

V. CONCLUSIONS

In conclusion, we conducted a comprehensive theoretical investigation of the electronic structure and magnetic properties of the three-dimensional breathing-kagome ferromagnet Fe_3Sn , using DFT, DFT + DMFT, and DFT + U . We calculated both intralayer and interlayer magnetic exchange interactions between the magnetic moments at the Fe sites, along with their respective band structures (spectral functions). Our results show that DFT + DMFT can be used to accurately reproduce the experimentally reported value of the MAE and to determine the most important contributions to the ferromagnetic coupling, including the presence of a 2–3% anisotropic contribution in the form of the Dzyaloshinskii-Moriya interaction. When the local Coulomb interaction is considered explicitly, via DFT + DMFT and DFT + U , the quasiparticle spectra undergo significant changes, with a series of nondispersive bands moving closer to the Fermi energy and even crossing it. Albeit this last conclusion depends on the particular choice of Coulomb interaction parameters, which is difficult to ascertain from first principles, these results point to a high tunability of the magnetic response, already reported for Fe_3Sn_2 [18], and in line with the high sensitivity to doping and structural variations [23,25]. Overall, topological Lifshitz transitions are expected to be tunable by small stimuli, such as strain and doping, which may substantially affect the anomalous Hall and Nernst effects. A key prerequisite for clearly observing this tunability is that the system does not undergo a significant phase transition, as, e.g., due to emergent structural distortions or changes in the magnetic ground state.

ACKNOWLEDGMENTS

We would like to thank H. S. Kim, I. E. Brumboiu, L. Prodan, and V. Tsurkan for insightful discussions and technical help. Computational work was performed on resources provided by the National Academic Infrastructure for Supercomputing in Sweden (NAISS), partially funded by the Swedish Research Council through Grant Agreement No. 2022-06725. We also acknowledge the Polish high-performance computing infrastructure PLGrid for awarding this project access to the LUMI supercomputer, owned by the EuroHPC Joint Undertaking, hosted by CSC (Finland) and the LUMI consortium through Grant No. PLL/2023/04/016450. I.D.M. acknowledges financial support from the European Research Council (ERC), Synergy Grant FASTCORR, Project No. 854843, as well as from the STINT Mobility Grant for Internationalization (Grant No. MG2022-9386). L.C. acknowledges financial support from the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) through TRR 360, Project No. 492547816. This research is also part of the Project No. 2022/45/P/ST3/04247 co-funded by the National Science Center of Poland and the European Union's Horizon 2020 research and innovation program under the Marie Skłodowska-Curie Grant Agreement No. 945339.

DATA AVAILABILITY

The data that support the findings of this article are openly available [89].

- [1] J.-X. Yin, B. Lian, and M. Z. Hasan, Topological kagome magnets and superconductors, *Nature (London)* **612**, 647 (2022).
- [2] Q. Wang, H. Lei, Y. Qi, and C. Felser, Topological quantum materials with kagome lattice, *Acc. Mater. Res.* **5**, 786 (2024).
- [3] B. P. Belbase, L. Ye, B. Karki, J. I. Facio, J.-S. You, J. G. Checkelsky, J. van den Brink, and M. P. Ghimire, Large anomalous Hall effect in single crystals of the kagome Weyl ferromagnet Fe_3Sn , *Phys. Rev. B* **108**, 075164 (2023).
- [4] H. Zhao, H. Li, B. R. Ortiz, S. M. Teicher, T. Park, M. Ye, Z. Wang, L. Balents, S. D. Wilson, and I. Zeljkovic, Cascade of correlated electron states in the kagome superconductor CsV_3Sb_5 , *Nature (London)* **599**, 216 (2021).
- [5] K. Jiang, T. Wu, J.-X. Yin, Z. Wang, M. Z. Hasan, S. D. Wilson, X. Chen, and J. Hu, Kagome superconductors AV_3Sb_5 ($A = \text{K}, \text{Rb}, \text{Cs}$), *Natl. Sci. Rev.* **10**, nwac199 (2022).
- [6] M. N. Hasan, R. Bharati, J. Hellsvik, A. Delin, S. K. Pal, A. Bergman, S. Sharma, I. Di Marco, M. Pereiro, P. Thunström, P. M. Oppeneer, O. Eriksson, and D. Karmakar, Magnetism in AV_3Sb_5 ($A = \text{Cs}, \text{Rb}, \text{and K}$): Origin and consequences for the strongly correlated phases, *Phys. Rev. Lett.* **131**, 196702 (2023).
- [7] D. Karmakar, M. Pereiro, M. N. Hasan, R. Bharati, J. Hellsvik, A. Delin, S. K. Pal, A. Bergman, S. Sharma, I. Di Marco, P. Thunström, P. M. Oppeneer, and O. Eriksson, Magnetism in AV_3Sb_5 ($A = \text{Cs}, \text{Rb}, \text{K}$): Complex landscape of dynamical magnetic textures, *Phys. Rev. B* **108**, 174413 (2023).
- [8] D. F. Liu, A. J. Liang, E. K. Liu, Q. N. Xu, Y. W. Li, C. Chen, D. Pei, W. J. Shi, S. K. Mo, P. Dudin, T. Kim, C. Cacho, G. Li, Y. Sun, L. X. Yang, Z. K. Liu, S. S. P. Parkin, C. Felser, and Y. L. Chen, Magnetic Weyl semimetal phase in a kagomé crystal, *Science* **365**, 1282 (2019).
- [9] E. Liu, Y. Sun, N. Kumar, L. Muechler, A. Sun, L. Jiao, S.-Y. Yang, D. Liu, A. Liang, Q. Xu, J. Kroder, V. Süß, H. Borrmann, C. Shekhar, Z. Wang, C. Xi, W. Wang, W. Schnelle, S. Wirth, Y. Chen *et al.*, Giant anomalous Hall effect in a ferromagnetic kagome-lattice semimetal, *Nat. Phys.* **14**, 1125 (2018).
- [10] I. V. Solov'yev, S. A. Nikolaev, A. V. Ushakov, V. Y. Irkhin, A. Tanaka, and S. V. Streltsov, Microscopic origins and stability of ferromagnetism in $\text{Co}_3\text{Sn}_2\text{S}_2$, *Phys. Rev. B* **105**, 014415 (2022).
- [11] K. Kuroda, T. Tomita, M.-T. Suzuki, C. Bareille, A. Nugroho, P. Goswami, M. Ochi, M. Ikhlas, M. Nakayama, S. Akebi, R. Noguchi, R. Ishii, N. Inami, K. Ono, H. Kumigashira, A. Varykhalov, T. Muro, T. Koretsune, R. Arita, S. Shin *et al.*, Evidence for magnetic Weyl fermions in a correlated metal, *Nat. Mater.* **16**, 1090 (2017).
- [12] L. Ye, M. Kang, J. Liu, F. Von Cube, C. R. Wicker, T. Suzuki, C. Jozwiak, A. Bostwick, E. Rotenberg, D. C. Bell, L. Fu, R. Comin, and J. G. Checkelsky, Massive Dirac fermions in a ferromagnetic kagome metal, *Nature (London)* **555**, 638 (2018).
- [13] Z. Lin, J.-H. Choi, Q. Zhang, W. Qin, S. Yi, P. Wang, L. Li, Y. Wang, H. Zhang, Z. Sun, L. Wei, S. Zhang, T. Guo, Q. Lu, J.-H. Cho, C. Zeng, and Z. Zhang, Flat bands and emergent ferromagnetic ordering in Fe_3Sn_2 kagome lattices, *Phys. Rev. Lett.* **121**, 096401 (2018).
- [14] M. Kang, L. Ye, S. Fang, J.-S. You, A. Levitan, M. Han, J. I. Facio, C. Jozwiak, A. Bostwick, E. Rotenberg, M. K. Chan, R. D. McDonald, D. Graf, K. Kaznatcheev, E. Vescovo, D. C. Bell, J. Kaxiras, E. van den Brink, M. Richter, M. P. Ghimire, J. G. Checkelsky *et al.*, Dirac fermions and flat bands in the ideal kagome metal FeSn , *Nat. Mater.* **19**, 163 (2020).
- [15] T. Chen, S. Minami, A. Sakai, Y. Wang, Z. Feng, T. Nomoto, M. Hirayama, R. Ishii, T. Koretsune, R. Arita, and S. Nakatsuji, Large anomalous Nernst effect and nodal plane in an iron-based kagome ferromagnet, *Sci. Adv.* **8**, eabk1480 (2022).
- [16] A. Bolens and N. Nagaosa, Topological states on the breathing kagome lattice, *Phys. Rev. B* **99**, 165141 (2019).
- [17] M. Ezawa, Higher-order topological insulators and semimetals on the breathing kagome and pyrochlore lattices, *Phys. Rev. Lett.* **120**, 026801 (2018).
- [18] H. Tanaka, Y. Fujisawa, K. Kuroda, R. Noguchi, S. Sakuragi, C. Bareille, B. Smith, C. Cacho, S. W. Jung, T. Muro, Y. Okada, and T. Kondo, Three-dimensional electronic structure in ferromagnetic Fe_3Sn_2 with breathing kagome bilayers, *Phys. Rev. B* **101**, 161114(R) (2020).
- [19] H. Tasaki, Hubbard model and the origin of ferromagnetism, *Eur. Phys. J. B* **64**, 365 (2008).
- [20] A. Mielke, Ferromagnetic ground states for the Hubbard model on line graphs, *J. Phys. A: Math. Gen.* **24**, L73 (1991).
- [21] Y. Nagaoka, Ferromagnetism in a narrow, almost half-filled s band, *Phys. Rev.* **147**, 392 (1966).
- [22] B. Sales, B. Sagarov, M. McGuire, D. Singh, and D. Parker, Ferromagnetism of Fe_3Sn and alloys, *Sci. Rep.* **4**, 7024 (2014).
- [23] B. Fayyazi, K. P. Skokov, T. Faske, I. Opahle, M. Duerrschabel, T. Helbig, I. Soldatov, U. Rohrmann, L. Molina-Luna, K. Güth, H. Zhang, W. Donner, R. Schäfer, and O. Gutfleisch, Experimental and computational analysis of binary Fe-Sn ferromagnetic compounds, *Acta Mater.* **180**, 126 (2019).
- [24] L. Prodan, D. M. Evans, S. M. Griffin, A. Östlin, M. Althaler, E. Lysne, I. G. Filippova, S. Shova, L. Chioncel, V. Tsurkan, and I. Kézsmárki, Large ordered moment with strong easy-plane anisotropy and vortex-domain pattern in the kagome ferromagnet Fe_3Sn , *Appl. Phys. Lett.* **123**, 021901 (2023).
- [25] O. Y. Vekilova, B. Fayyazi, K. P. Skokov, O. Gutfleisch, C. Echevarria-Bonet, J. M. Barandiarán, A. Kovacs, J. Fischbacher, T. Schrefl, O. Eriksson, and H. C. Herper, Tuning the magnetocrystalline anisotropy of Fe_3Sn by alloying, *Phys. Rev. B* **99**, 024421 (2019).
- [26] A. Low, S. Ghosh, S. Ghorai, and S. Thirupathiah, Effect of electron-phonon scattering on the anomalous Hall conductivity of Fe_3Sn : A kagome ferromagnetic metal, *Phys. Rev. B* **108**, 094404 (2023).
- [27] L. Prodan, A. Chmeruk, L. Chioncel, V. Tsurkan, and I. Kézsmárki, Anisotropic charge transport in the easy-plane kagome ferromagnet Fe_3Sn , *Phys. Rev. B* **110**, 094407 (2024).
- [28] S. Kurosawa, T. Higo, S. Saito, R. Uesugi, and S. Nakatsuji, Large spontaneous magneto-thermoelectric effect in epitaxial thin films of the topological kagome ferromagnet Fe_3Sn , *Phys. Rev. Mater.* **8**, 054206 (2024).
- [29] S. Samanta, H. Park, C. Lee, S. Jeon, H. Cui, Y. Yao, J. Hwang, K. Choi, and H.-S. Kim, Emergence of flat bands and ferromagnetic fluctuations via orbital-selective electron correlations in Mn-based kagome metal, *Nat. Commun.* **15**, 5376 (2024).
- [30] S. A. Ekahana, Y. Soh, A. Tamai, D. Gosálbez-Martínez, M. Yao, A. Hunter, W. Fan, Y. Wang, J. Li, A. Kleibert, C. A. F. Vaz, J. Ma, H. Lee, Y. Xiong, O. V. Yazyev, F. Baumberger, M. Shi, and G. Aepli, Anomalous electrons in a metallic kagome ferromagnet, *Nature (London)* **627**, 67 (2024).
- [31] R. M. Martin, *Electronic Structure: Basic Theory and Practical Methods* (Cambridge University Press, Cambridge, 2004).

- [32] A. Georges, G. Kotliar, W. Krauth, and M. J. Rozenberg, Dynamical mean-field theory of strongly correlated fermion systems and the limit of infinite dimensions, *Rev. Mod. Phys.* **68**, 13 (1996).
- [33] G. Kotliar, S. Y. Savrasov, K. Haule, V. S. Oudovenko, O. Parcollet, and C. A. Marianetti, Electronic structure calculations with dynamical mean-field theory, *Rev. Mod. Phys.* **78**, 865 (2006).
- [34] K. Held, Electronic structure calculations using dynamical mean field theory, *Adv. Phys.* **56**, 829 (2007).
- [35] J. M. Wills, M. Alouani, P. Andersson, A. Delin, O. Eriksson, and O. Grechnev, *In Full-Potential Electronic Structure Method*, edited by H. Dreysse, Electronic Structure and Physical Properties of Solids: Springer Series in Solid-State Sciences (Springer-Verlag, Berlin, 2010).
- [36] O. Grånäs, I. Di Marco, P. Thunström, L. Nordström, O. Eriksson, T. Björkman, and J. Wills, Charge self-consistent dynamical mean-field theory based on the full-potential linear muffin-tin orbital method: Methodology and applications, *Comput. Mater. Sci.* **55**, 295 (2012).
- [37] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized gradient approximation made simple, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [38] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized gradient approximation made simple [Phys. Rev. Lett. **77**, 3865 (1996)], *Phys. Rev. Lett.* **78**, 1396(E) (1997).
- [39] J. P. Perdew and Y. Wang, Accurate and simple analytic representation of the electron-gas correlation energy, *Phys. Rev. B* **45**, 13244 (1992).
- [40] M. I. Katsnelson and A. I. Lichtenstein, Electronic structure and magnetic properties of correlated metals, *Eur. Phys. J. B* **30**, 9 (2002).
- [41] A. Grechnev, I. Di Marco, M. I. Katsnelson, A. I. Lichtenstein, J. Wills, and O. Eriksson, Theory of bulk and surface quasiparticle spectra for Fe, Co, and Ni, *Phys. Rev. B* **76**, 035107 (2007).
- [42] L. V. Pourovskii, M. I. Katsnelson, and A. I. Lichtenstein, Correlation effects in electronic structure of actinide monochalcogenides, *Phys. Rev. B* **72**, 115106 (2005).
- [43] I. Di Marco, J. Minár, J. Braun, M. I. Katsnelson, A. Grechnev, H. Ebert, A. I. Lichtenstein, and O. Eriksson, γ -Mn at the border between weak and strong correlations, *Eur. Phys. J. B* **72**, 473 (2009).
- [44] M. S. Litsarev, I. Di Marco, P. Thunström, and O. Eriksson, Correlated electronic structure and chemical bonding of cerium pnictides and γ -Ce, *Phys. Rev. B* **86**, 115116 (2012).
- [45] V. Drchal, V. Janiš, J. Kudrnovský, V. S. Oudovenko, X. Dai, K. Haule, and G. Kotliar, Dynamical correlations in multi-orbital Hubbard models: Fluctuation exchange approximations, *J. Phys.: Condens. Matter* **17**, 61 (2004).
- [46] J. Braun, J. Minár, H. Ebert, M. I. Katsnelson, and A. I. Lichtenstein, Spectral function of ferromagnetic $3d$ metals: A self-consistent LSDA + DMFT approach combined with the one-step model of photoemission, *Phys. Rev. Lett.* **97**, 227601 (2006).
- [47] I. Di Marco, J. Minár, S. Chadov, M. I. Katsnelson, H. Ebert, and A. I. Lichtenstein, Correlation effects in the total energy, the bulk modulus, and the lattice constant of a transition metal: Combined local-density approximation and dynamical mean-field theory applied to Ni and Mn, *Phys. Rev. B* **79**, 115111 (2009).
- [48] M. I. Katsnelson, V. Y. Irkhin, L. Chioncel, A. I. Lichtenstein, and R. A. de Groot, Half-metallic ferromagnets: From band structure to many-body effects, *Rev. Mod. Phys.* **80**, 315 (2008).
- [49] S. Ghosh, S. Ershadrad, V. Borisov, and B. Sanyal, Unraveling effects of electron correlation in two-dimensional Fe_nGeTe_2 ($n = 3, 4, 5$) by dynamical mean field theory, *npj Comput. Mater.* **9**, 86 (2023).
- [50] D. Redka, S. A. Khan, E. Martino, X. Mettan, L. Ciric, D. Tolj, T. Ivšić, A. Held, M. Caputo, E. B. Guedes, V. N. Strocov, I. Di Marco, H. Ebert, H. P. Huber, J. H. Dil, L. Forró, and J. Minár, Interplay between disorder and electronic correlations in compositionally complex alloys, *Nat. Commun.* **15**, 7983 (2024).
- [51] V. I. Anisimov, F. Aryasetiawan, and A. I. Lichtenstein, First-principles calculations of the electronic structure and spectra of strongly correlated systems: the LDA+ U method, *J. Phys.: Condens. Matter* **9**, 767 (1997).
- [52] A. I. Lichtenstein, M. I. Katsnelson, and G. Kotliar, Finite-temperature magnetism of transition metals: An *ab initio* dynamical mean-field theory, *Phys. Rev. Lett.* **87**, 067205 (2001).
- [53] I. Leonov, A. I. Poteryaev, V. I. Anisimov, and D. Vollhardt, Electronic correlations at the α - γ structural phase transition in paramagnetic iron, *Phys. Rev. Lett.* **106**, 106405 (2011).
- [54] D. Di Sante, B. Kim, W. Hanke, T. Wehling, C. Franchini, R. Thomale, and G. Sangiovanni, Electronic correlations and universal long-range scaling in kagome metals, *Phys. Rev. Res.* **5**, L012008 (2023).
- [55] I. Di Marco, A. Held, S. Keshavarz, Y. O. Kvashnin, and L. Chioncel, Half-metallicity and magnetism in the $\text{Co}_2\text{MnAl}/\text{CoMnVAI}$ heterostructure, *Phys. Rev. B* **97**, 035105 (2018).
- [56] J. Schött, I. L. M. Loch, E. Lundin, O. Grånäs, O. Eriksson, and I. Di Marco, Analytic continuation by averaging Padé approximants, *Phys. Rev. B* **93**, 075104 (2016).
- [57] Y. O. Kvashnin, O. Grånäs, I. Di Marco, M. I. Katsnelson, A. I. Lichtenstein, and O. Eriksson, Exchange parameters of strongly correlated materials: Extraction from spin-polarized density functional theory plus dynamical mean-field theory, *Phys. Rev. B* **91**, 125133 (2015).
- [58] A. Liechtenstein, M. Katsnelson, V. Antropov, and V. Gubanov, Local spin density functional approach to the theory of exchange interactions in ferromagnetic metals and alloys, *J. Magn. Magn. Mater.* **67**, 65 (1987).
- [59] Y. O. Kvashnin, A. Bergman, A. I. Lichtenstein, and M. I. Katsnelson, Relativistic exchange interactions in CrX_3 ($X = \text{Cl}, \text{Br}, \text{I}$) monolayers, *Phys. Rev. B* **102**, 115162 (2020).
- [60] T. Moriya, Anisotropic superexchange interaction and weak ferromagnetism, *Phys. Rev.* **120**, 91 (1960).
- [61] I. Dzyaloshinsky, A thermodynamic theory of “weak” ferromagnetism of antiferromagnetics, *J. Phys. Chem. Solids* **4**, 241 (1958).
- [62] L. Udvardi, L. Szunyogh, K. Palotás, and P. Weinberger, First-principles relativistic study of spin waves in thin magnetic films, *Phys. Rev. B* **68**, 104436 (2003).
- [63] K. Lejaeghere, G. Bihlmayer, T. Björkman, P. Blaha, S. Blügel, V. Blum, D. Caliste, I. E. Castelli, S. J. Clark, A. D. Corso, S. de Gironcoli, T. Deutsch, J. K. Dewhurst, I. D. Marco, C. Draxl, M. Dułak, O. Eriksson, J. A. Flores-Livas, K. F. Garrity, L. Genovese *et al.*, Reproducibility in density

- functional theory calculations of solids, *Science* **351**, aad3000 (2016).
- [64] L. Nordström, M. S. S. Brooks, and B. Johansson, Calculation of orbital magnetism and magnetocrystalline anisotropy energy in YCo_5 , *J. Phys.: Condens. Matter* **4**, 3261 (1992).
- [65] E. R. Ylvisaker, W. E. Pickett, and K. Koepf, Anisotropy and magnetism in the LSDA + U method, *Phys. Rev. B* **79**, 035103 (2009).
- [66] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/xmmr-mfv4> for additional details on the calculations, as well as the results of the optimized lattice parameters and elastic properties.
- [67] S. Keshavarz, J. Schött, A. J. Millis, and Y. O. Kvashnin, Electronic structure, magnetism, and exchange integrals in transition-metal oxides: Role of the spin polarization of the functional in DFT + U calculations, *Phys. Rev. B* **97**, 184404 (2018).
- [68] S. W. Jang, S. Ryee, H. Yoon, and M. J. Han, Charge density functional plus U theory of LaMnO_3 : Phase diagram, electronic structure, and magnetic interaction, *Phys. Rev. B* **98**, 125126 (2018).
- [69] C. Shen, I. Samathrakris, K. Hu, H. K. Singh, N. Fortunato, H. Liu, O. Gutfleisch, and H. Zhang, Thermodynamical and topological properties of metastable Fe_3Sn , *npj Comput. Mater.* **8**, 248 (2022).
- [70] L. Huang and H. Lu, Signatures of Hundness in kagome metals, *Phys. Rev. B* **102**, 125130 (2020).
- [71] Z. Ren, J. Huang, H. Tan, A. Biswas, A. Pulkkinen, Y. Zhang, Y. Xie, Z. Yue, L. Chen, F. Xie, K. Allen, H. Wu, Q. Ren, A. Rajapitamahuni, A. K. Kundu, E. Vescovo, J. Kono, E. Morosan, P. Dai, J.-X. Zhu *et al.*, Persistent flat band splitting and strong selective band renormalization in a kagome magnet thin film, *Nat. Commun.* **15**, 9376 (2024).
- [72] S. Blundell, *Magnetism in Condensed Matter* (Oxford University Press, New York, 2001), pp. 156–157.
- [73] S. Sarkar, F. Cossu, P. Kumari, A. G. Moghaddam, A. Akbari, Y. O. Kvashnin, and I. D. Marco, Magnetism between magnetic adatoms on monolayer NbSe_2 , *2D Mater.* **9**, 045012 (2022).
- [74] G. Skorupskii, F. Orlandi, I. Robredo, M. Jovanovic, R. Yamada, F. Katmer, M. G. Vergniory, P. Manuel, M. Hirschberger, and L. M. Schoop, Designing giant Hall response in layered topological semimetals, *Nat. Commun.* **15**, 10112 (2024).
- [75] R. E. Camley and K. L. Livesey, Consequences of the Dzyaloshinskii-Moriya interaction, *Surf. Sci. Rep.* **78**, 100605 (2023).
- [76] O. Eriksson, A. Bergman, L. Bergqvist, and J. Hellsvik, *Atomistic Spin Dynamics: Foundations and Applications* (Oxford University Press, Oxford, 2017).
- [77] S. Chadov, J. Minár, M. I. Katsnelson, H. Ebert, D. Kädderitzsch, and A. I. Lichtenstein, Orbital magnetism in transition metal systems: The role of local correlation effects, *Europhys. Lett.* **82**, 37001 (2008).
- [78] A. G. Petukhov, I. I. Mazin, L. Chioncel, and A. I. Lichtenstein, Correlated metals and the LDA + U method, *Phys. Rev. B* **67**, 153106 (2003).
- [79] L. Ye, S. Fang, M. Kang, J. Kaufmann, Y. Lee, C. John, P. M. Neves, S. Y. F. Zhao, J. Denlinger, C. Jozwiak, A. Bostwick, E. Rotenberg, E. Kaxiras, D. C. Bell, O. Janson, R. Comin, and J. G. Checkelsky, Hopping frustration-induced flat band and strange metallicity in a kagome metal, *Nat. Phys.* **20**, 610 (2024).
- [80] Y. Xu, X. Jin, J. Xiang, H. Zhang, and F. Tian, DFT + DMFT investigation of the magnetic phase transition in the itinerant ferromagnet Fe_3GaTe_2 , *Phys. Rev. B* **111**, 155142 (2025).
- [81] F. Pollmann, P. Fulde, and K. Shtengel, Kinetic ferromagnetism on a kagome lattice, *Phys. Rev. Lett.* **100**, 136404 (2008).
- [82] P. Jiang, L. Li, Z. Liao, Y. Zhao, and Z. Zhong, Spin direction-controlled electronic band structure in two-dimensional ferromagnetic CrI_3 , *Nano Lett.* **18**, 3844 (2018).
- [83] X. Fu, J. Yu, Q. Zhang, Z. Li, and Z. Liu, The magnetic property and anomalous Hall effect of polycrystalline Fe_3Sn , *J. Phys. Chem. Solids* **198**, 112473 (2025).
- [84] T. Yu, R. Liu, Y. Peng, P. Zheng, G. Wang, X. Ma, Z. Yuan, and Z. Yin, Correlated electronic structure of the kagome metal Mn_3Sn , *Phys. Rev. B* **106**, 205103 (2022).
- [85] J. Kuneš, I. Leonov, M. Kollar, K. Byczuk, V. Anisimov, and D. Vollhardt, Dynamical mean-field approach to materials with strong electronic correlations, *Eur. Phys. J.: Spec. Top.* **180**, 5 (2009).
- [86] M. Liu, Z. Wang, and J.-J. Zhou, Weak electronic correlations in the kagome superconductor AV_3Sb_5 ($A = \text{K}, \text{Rb}, \text{Cs}$), *Phys. Rev. B* **105**, 235130 (2022).
- [87] J. Zhao, W. Wu, Y. Wang, and S. A. Yang, Electronic correlations in the normal state of the kagome superconductor KV_3Sb_5 , *Phys. Rev. B* **103**, L241117 (2021).
- [88] T. Yu, J. Lai, X. Liu, P. Liu, X.-Q. Chen, and Y. Sun, Magnetism and weak electronic correlations in the kagome metal ScV_6Sn_6 , *Phys. Rev. B* **109**, 195145 (2024).
- [89] S. Sharma, L. Chioncel, and I. Di Marco, Exploring strong electronic correlations in the breathing kagome metal Fe_3Sn , *Materials Cloud Archive* **2025.82** (2025).