UNIVERSITÄT AUGSBURG
Universitätsbibliothek

OPEN ACCESS
OPUS AUGSBURG

Suppression of the Kondo state in YbRh2Si2 by large magnetic fields

Y. Tokiwa, Philipp Gegenwart, F. Weickert, R. Küchler, J. Custers, J. Ferstl, C. Geibel, F. Steglich

Angaben zur Veröffentlichung / Publication details:

Tokiwa, Y., Philipp Gegenwart, F. Weickert, R. Küchler, J. Custers, J. Ferstl, C. Geibel, and F. Steglich. 2004. "Suppression of the Kondo state in YbRh2Si2 by large magnetic fields." *Journal of Magnetism and Magnetic Materials* 272-276: E87–88. https://doi.org/10.1016/j.jmmm.2003.12.398.

Nutzungsbedingungen / Terms of use:

CC BY-NC-ND 4.0

Dieses Dokument wird unter folgenden Bedingungen zur Verfügung gestellt: / This document is made available under these conditions:
CC-BY-NC-ND 4.0: Creative Commons: Namensnennung - Nicht kommerziell - Keine Bearbeitung
Weitere Informationen finden Sie unter: / For more information see:
https://creativecommons.org/licenses/by-nc-nd/4.0/deed.de

Suppression of the Kondo state in $YbRh_2Si_2$ by large magnetic fields

Y. Tokiwa*, P. Gegenwart, F. Weickert, R. Küchler, J. Custers, J. Ferstl, C. Geibel, F. Steglich

Max-Planck Institute for Chemical Physics of Solids, Noethnitzer Str. 40, D-01187 Dresden, Germany

Abstract

We present DC-magnetization, $M(B)$, magnetostriction, $\Delta L(B)/L$, and magnetoresistance $\rho(T,B)$ measurements on high-quality single crystals of $YbRh_2Si_2$ in magnetic fields up to 18 T and at temperatures down to 15 mK. At $B^\star \approx 9.5$ T, both $M(B)$ and $\Delta L(B)/L$ show pronounced changes of their slopes, indicative for a broadened phase transition. For fields above $B^\star$, the coefficient A of the Fermi liquid behavior $\Delta\rho = \rho_0 + A(B)T^2$ is reduced to very small values, indicating the suppression of the Heavy Fermion state.

High-field studies in Ce- and U-based compounds have revealed interesting phenomena such as metamagnetic transitions in $CeRu_2Si_2$ and UPt_3 [1,2]. In the case of Yb-based valence-fluctuating compounds with characteristic temperatures $T_0 \gtrsim 70$ K like $YbCu_{5-x}Ag_x$, the application of large magnetic fields induces a metamagnetic-like cross-over to a stable Yb^{3+} state with localized magnetic moments [3]. Here we report on the high-field behavior of $YbRh_2Si_2$ which is the only stoichiometric Yb-based HF system with a characteristic Kondo temperature of the order of 25 K [4]. It is located very close to a quantum critical point (QCP), related to very weak antiferromagnetic order at $T_N = 70$ mK. A very small critical magnetic field $B_c = 0.06$ T, applied perpendicular to the tetragonal c-axis, i.e. in the magnetic easy-plane, is sufficient to drive the system through the field-induced QCP [5]. For $B > B_c$ a Landau Fermi liquid (LFL) state is induced with a strongly field-dependent heavy quasiparticle mass [5].

In order to study the high-field properties in $YbRh_2Si_2$, we performed DC-magnetization $M(B)$, magnetostriction $\Delta L(B)/L$, and magnetoresistance $\rho(T,B)$ measurements on high-quality single crystals ($\rho_0 = 1\,\mu\Omega$ cm) of $YbRh_2Si_2$, prepared as described earlier [4]. For the magnetization and magnetostriction measurements a high-resolution Faraday magnetometer and a CuBe dilatometer have been adapted to dilution refrigerators, respectively. The resistivity was measured with the standard four-terminal AC technique.

The low-T magnetization $M(B)$ shows two anomalies (Fig. 1). The low-field anomaly near at 0.09 T is related to the QCP and indicates the polarization of a small moment of $0.1\mu_B$. The remaining moment is still fluctuating and contributes to the strongly enhanced Pauli-paramagnetic susceptibility [5]. Here, we concentrate on the high-field anomaly. The susceptibility $\chi = dM/dB$ and magnetostriction coefficient $\lambda = d(\Delta L(B)/L)/dB$ show step-like anomalies at $B^\star \approx 9.5$ T, indicative for a broadened second-order phase transition. The polarization at $B^\star$ amounts to $1\mu_B$. With increasing temperature, the kink in $M(B)$ becomes broader but $B^\star$ is not shifted up to 2 K. For $B^\star$ the magnetostriction coefficient λ is negative, indicating a shrinking of the Yb-ions. Since the ionic radius of magnetic Yb^{3+} configuration is smaller than that of the non-magnetic

*Corresponding author. Fax: +49-351-4646-3119.
E-mail address: ytokiwa@cpfs.mpg.de (Y. Tokiwa).

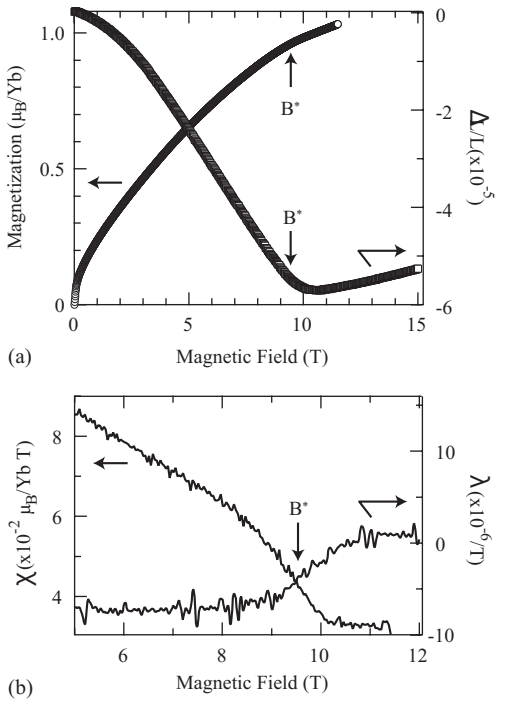

Fig. 1. Magnetization (at 80 mK, left axis) and magnetostriction (at 15 mK, right axis) vs magnetic field ($B \perp c$) (a). Susceptibility $\chi = dM/dB$ and magnetostriction coefficient $\lambda = d(\Delta L(B)/L)/dB$ vs B (b). Arrows indicate critical field $B^\star$.

Yb^{2+} one, the effective valency increases with increasing field and reaches 3+ at $B^\star$. The localization of the f-electrons leads to a reduction of the Pauli-paramagnetic contribution to the susceptibility and therefore results in a kink of the magnetization curve.

To get more information on the properties of the heavy quasiparticles around $B^\star$, we analyze the field dependence of the coefficient A, derived from the LFL behavior of the electrical resistivity [5]. As shown in Fig. 2, $A(B)$ is drastically reduced upon increasing B from below to above $B^\star$. Since it has been shown that

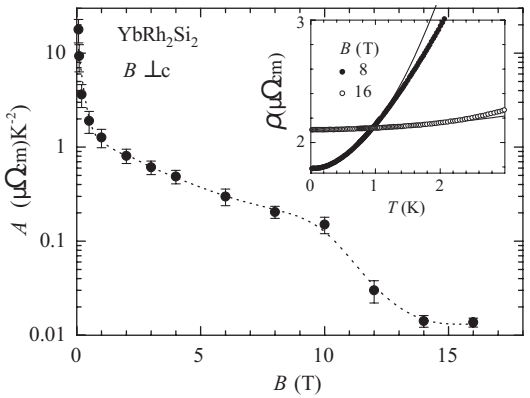

Fig. 2. Magnetic-field dependence of coefficient A (on a logarithmic scale) from Fermi liquid behavior $\rho(T) = \rho_0 + AT^2$ in the electrical resistivity, observed for $B > 0.06$ T ($B \perp c$) [5]. Dotted line is intended as guide to the eyes. Inset shows ρ vs. T for 8 and 16 T. Solid lines represent T^2 behavior.

the scaling relation $A \propto \gamma^2$ holds at least up to 4 T [5], this indicates a step-like decrease of the quasiparticle mass. Using the value for A/γ^2 determined in [5], a γ-coefficient of about 70 mJ mol^{-1} K^{-2}, only, is estimated at 16 T.

To conclude, a broadened phase transition at $B^\star = (9.5 \pm 0.5)$ T is observed in $YbRh_2Si_2$ for fields applied in the easy magnetic plane, which indicates the complete localization of the 4f-electrons and the suppression of the HF state.

References

[1] P. Haen, et al., J. Low Temp. Phys 67 (1987) 391.
[2] P.H. Frings, et al., Phys. Rev B 31 (1985) 4355.
[3] N. Tsujii, et al., Physica B 294–295 (2001) 284.
[4] O. Trovarelli, et al., Phys. Rev. Lett. 85 (2000) 626.
[5] P. Gegenwart, et al., Phys. Rev. Lett. 89 (2002) 056402.